


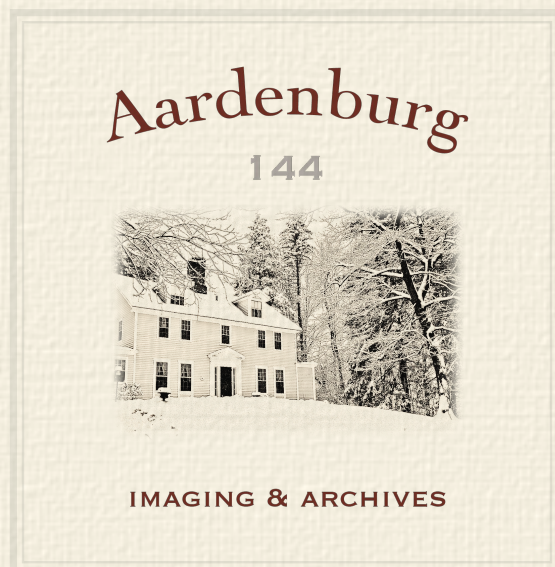

Accelerated Light Fading Test Results

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas
with Clearshield® Type C Satin Overcoat*

Sample # AaI_20090203_SN003

160 Megalux-hours completed

Conservation Display Rating *	
Lower Exposure Limit (Megalux hours)	Upper Exposure limit (Megalux hours)
8	56

* Please read document **AaI_2009_0118_TA-01.pdf**, “An Overview of the AaI&A Conservation Display Ratings”, located on the Documents page of the AaI&A website for an explanation of the conservation display ratings.

Document #: AaI_20090203_SN003Lf.pdf Rev: June 4, 2012

Test Print Prepared by: AaI&A member

Copyright 2012. This report has been prepared for the exclusive use of members of Aardenburg Imaging & Archives. Members may share this information with other members, friends, colleagues, and individual clients. It may also be distributed to groups for educational purposes (classes, lectures, educational seminars. etc). However, all contents including but not limited to Conservation Display Ratings may not be posted to web sites and may not be reproduced or distributed for corporate research, marketing, or other promotional purposes without written permission from Aardenburg Imaging & Archives.

For more information please contact: info@aardenburg-imaging.com



About this Report

This report contains light fastness information about a single test print produced by a specific digital printing system. “System” refers to all hardware, software, and materials used to make the finished print. The hardware, software, material components, and printmaker’s skills contribute to the final image quality and image permanence. The tested sample is made with current or recently discontinued stocks of commercially available products unless otherwise stated. Each sample has been prepared by Aardenburg Imaging & Archives or one of its members in accordance with customary print making practices unless otherwise noted. The sample may also contain additional finishing materials such as overcoats and laminates which are also noted when used. Finally, the sample has been tested under standardized conditions that are defined on the Sample Description page (see page 2). AaI&A makes every effort to ensure but cannot guarantee that the samples are properly identified and documented and that test results are accurate. For this reason, AaI&A also strives to test independently produced sample replicates in order to increase sampling confidence and to provide information on process variability. Please compare the results in this report to replicate test samples when the data become available.

Understanding the Test Results



AaI_StandardColorSet(v2)forSRGB.tif

The magnitude and visual appearance of fading depends not only on the chosen printing system but the chosen image as well. In other words, different images are comprised of different colors, and the fading relationships between those colors dictate how the image will look as it fades. The sample print in this test report was made by reproducing the digital image shown on the left. It contains 30 standard colors. 24 of the colors are colorimetrically matched to the Macbeth ColorChecker™ chart viewed under D50 illumination. The remaining six colors supplement the ColorChecker™ array with four additional skin tone colors, one patch for paper white, and another for maximum black. The additional colors also round out the distribution of L* lightness values in the test target.

Information about the fading characteristics of the product is provided in three ways:

1) ***You can visually assess the fading.*** The target images reproduced in this report are digitally reconstructed from the spectrally measured color data rather than scanning or otherwise reproducing the physical print by conventional techniques. This method ensures a colorimetrically accurate representation of the print appearance as the print fades. A calibrated monitor is recommended to experience the best possible reproduction of the test sample appearance. The side-by-side presentation of the target images simulates looking at the light-exposed print along side a perfect duplicate of the unexposed original print. The “Before/After” Layer mode takes advantage of Adobe Reader Layer technology. Toggle the “Before/After” layer on and off using the layers feature of Adobe Reader to directly switch between the light exposed print colors and the initial print colors for the image located on the right side of each page. Also, use Adobe Reader’s full screen mode to cycle through the pages and “animate” the fading.

2) ***I* Color and tonal accuracy scores are reported.*** This report includes I* metric scores that compare the color and tonal relationships of the light exposed samples to the color and tonal relationships existing in the original print prior to light exposure. Perfect I* scores of 100% can be approached when no significant fading occurs. Average scores above 90% generally indicate excellent retention of original quality, 80% good, 70% fair, etc., but your conclusions may vary depending on your image quality requirements. ***I* color*** rates the retained color accuracy (hue and chroma) while ***I* tone*** rates the retained tonal accuracy (lightness and contrast). The score is on a percentile scale where 100% is a perfect match between the comparison image (e.g., “after” light exposure) and the reference image (e.g., “before” any light exposure). 0% ***I* color*** means no color accuracy is left. 0% ***I* tone*** means essentially no tonality remains and all image information content is lost. Negative I* values have significance as well and contribute to the average I* score when they occur. Negative I* color values mean false color has occurred, for example, when a skin tone turns green or a neutral gray becomes distinctly colorful. Negative I* tone scores mean visual contrast between colors has become inverted (i.e., like the tonal relationships in a photographic film negative). Serious image quality problems must arise before false colors and/or tones appear. For more information on the I* metric, please refer to the AaI&A web site.

3) ***Color changes are also reported using the classic color difference model, ΔE .*** Note that ΔE values lose perceptual scaling significance when they become large (e.g., > 15). Also, the ΔE equation does not unambiguously measure changes in image contrast. This limitation is generally not a problem for paints and textiles, but can be a serious oversight when evaluating photographic images. It was a major reason behind the development of the I* metric.



Sample Description

Printer: Epson Stylus Pro 4880


Ink: Epson Ultrachrome K3™ with Vivid Magenta Ink

Media/coating: Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat

Sample #: AaI_20090203_SN003

Test Print Prepared by: AaI&A member, category: amateur

Test Image: AaI_StandardColorSet(v2)forSRGB.tif

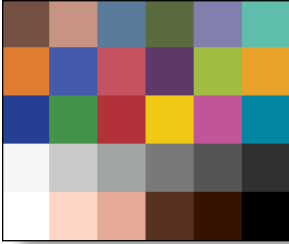

AaI_StandardColorSet(v2)forSRGB.tif

RIP/Driver settings: PSCS3/Epson OEM driver ver. 6.11, Page Setup = Roll Paper, Print Mode = AccuPhoto HD (16 Bit Output), Color Mode = Off (No Color Management), Output Resolution = SuperPhoto 1440 dpi, Platen Gap = Wider

Media Setting: Media type = Premium Glossy Photo Paper (250)

Printed: February 3, 2009

Original print colors measured on: March 12, 2009

Test started on: March 20, 2009

Profile: BC_BCW_9880pk_premiumglossypp_1440dpi_nocoloradj_io.icc

Rendering Intent: Absolute Colorimetric (see notes for further explanation) **Profile type:** generic, <http://www.breathingcolor.com/>

Profile Creation Software: n.a.

Media White Color (UV–included versus UV–excluded) and Maximum Printed Black						
Optical Brighteners present? yes*	L*		a*		b*	
	UV inc	UV exc	UV inc	UV exc	UV inc	UV exc
Maximum Paper White (no colorants printed)	95.0	95.0	0.7	0.7	3.0	3.3
(1) ΔL^* , Δa^* , Δb^* respectively	0.0		0.0		0.3	
(1) Calculated differences, especially for Δb^* , indicate the role and magnitude of fluorescence on original paper color						
Maximum Printed black (UV included)	L* = 22.9		a* = -0.2		b* = -1.0	

Light Source: Phillips Colortone F40T12/C50

Filter/Glazing: Sample framed under Glass**

Light Exposure Cycle: 8 hours on, 4 hours off, twice per 24 hours

Average Illuminance during “on” cycle: 11,854 Lux

Average Temperature: 23.2°C over full test duration, 24.8°C during light exposure

Average Relative humidity: 56.6%RH full test period, 56.7%RH during light exposure

CIELAB measurements: D50 2° observer, Xrite Gretag/Macbeth Spectrolino/Spectroscan


Replicates/Compare to:

Compare the results of AaI_20090203_SN003 (with Clearshield Type C satin overcoat) to AaI_20090203_SN001 (same printer, ink, and canvas batch but no overcoat applied).

Notes/Comments:

* OBAs present in the canvas sizing but not the image receiver layer. These media white point readings include the coating layer. The coating reduces the OBA fluorescence contribution to final reading. Compare these results to the uncoated sample in report # AaI_20090203_SN001Lf.pdf.

** The Phillips Colortone F40T12/C50 fluorescent light source and ordinary glass picture frame glazing yields UVA content and overall spectral power similar to natural 5000°K daylight entering a window and then striking a print that has been framed by **standard acrylic glazing** rather than ordinary glass. Other light sources and/or different glazing options may yield greater or lesser fade rates (generally, a 2-5x increase in fade rate for direct sunlight compared to UV-excluded sources at the same Lux level). The spectral quality of the light can also affect individual colors differently.

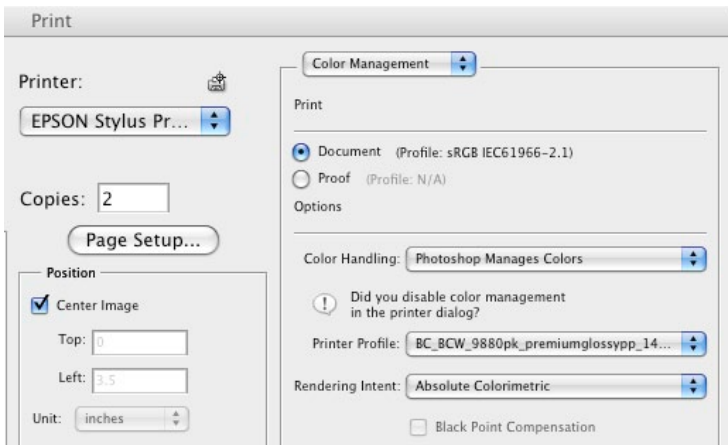


The choice of Absolute Colorimetric rendering produced accurate colors for most patches in the test target but added a small amount of ink density to the media white (A5) patch and forced the black patch (F4) to print like Max black (F5) in the image target. Absolute colorimetric rendering can be a good choice for reproducing artwork on canvas when the artwork does not have important shadow details at low lightness values or vivid color gradients exceeding the printer/ink/media color gamut. Please note that all measurements of media white patch A5 in the image target include the effects of both the small amount of ink density and the Clearshield overcoat properties as well, whereas the media white UV-included and UV-excluded measurements reported on page 2 indicate media white plus coating effects only (i.e., an unprinted but coated area of the media was measured).

May 11, 2009 – 10 megalux hours: Note the slight light bleaching of the media white and highlight values, more pronounced in this coated sample compared to uncoated sample # AaI_2009_SN001. Rather than “yellowing” as would be the case if related to typical optical brightener behavior, the colorimetric values have moved to a slightly “cooler” color (lower b* values). Although the change has triggered the lower limit of the conservation display rating at only 8 megalux hours, this subtle color shift may not be of concern to many users as it is unlikely to continue. Subsequent light exposure test intervals should confirm.

March 06, 2010 – 60 megalux hours: Compare this coated sample to its uncoated control, sample # AaI_20090203_SN001 which has been run side-by-side in testing and was made with the same printer, ink, and canvas batch but has no overcoat applied. Coatings typically should do no harm and often will improve light fade resistance (by reducing photo oxidation rates but sometimes by providing some UV protection as well). In this case the combination of this coating, media, and ink is less lightfast than the media and ink by themselves. Note in particular the increased fade rates in the light skin tones and light neutral patches.

Table to Convert Megalux-hours of Light Exposure to estimated “Years on Display”												
Indoor Light Levels for Print Display		Multiply Mlux-hrs by	Megalux-hours in test									
Light Exposure	Description		10	20	30	40	50	60	70	80	90	100
≤ 10 Lux 24 hours per day	Interior rooms, storage areas, or hallways without windows, illuminated sparingly by artificial lighting	11.42	114	228	342	457	571	685	799	913	1027	1142
50 Lux 12 hours per day	“Museum Standard” display condition	4.57	46	91	137	183	228	274	325	365	411	457
120 Lux 12 hours per day “Kodak Display Years” (1)	Average home illumination level for photos is ~ 60 lux. 90% of all displayed photos do not exceed 120 lux (1).	1.90	19	38	57	76	95	114	133	152	171	190
228 Lux 12 hours per day	Relatively bright home or office. Note the simple 1:1 relationship between “years on display” and Mlux-hr values at this condition.	1.00	10	20	30	40	50	60	70	80	90	100
450 Lux 12 hours per day “WIR Display Years” (2) Also equals 500 lux for 11.8 hours per day	A bright home or commercial office building illumination level is 200-500 lux. Also, good illumination for color critical viewing and color matching tasks begins at about 500 lux.	0.51	5	10	15	20	25	30	35	41	46	51
2000 Lux 12 hours per day	Commercial Gallery. Also, critical color evaluation standards call for 2000 lux and a D50 illumination source.	0.114	1.1	2.3	3.4	4.6	5.7	6.8	8.0	9.1	10.3	11.4
5000 Lux 12 hours per day	E.g., Sunlight through a window striking print at an angle.	0.046	0.5	0.9	1.4	1.8	2.3	2.7	3.2	3.7	4.1	4.6
10,000 Lux 12 hours per day	South-facing window in U.S.A. , e.g., storefront display with photos directly facing window.	0.023	0.2	0.5	0.7	0.9	1.1	1.4	1.6	1.8	2.1	2.3
Light levels commonly encountered in the real world fluctuate widely throughout indoor print display environments and produce large variations in how long it takes for artwork to acquire light-induced damage. Use this table as a guide to estimate how many “years on display” (denoted in red text) it takes to accumulate the light exposure test dosage. Review the test results to decide which Megalux-hour dose has caused fading to your level of concern (e.g., just noticeable, easily noticeable, objectionable, etc.). Then choose the print display description that best represents how your print is likely to be displayed. You may want to obtain a lux meter and make some measurements in your own display environment! Note that as the years of display time increase, light-induced fading can be eclipsed by other serious aging mechanisms such as fading and/or staining caused by heat, humidity, and air pollutants. Mould damage can also occur at high humidity. Even when colorants remain water fast, direct contact with liquids may result in physical deformation and staining of the substrate. Also, temperature and especially humidity cycling can cause physical cracks and/or flaking, etc. Handling damage such as scratching, abrasion, tears and creases, and catastrophic damage by smoke, fire, flood, etc., also degrade print quality over time. Thus, as illumination levels are reduced other forms of degradation take on greater proportion of risk and may appear in shorter time intervals. (1) Eastman Kodak has cited this exposure condition and 90% confidence limit as a rationale for estimating print fading times of traditional color photo materials in typical home display environments. For recent light fading claims regarding its line of pigment-based inkjet printers, Kodak has adopted the higher level of 450lux/12 hours per day which is also used by Wilhelm Imaging Research, Inc. (See below). (2) Wilhelm Imaging Research (WIR) has standardized its light fastness ratings on 450 lux for 12 hours per day in order to estimate the years on display necessary to reach “noticeable” fading. This average light exposure condition, an assumed 75°F/60%RH temperature and humidity level, and WIR’s visually weighted densitometric endpoint criteria set V3.0 has become a de facto industry standard for most predictive light fading estimates in the absence of a published International Standards Organization (ISO) test standard.												

100_{color}/100_{tone}

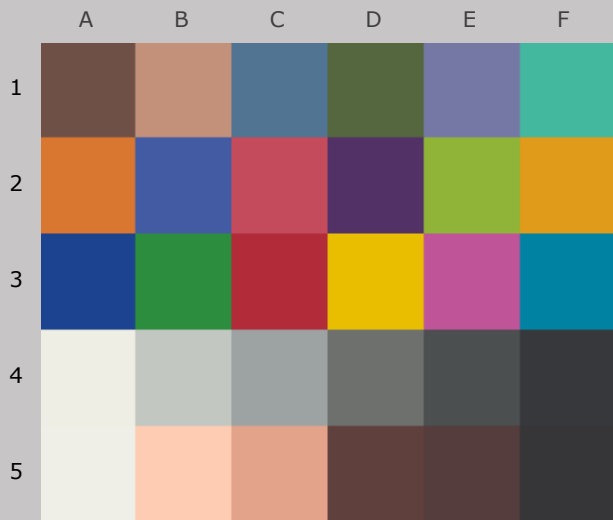


Original Print Colors
(measured before light exposure)




Colors at Zero Megalux-hours of Light Exposure
(same as original print colors)

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*


Original Print Colors as Measured and at Start of Test

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	100.0	0.0	37.4		11.6		11.0	
B1	light Skin	100.0	0.0	64.4		18.0		19.8	
C1	blue sky	100.0	0.0	47.1		-6.7		-20.3	
D1	foliage	100.0	0.0	41.2		-13.4		20.5	
E1	blue flower	100.0	0.0	51.4		6.8		-24.8	
F1	bluish green	100.0	0.0	67.5		-37.9		2.5	
A2	orange	100.0	0.0	60.4		36.3		54.0	
B2	purplish blue	100.0	0.0	39.5		7.7		-41.7	
C2	moderate red	100.0	0.0	49.6		49.7		17.1	
D2	purple	100.0	0.0	26.6		23.0		-25.2	
E2	yellow green	100.0	0.0	68.9		-26.4		56.2	
F2	orange yellow	100.0	0.0	69.8		19.8		69.4	
A3	blue	100.0	0.0	29.4		8.5		-47.3	
B3	green	100.0	0.0	51.7		-41.9		32.6	
C3	red	100.0	0.0	40.7		53.5		27.3	
D3	yellow	100.0	0.0	78.8		6.6		80.9	
E3	magenta	100.0	0.0	51.8		49.2		-15.8	
F3	cyan	100.0	0.0	49.8		-25.1		-25.6	
A4	white	100.0	0.0	94.2		-1.1		5.0	
B4	neutral 8	100.0	0.0	80.2		-2.5		2.7	
C4	neutral 6.5	100.0	0.0	66.7		-2.8		-0.3	
D4	neutral 5	100.0	0.0	46.8		-0.8		0.9	
E4	neutral 3.5	100.0	0.0	33.2		-1.1		-0.5	
F4	black	100.0	0.0	23.6		-0.2		-2.0	
A5	paper white	100.0	0.0	94.1		-0.6		3.0	
B5	skin highlight L*=89	100.0	0.0	85.8		14.6		19.7	
C5	skin highlight L*=75	100.0	0.0	72.9		21.6		23.1	
D5	skin shadow L*=25	100.0	0.0	30.9		13.7		8.2	
E5	skin shadow L*=11	100.0	0.0	28.1		9.6		5.2	
F5	Max Black	100.0	0.0	22.9		-0.2		-1.0	
Summary Results		I*Color	I*tone	ΔE	 AARDENBURG IMAGING & ARCHIVES				
Average Score for all patches		100	100	0.0					
Average Score for the Worst 10% (3 lowest scoring patches)		100	100	0.0					

96.0_{color} / 97.3_{tone}

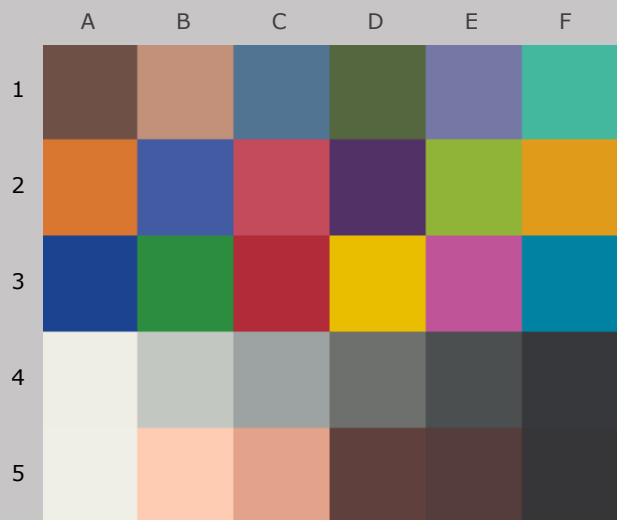

Original Print Colors
(measured before light exposure)

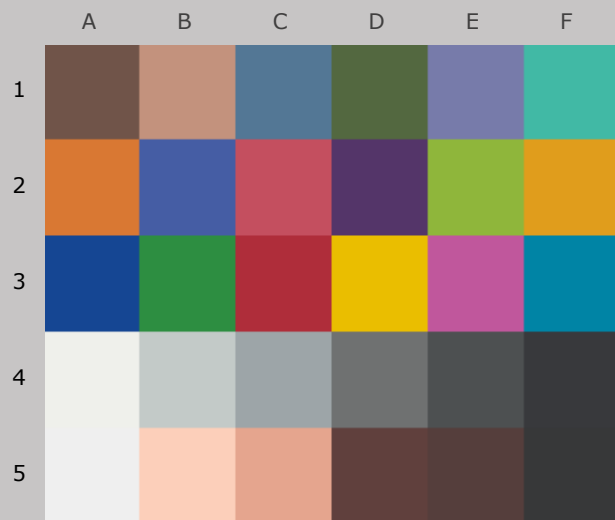

Colors after 10 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

10 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	100.0	0.9	37.4	38.3	11.6	11.4	11.0	10.7
B1	light Skin	96.8	1.6	64.4	65.3	18.0	17.2	19.8	18.7
C1	blue sky	99.6	1.2	47.1	48.2	-6.7	-6.7	-20.3	-20.9
D1	foliage	100.0	0.6	41.2	41.6	-13.4	-13.6	20.5	20.2
E1	blue flower	98.1	1.5	51.4	52.5	6.8	6.5	-24.8	-25.8
F1	bluish green	95.8	2.2	67.5	68.1	-37.9	-37.7	2.5	0.4
A2	orange	98.8	1.4	60.4	60.9	36.3	35.2	54.0	53.4
B2	purplish blue	100.0	0.9	39.5	40.2	7.7	7.6	-41.7	-42.2
C2	moderate red	98.5	1.4	49.6	50.1	49.7	49.2	17.1	15.9
D2	purple	98.4	1.7	26.6	27.9	23.0	22.0	-25.2	-24.7
E2	yellow green	99.4	1.0	68.9	69.3	-26.4	-26.7	56.2	55.4
F2	orange yellow	99.2	1.3	69.8	70.4	19.8	18.8	69.4	69.0
A3	blue	100.0	0.7	29.4	30.0	8.5	8.2	-47.3	-47.6
B3	green	99.8	0.7	51.7	52.1	-41.9	-42.1	32.6	32.0
C3	red	98.8	1.2	40.7	40.7	53.5	53.0	27.3	26.2
D3	yellow	99.3	1.1	78.8	79.2	6.6	5.7	80.9	80.4
E3	magenta	99.0	1.2	51.8	52.5	49.2	48.8	-15.8	-16.7
F3	cyan	97.9	1.4	49.8	50.4	-25.1	-24.8	-25.6	-26.8
A4	white	71.1	3.3	94.2	94.5	-1.1	-0.6	5.0	1.8
B4	neutral 8	81.5	2.3	80.2	80.8	-2.5	-2.6	2.7	0.5
C4	neutral 6.5	90.4	1.6	66.7	67.5	-2.8	-3.1	-0.3	-1.7
D4	neutral 5	97.8	0.9	46.8	47.4	-0.8	-1.0	0.9	0.2
E4	neutral 3.5	100.0	0.6	33.2	33.7	-1.1	-1.3	-0.5	-0.8
F4	black	100.0	0.5	23.6	24.1	-0.2	-0.2	-2.0	-2.2
A5	media white	73.1	3.1	94.1	94.6	-0.6	-0.2	3.0	0.0
B5	skin highlight L*=89	91.3	2.8	85.8	86.6	14.6	13.6	19.7	17.3
C5	skin highlight L*=75	96.0	2.0	72.9	73.8	21.6	20.6	23.1	21.7
D5	skin shadow L*=25	100.0	0.3	30.9	31.1	13.7	13.8	8.2	8.1
E5	skin shadow L*=11	100.0	0.4	28.1	28.6	9.6	9.6	5.2	5.1
F5	Max Black	100.0	0.6	22.9	23.5	-0.2	-0.3	-1.0	-1.2

Summary Results

I*Color

I*tone

ΔE

Average Score for all patches

96.0

97.3


1.3

**Average Score for the Worst 10%
(3 lowest scoring patches)**

75.3


94.2

3.0



AARDENBURG IMAGING
& ARCHIVES

94.7_{color} / 96.2_{tone}

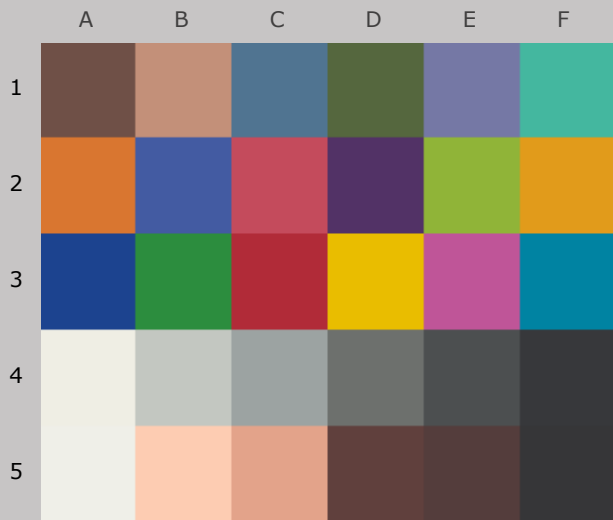


Original Print Colors
(measured before light exposure)




Colors after 20 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*


20 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	100.0	0.4	37.4	37.9	11.6	11.7	11.0	10.9
B1	light Skin	94.5	2.3	64.4	65.6	18.0	16.9	19.8	18.1
C1	blue sky	98.6	1.6	47.1	48.5	-6.7	-6.8	-20.3	-21.1
D1	foliage	100.0	0.6	41.2	41.7	-13.4	-13.7	20.5	20.4
E1	blue flower	97.0	1.8	51.4	52.7	6.8	6.4	-24.8	-26.0
F1	bluish green	93.4	3.1	67.5	68.1	-37.9	-37.7	2.5	-0.5
A2	orange	98.6	1.5	60.4	61.0	36.3	35.0	54.0	53.7
B2	purplish blue	99.4	1.0	39.5	40.2	7.7	7.5	-41.7	-42.4
C2	moderate red	97.6	1.8	49.6	50.1	49.7	49.2	17.1	15.4
D2	purple	99.2	1.5	26.6	27.8	23.0	22.2	-25.2	-24.9
E2	yellow green	99.2	1.1	68.9	69.3	-26.4	-26.8	56.2	55.3
F2	orange yellow	98.4	1.8	69.8	70.6	19.8	18.2	69.4	68.9
A3	blue	98.9	1.0	29.4	29.5	8.5	8.2	-47.3	-48.3
B3	green	99.6	0.9	51.7	52.2	-41.9	-42.2	32.6	31.9
C3	red	99.1	1.1	40.7	40.3	53.5	53.3	27.3	26.3
D3	yellow	98.9	1.5	78.8	79.5	6.6	5.2	80.9	80.8
E3	magenta	99.0	1.3	51.8	52.6	49.2	48.9	-15.8	-16.8
F3	cyan	96.9	1.7	49.8	50.5	-25.1	-25.0	-25.6	-27.2
A4	white	64.5	3.9	94.2	94.5	-1.1	-0.5	5.0	1.2
B4	neutral 8	74.9	3.0	80.2	81.0	-2.5	-2.8	2.7	-0.1
C4	neutral 6.5	86.6	2.0	66.7	67.6	-2.8	-3.2	-0.3	-2.1
D4	neutral 5	96.6	1.1	46.8	47.5	-0.8	-1.0	0.9	0.1
E4	neutral 3.5	100.0	0.4	33.2	33.3	-1.1	-1.3	-0.5	-0.9
F4	black	100.0	0.3	23.6	23.6	-0.2	-0.2	-2.0	-2.3
A5	media white	69.8	3.4	94.1	94.5	-0.6	-0.1	3.0	-0.3
B5	skin highlight L*=89	87.0	3.8	85.8	86.8	14.6	12.9	19.7	16.5
C5	skin highlight L*=75	93.7	2.7	72.9	74.0	21.6	20.0	23.1	21.2
D5	skin shadow L*=25	100.0	0.3	30.9	31.0	13.7	13.9	8.2	8.1
E5	skin shadow L*=11	99.6	0.6	28.1	27.9	9.6	10.1	5.2	5.4
F5	Max Black	100.0	0.4	22.9	22.5	-0.2	-0.2	-1.0	-1.2
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		94.7	96.2						
Average Score for the Worst 10% (3 lowest scoring patches)		69.7	92.0						
ΔE				Page 7					

93.1_{color} / 94.9_{tone}

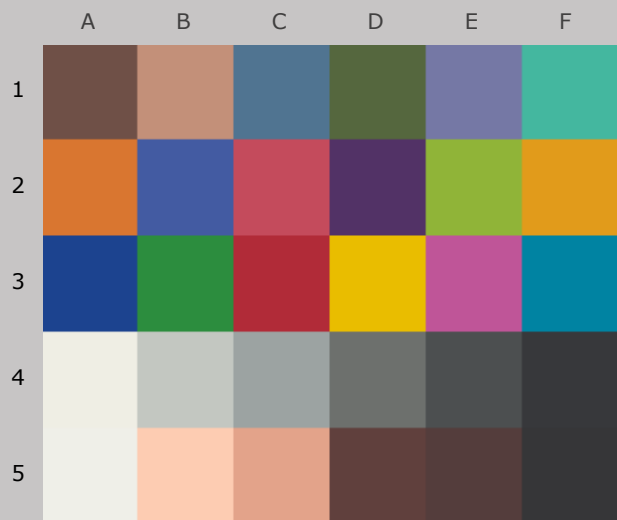


Original Print Colors
(measured before light exposure)

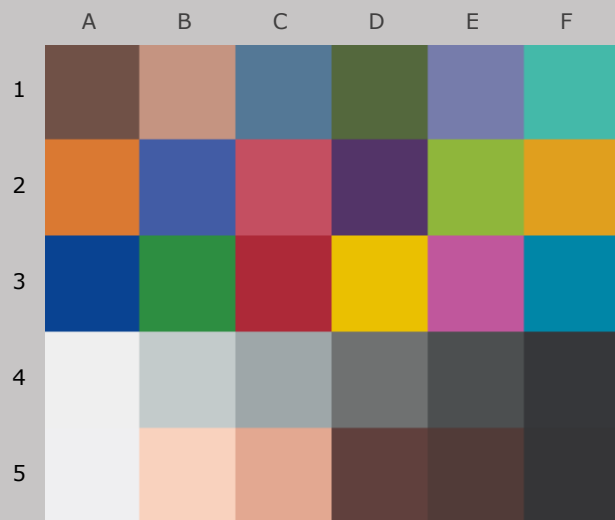


Colors after 30 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

30 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	100.0	0.3	37.4	37.6	11.6	11.9	11.0	11.0
B1	light Skin	92.9	2.8	64.4	65.8	18.0	16.7	19.8	17.8
C1	blue sky	97.4	1.8	47.1	48.6	-6.7	-6.7	-20.3	-21.4
D1	foliage	99.7	0.6	41.2	41.5	-13.4	-14.0	20.5	20.5
E1	blue flower	95.9	2.2	51.4	52.9	6.8	6.5	-24.8	-26.3
F1	bluish green	90.7	4.1	67.5	68.2	-37.9	-37.5	2.5	-1.5
A2	orange	98.3	1.7	60.4	61.1	36.3	34.7	54.0	53.8
B2	purplish blue	98.1	1.4	39.5	39.9	7.7	7.5	-41.7	-43.0
C2	moderate red	97.0	2.2	49.6	50.1	49.7	49.3	17.1	15.0
D2	purple	100.0	1.2	26.6	27.6	23.0	22.5	-25.2	-25.1
E2	yellow green	98.8	1.3	68.9	69.4	-26.4	-27.0	56.2	55.1
F2	orange yellow	97.9	2.3	69.8	70.7	19.8	17.8	69.4	69.1
A3	blue	98.5	1.2	29.4	29.2	8.5	8.2	-47.3	-48.5
B3	green	99.0	1.1	51.7	52.1	-41.9	-42.5	32.6	31.7
C3	red	99.3	1.1	40.7	40.2	53.5	53.6	27.3	26.4
D3	yellow	98.4	2.0	78.8	79.6	6.6	4.8	80.9	80.7
E3	magenta	99.1	1.2	51.8	52.6	49.2	48.9	-15.8	-16.7
F3	cyan	95.7	2.1	49.8	50.5	-25.1	-24.7	-25.6	-27.6
A4	white	57.2	4.6	94.2	94.4	-1.1	-0.4	5.0	0.5
B4	neutral 8	66.9	3.8	80.2	81.2	-2.5	-2.8	2.7	-0.9
C4	neutral 6.5	82.4	2.5	66.7	67.8	-2.8	-3.2	-0.3	-2.5
D4	neutral 5	94.3	1.2	46.8	47.5	-0.8	-1.0	0.9	-0.1
E4	neutral 3.5	99.7	0.5	33.2	33.2	-1.1	-1.3	-0.5	-1.0
F4	black	100.0	0.8	23.6	23.0	-0.2	-0.2	-2.0	-2.5
A5	media white	67.0	3.6	94.1	94.4	-0.6	-0.1	3.0	-0.6
B5	skin highlight L*=89	82.4	5.0	85.8	87.2	14.6	12.5	19.7	15.4
C5	skin highlight L*=75	91.4	3.5	72.9	74.2	21.6	19.6	23.1	20.6
D5	skin shadow L*=25	99.9	0.5	30.9	30.7	13.7	14.2	8.2	8.1
E5	skin shadow L*=11	96.4	1.2	28.1	27.3	9.6	10.4	5.2	5.5
F5	Max Black	100.0	0.7	22.9	22.2	-0.2	-0.2	-1.0	-1.3
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		93.1	94.9						
Average Score for the Worst 10% (3 lowest scoring patches)		63.7	89.6						
ΔE				Page 8					

91.9_{color} / 94.5_{tone}

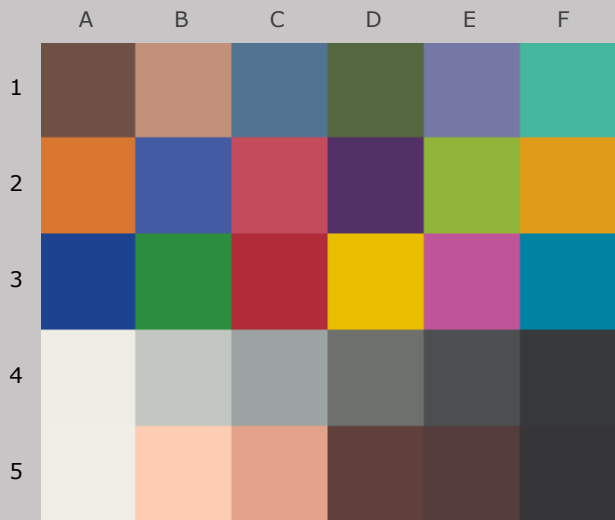


Original Print Colors
(measured before light exposure)




Colors after 40 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

40 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	100.0	0.7	37.4	38.1	11.6	11.8	11.0	10.7
B1	light Skin	91.2	3.4	64.4	66.2	18.0	16.6	19.8	17.3
C1	blue sky	96.8	2.2	47.1	49.0	-6.7	-6.6	-20.3	-21.5
D1	foliage	99.6	0.8	41.2	41.8	-13.4	-13.9	20.5	20.2
E1	blue flower	95.4	2.5	51.4	53.3	6.8	6.4	-24.8	-26.4
F1	bluish green	88.6	4.9	67.5	68.5	-37.9	-37.2	2.5	-2.3
A2	orange	97.7	2.2	60.4	61.4	36.3	34.4	54.0	53.4
B2	purplish blue	98.8	1.3	39.5	40.3	7.7	7.4	-41.7	-42.7
C2	moderate red	96.2	2.6	49.6	50.4	49.7	49.2	17.1	14.6
D2	purple	100.0	1.1	26.6	27.6	23.0	22.9	-25.2	-25.4
E2	yellow green	98.1	1.8	68.9	69.6	-26.4	-27.0	56.2	54.6
F2	orange yellow	97.4	2.7	69.8	71.1	19.8	17.4	69.4	69.0
A3	blue	98.9	1.1	29.4	29.8	8.5	7.8	-47.3	-48.1
B3	green	98.5	1.5	51.7	52.4	-41.9	-42.5	32.6	31.4
C3	red	98.5	1.4	40.7	40.4	53.5	53.5	27.3	25.9
D3	yellow	97.9	2.5	78.8	80.0	6.6	4.4	80.9	80.3
E3	magenta	99.2	1.6	51.8	53.1	49.2	48.7	-15.8	-16.5
F3	cyan	94.6	2.6	49.8	50.8	-25.1	-24.6	-25.6	-28.0
A4	white	52.0	5.1	94.2	94.7	-1.1	-0.2	5.0	0.0
B4	neutral 8	59.6	4.5	80.2	81.5	-2.5	-2.7	2.7	-1.6
C4	neutral 6.5	78.0	3.0	66.7	68.1	-2.8	-3.3	-0.3	-2.9
D4	neutral 5	92.4	1.6	46.8	47.9	-0.8	-1.0	0.9	-0.3
E4	neutral 3.5	98.8	0.6	33.2	33.4	-1.1	-1.3	-0.5	-1.1
F4	black	100.0	0.5	23.6	23.7	-0.2	-0.2	-2.0	-2.4
A5	media white	64.1	4.0	94.1	94.7	-0.6	0.0	3.0	-0.8
B5	skin highlight L*=89	79.2	5.9	85.8	87.6	14.6	12.2	19.7	14.7
C5	skin highlight L*=75	89.3	4.3	72.9	74.8	21.6	19.4	23.1	19.9
D5	skin shadow L*=25	99.8	0.6	30.9	31.2	13.7	14.2	8.2	8.0
E5	skin shadow L*=11	97.9	0.8	28.1	27.9	9.6	10.3	5.2	5.3
F5	Max Black	100.0	0.5	22.9	22.5	-0.2	-0.1	-1.0	-1.4
Summary Results		I*Color	I*tone	ΔE	AARDENBURG IMAGING & ARCHIVES Page 9				
Average Score for all patches		91.9	94.5	2.3					
Average Score for the Worst 10% (3 lowest scoring patches)		58.6	88.2	5.3					

90.7_{color} / 94.1_{tone}

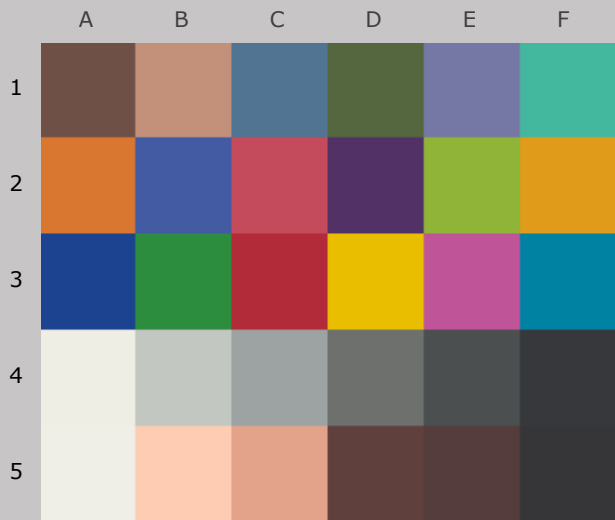

Original Print Colors
(measured before light exposure)



Colors after 50 Megalux-hours
light exposure


*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

50 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	100.0	0.8	37.4	38.1	11.6	11.8	11.0	10.6
B1	light Skin	89.6	3.8	64.4	66.3	18.0	16.5	19.8	16.8
C1	blue sky	95.3	2.5	47.1	49.1	-6.7	-6.7	-20.3	-21.9
D1	foliage	99.2	1.0	41.2	41.9	-13.4	-13.9	20.5	20.0
E1	blue flower	94.5	2.8	51.4	53.4	6.8	6.3	-24.8	-26.6
F1	bluish green	86.3	5.8	67.5	68.6	-37.9	-37.0	2.5	-3.2
A2	orange	97.6	2.4	60.4	61.5	36.3	34.3	54.0	53.4
B2	purplish blue	98.9	1.4	39.5	40.6	7.7	7.2	-41.7	-42.5
C2	moderate red	95.5	3.0	49.6	50.5	49.7	49.3	17.1	14.3
D2	purple	100.0	1.3	26.6	27.8	23.0	22.8	-25.2	-25.1
E2	yellow green	97.1	2.5	68.9	69.7	-26.4	-27.1	56.2	54.0
F2	orange yellow	97.0	3.1	69.8	71.3	19.8	17.2	69.4	68.9
A3	blue	98.6	1.2	29.4	29.8	8.5	7.6	-47.3	-48.1
B3	green	97.8	1.8	51.7	52.4	-41.9	-42.6	32.6	31.1
C3	red	98.3	1.6	40.7	40.4	53.5	53.7	27.3	25.8
D3	yellow	97.4	2.9	78.8	80.1	6.6	4.2	80.9	79.8
E3	magenta	99.2	1.7	51.8	53.3	49.2	48.5	-15.8	-16.3
F3	cyan	93.5	3.1	49.8	50.9	-25.1	-24.4	-25.6	-28.4
A4	white	47.0	5.6	94.2	94.7	-1.1	-0.1	5.0	-0.5
B4	neutral 8	53.4	5.1	80.2	81.7	-2.5	-2.7	2.7	-2.2
C4	neutral 6.5	74.2	3.3	66.7	68.2	-2.8	-3.3	-0.3	-3.2
D4	neutral 5	90.9	1.8	46.8	48.0	-0.8	-1.0	0.9	-0.4
E4	neutral 3.5	97.5	1.0	33.2	33.9	-1.1	-1.2	-0.5	-1.3
F4	black	99.9	0.6	23.6	23.9	-0.2	-0.1	-2.0	-2.5
A5	media white	61.3	4.2	94.1	94.7	-0.6	0.1	3.0	-1.1
B5	skin highlight L*=89	75.7	6.8	85.8	87.9	14.6	11.9	19.7	13.9
C5	skin highlight L*=75	87.1	5.0	72.9	75.0	21.6	19.1	23.1	19.3
D5	skin shadow L*=25	98.7	0.8	30.9	31.2	13.7	14.2	8.2	7.8
E5	skin shadow L*=11	99.0	0.7	28.1	28.5	9.6	10.1	5.2	4.9
F5	Max Black	100.0	0.4	22.9	22.9	-0.2	-0.2	-1.0	-1.4
Summary Results		I*Color	I*tone	ΔE	AARDENBURG IMAGING & ARCHIVES				
Average Score for all patches		90.7	94.1	2.6					
Average Score for the Worst 10% (3 lowest scoring patches)		53.9	87.2	6.1					

Page 10

89.5_{color} / 93.3_{tone}

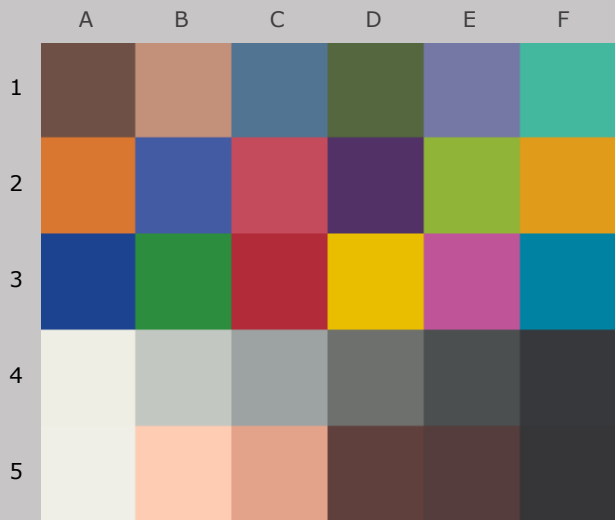


Original Print Colors
(measured before light exposure)




Colors after 60 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

60 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	99.1	1.0	37.4	38.2	11.6	11.9	11.0	10.4
B1	light Skin	87.6	4.4	64.4	66.5	18.0	16.4	19.8	16.3
C1	blue sky	94.3	2.7	47.1	49.2	-6.7	-6.7	-20.3	-22.1
D1	foliage	98.4	1.2	41.2	41.9	-13.4	-13.9	20.5	19.8
E1	blue flower	94.1	3.0	51.4	53.6	6.8	6.2	-24.8	-26.7
F1	bluish green	84.1	6.6	67.5	68.6	-37.9	-36.8	2.5	-4.0
A2	orange	97.2	2.6	60.4	61.7	36.3	34.1	54.0	53.2
B2	purplish blue	99.1	1.5	39.5	40.8	7.7	7.1	-41.7	-42.3
C2	moderate red	94.9	3.3	49.6	50.6	49.7	49.4	17.1	13.9
D2	purple	100.0	1.1	26.6	27.7	23.0	23.0	-25.2	-25.2
E2	yellow green	96.6	2.7	68.9	69.8	-26.4	-27.2	56.2	53.7
F2	orange yellow	96.5	3.5	69.8	71.4	19.8	16.9	69.4	68.5
A3	blue	98.4	1.3	29.4	29.8	8.5	7.4	-47.3	-48.0
B3	green	96.9	2.3	51.7	52.5	-41.9	-42.5	32.6	30.5
C3	red	97.8	1.9	40.7	40.4	53.5	53.6	27.3	25.5
D3	yellow	96.9	3.3	78.8	80.2	6.6	3.9	80.9	79.4
E3	magenta	99.1	1.9	51.8	53.5	49.2	48.3	-15.8	-16.1
F3	cyan	92.7	3.3	49.8	51.0	-25.1	-24.3	-25.6	-28.6
A4	white	43.9	5.8	94.2	94.8	-1.1	0.0	5.0	-0.7
B4	neutral 8	47.5	5.7	80.2	81.7	-2.5	-2.7	2.7	-2.8
C4	neutral 6.5	71.2	3.7	66.7	68.4	-2.8	-3.3	-0.3	-3.5
D4	neutral 5	88.9	2.0	46.8	48.2	-0.8	-1.0	0.9	-0.6
E4	neutral 3.5	96.8	1.2	33.2	34.1	-1.1	-1.2	-0.5	-1.3
F4	black	99.3	0.6	23.6	23.8	-0.2	-0.1	-2.0	-2.6
A5	media white	60.4	4.3	94.1	94.8	-0.6	0.1	3.0	-1.2
B5	skin highlight L*=89	72.5	7.6	85.8	88.1	14.6	11.7	19.7	13.1
C5	skin highlight L*=75	85.2	5.6	72.9	75.2	21.6	18.9	23.1	18.7
D5	skin shadow L*=25	97.8	0.9	30.9	31.1	13.7	14.3	8.2	7.7
E5	skin shadow L*=11	98.3	0.7	28.1	28.4	9.6	10.2	5.2	4.9
F5	Max Black	100.0	0.4	22.9	22.7	-0.2	-0.1	-1.0	-1.4
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		89.5	93.3						
Average Score for the Worst 10% (3 lowest scoring patches)		50.6	86.5						
				Page 11					

88.4_{color} / 92.6_{tone}

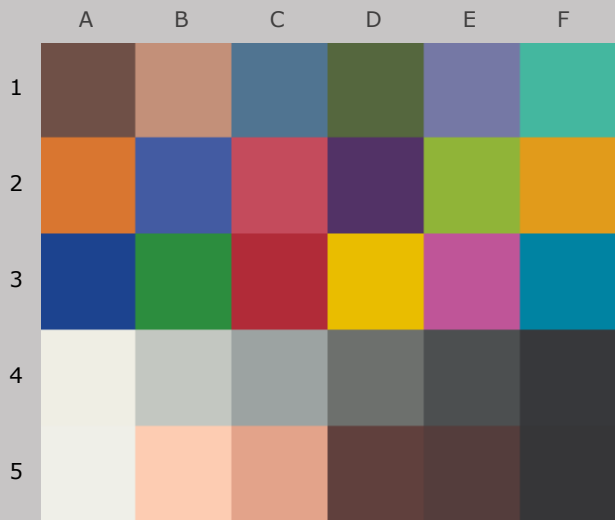


Original Print Colors
(measured before light exposure)




Colors after 70 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*


70 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	98.2	1.1	37.4	38.3	11.6	11.9	11.0	10.3
B1	light Skin	85.8	4.9	64.4	66.7	18.0	16.2	19.8	15.9
C1	blue sky	94.1	2.9	47.1	49.4	-6.7	-6.8	-20.3	-22.1
D1	foliage	98.2	1.2	41.2	41.9	-13.4	-14.0	20.5	19.8
E1	blue flower	94.1	3.2	51.4	53.9	6.8	6.1	-24.8	-26.7
F1	bluish green	81.8	7.5	67.5	68.7	-37.9	-36.5	2.5	-4.8
A2	orange	96.8	2.9	60.4	61.8	36.3	34.0	54.0	53.0
B2	purplish blue	99.0	1.7	39.5	41.0	7.7	6.8	-41.7	-42.0
C2	moderate red	93.9	3.9	49.6	50.7	49.7	49.1	17.1	13.4
D2	purple	98.7	1.9	26.6	28.2	23.0	22.5	-25.2	-24.4
E2	yellow green	96.1	3.1	68.9	69.9	-26.4	-27.2	56.2	53.4
F2	orange yellow	96.0	3.8	69.8	71.6	19.8	16.6	69.4	68.2
A3	blue	98.0	1.5	29.4	29.8	8.5	7.1	-47.3	-47.7
B3	green	96.4	2.6	51.7	52.6	-41.9	-42.7	32.6	30.3
C3	red	97.4	2.1	40.7	40.3	53.5	53.7	27.3	25.2
D3	yellow	96.6	3.7	78.8	80.4	6.6	3.7	80.9	79.3
E3	magenta	99.4	1.9	51.8	53.5	49.2	48.4	-15.8	-15.9
F3	cyan	91.9	3.6	49.8	51.0	-25.1	-24.4	-25.6	-28.9
A4	white	42.3	6.0	94.2	94.7	-1.1	0.1	5.0	-0.9
B4	neutral 8	41.7	6.3	80.2	81.9	-2.5	-2.7	2.7	-3.3
C4	neutral 6.5	68.6	4.0	66.7	68.6	-2.8	-3.4	-0.3	-3.8
D4	neutral 5	88.0	2.1	46.8	48.2	-0.8	-1.0	0.9	-0.7
E4	neutral 3.5	96.0	1.1	33.2	33.8	-1.1	-1.2	-0.5	-1.4
F4	black	98.3	0.7	23.6	23.5	-0.2	-0.2	-2.0	-2.7
A5	media white	60.2	4.3	94.1	94.7	-0.6	0.1	3.0	-1.2
B5	skin highlight L*=89	68.8	8.6	85.8	88.3	14.6	11.4	19.7	12.2
C5	skin highlight L*=75	83.2	6.3	72.9	75.4	21.6	18.6	23.1	18.2
D5	skin shadow L*=25	97.1	1.0	30.9	31.3	13.7	14.3	8.2	7.6
E5	skin shadow L*=11	96.5	0.9	28.1	28.1	9.6	10.4	5.2	4.9
F5	Max Black	100.0	0.6	22.9	22.4	-0.2	-0.2	-1.0	-1.5
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		88.4	92.6						
Average Score for the Worst 10% (3 lowest scoring patches)		48.1	85.0						
				Page 12					

87.1_{color} / 91.8_{tone}

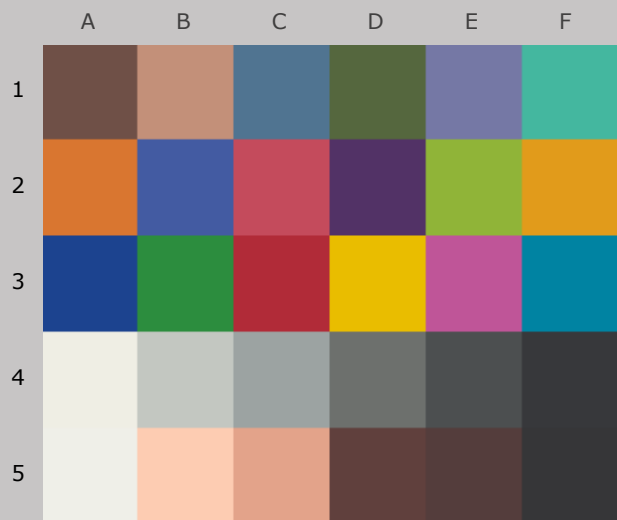

Original Print Colors
(measured before light exposure)

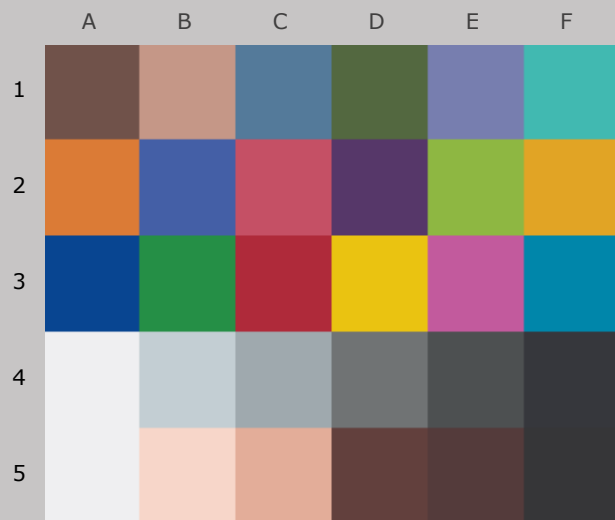

Colors after 80 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

80 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	98.0	1.0	37.4	38.0	11.6	12.1	11.0	10.4
B1	light Skin	84.2	5.4	64.4	66.9	18.0	16.1	19.8	15.5
C1	blue sky	93.1	3.1	47.1	49.4	-6.7	-6.8	-20.3	-22.3
D1	foliage	97.7	1.2	41.2	41.6	-13.4	-14.2	20.5	19.9
E1	blue flower	92.6	3.5	51.4	53.9	6.8	6.1	-24.8	-27.1
F1	bluish green	79.5	8.4	67.5	68.8	-37.9	-36.3	2.5	-5.7
A2	orange	96.7	3.0	60.4	61.8	36.3	33.8	54.0	53.0
B2	purplish blue	98.4	1.8	39.5	40.8	7.7	6.7	-41.7	-42.3
C2	moderate red	93.2	4.2	49.6	50.7	49.7	49.3	17.1	13.1
D2	purple	97.5	2.4	26.6	28.5	23.0	22.3	-25.2	-24.0
E2	yellow green	95.8	3.2	68.9	69.8	-26.4	-27.4	56.2	53.3
F2	orange yellow	95.7	4.1	69.8	71.7	19.8	16.4	69.4	68.2
A3	blue	97.5	1.7	29.4	29.5	8.5	6.9	-47.3	-48.0
B3	green	95.6	3.0	51.7	52.5	-41.9	-42.9	32.6	29.9
C3	red	97.3	2.2	40.7	40.2	53.5	53.9	27.3	25.2
D3	yellow	96.0	4.0	78.8	80.5	6.6	3.5	80.9	78.8
E3	magenta	99.0	1.9	51.8	53.5	49.2	48.2	-15.8	-15.8
F3	cyan	90.9	3.9	49.8	50.9	-25.1	-24.4	-25.6	-29.3
A4	white	40.1	6.2	94.2	94.5	-1.1	0.1	5.0	-1.1
B4	neutral 8	33.8	7.0	80.2	82.0	-2.5	-2.6	2.7	-4.1
C4	neutral 6.5	64.7	4.3	66.7	68.6	-2.8	-3.4	-0.3	-4.1
D4	neutral 5	86.4	2.2	46.8	48.1	-0.8	-1.0	0.9	-0.9
E4	neutral 3.5	95.1	1.1	33.2	33.7	-1.1	-1.2	-0.5	-1.5
F4	black	97.9	0.8	23.6	23.1	-0.2	-0.1	-2.0	-2.7
A5	media white	59.2	4.4	94.1	94.6	-0.6	0.1	3.0	-1.3
B5	skin highlight L*=89	64.7	9.6	85.8	88.4	14.6	11.2	19.7	11.2
C5	skin highlight L*=75	81.4	6.9	72.9	75.5	21.6	18.3	23.1	17.6
D5	skin shadow L*=25	95.5	1.2	30.9	30.9	13.7	14.8	8.2	7.7
E5	skin shadow L*=11	94.5	1.2	28.1	27.8	9.6	10.6	5.2	4.9
F5	Max Black	100.0	0.5	22.9	22.6	-0.2	-0.1	-1.0	-1.4

Summary Results

I*Color

I*tone

ΔE

Average Score for all patches

87.1

91.8


3.4

**Average Score for the Worst 10%
(3 lowest scoring patches)**

44.4


83.4

8.3



AARDENBURG IMAGING
& ARCHIVES

85.6_{color} / 91.6_{tone}

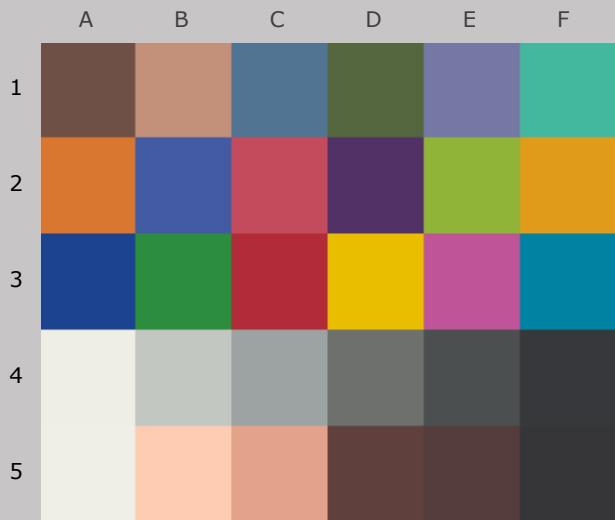


Original Print Colors
(measured before light exposure)




Colors after 90 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

90 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	95.8	1.7	37.4	38.6	11.6	12.0	11.0	9.9
B1	light Skin	81.6	6.1	64.4	67.1	18.0	16.0	19.8	14.7
C1	blue sky	91.8	3.5	47.1	49.8	-6.7	-6.7	-20.3	-22.6
D1	foliage	97.0	1.5	41.2	42.0	-13.4	-14.1	20.5	19.5
E1	blue flower	92.9	3.9	51.4	54.5	6.8	6.0	-24.8	-27.0
F1	bluish green	76.6	9.5	67.5	68.9	-37.9	-35.9	2.5	-6.7
A2	orange	96.1	3.5	60.4	62.0	36.3	33.6	54.0	52.6
B2	purplish blue	98.3	2.2	39.5	41.4	7.7	6.5	-41.7	-42.0
C2	moderate red	92.3	4.7	49.6	51.0	49.7	49.4	17.1	12.6
D2	purple	98.2	2.4	26.6	28.7	23.0	22.7	-25.2	-24.1
E2	yellow green	94.5	4.1	68.9	70.1	-26.4	-27.3	56.2	52.4
F2	orange yellow	95.1	4.6	69.8	71.9	19.8	16.1	69.4	67.7
A3	blue	96.8	2.2	29.4	30.3	8.5	6.5	-47.3	-47.3
B3	green	95.1	3.2	51.7	52.8	-41.9	-42.7	32.6	29.6
C3	red	96.5	2.6	40.7	40.5	53.5	53.8	27.3	24.7
D3	yellow	95.5	4.6	78.8	80.7	6.6	3.3	80.9	78.3
E3	magenta	99.3	2.3	51.8	53.9	49.2	48.4	-15.8	-15.8
F3	cyan	89.8	4.4	49.8	51.3	-25.1	-24.1	-25.6	-29.7
A4	white	39.0	6.3	94.2	94.8	-1.1	0.1	5.0	-1.2
B4	neutral 8	26.3	7.8	80.2	82.2	-2.5	-2.4	2.7	-4.8
C4	neutral 6.5	59.3	4.9	66.7	68.8	-2.8	-3.4	-0.3	-4.7
D4	neutral 5	83.5	2.6	46.8	48.4	-0.8	-1.0	0.9	-1.1
E4	neutral 3.5	93.0	1.3	33.2	33.9	-1.1	-1.2	-0.5	-1.7
F4	black	97.7	0.8	23.6	23.9	-0.2	-0.1	-2.0	-2.7
A5	media white	58.5	4.5	94.1	94.8	-0.6	0.2	3.0	-1.4
B5	skin highlight L*=89	60.5	10.6	85.8	88.7	14.6	11.2	19.7	10.1
C5	skin highlight L*=75	78.8	7.8	72.9	75.9	21.6	18.3	23.1	16.7
D5	skin shadow L*=25	95.1	1.3	30.9	31.3	13.7	14.6	8.2	7.4
E5	skin shadow L*=11	94.8	1.1	28.1	28.2	9.6	10.5	5.2	4.7
F5	Max Black	99.5	0.6	22.9	22.7	-0.2	-0.1	-1.0	-1.6
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		85.6	91.6						
Average Score for the Worst 10% (3 lowest scoring patches)		41.3	82.6						
ΔE				Page 14					

85.0_{color} / 91.3_{tone}

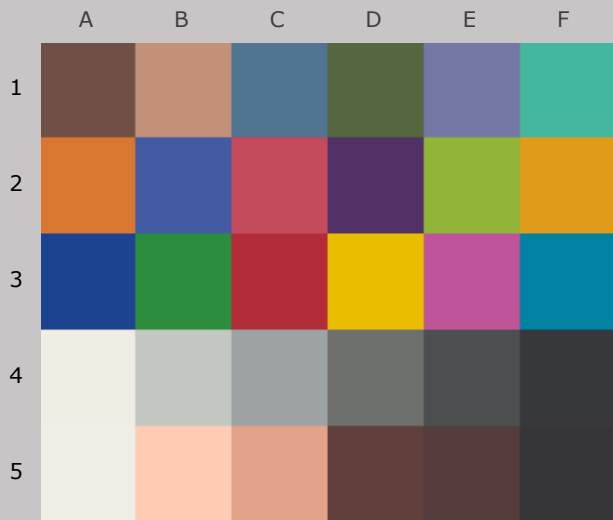


Original Print Colors
(measured before light exposure)




Colors after 100 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

100 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	94.1	2.1	37.4	39.0	11.6	11.8	11.0	9.6
B1	light Skin	80.1	6.5	64.4	67.3	18.0	16.0	19.8	14.3
C1	blue sky	91.2	3.7	47.1	49.9	-6.7	-6.8	-20.3	-22.7
D1	foliage	96.1	1.7	41.2	42.1	-13.4	-14.0	20.5	19.2
E1	blue flower	93.1	4.0	51.4	54.7	6.8	5.8	-24.8	-26.9
F1	bluish green	74.7	10.2	67.5	69.0	-37.9	-35.7	2.5	-7.4
A2	orange	95.9	3.6	60.4	62.1	36.3	33.5	54.0	52.5
B2	purplish blue	97.7	2.5	39.5	41.6	7.7	6.3	-41.7	-41.5
C2	moderate red	92.0	4.9	49.6	51.1	49.7	49.5	17.1	12.4
D2	purple	98.9	2.0	26.6	28.3	23.0	23.3	-25.2	-24.4
E2	yellow green	93.4	4.8	68.9	70.2	-26.4	-27.3	56.2	51.7
F2	orange yellow	94.8	4.9	69.8	72.1	19.8	16.0	69.4	67.5
A3	blue	96.1	2.6	29.4	30.5	8.5	6.2	-47.3	-47.0
B3	green	94.5	3.6	51.7	52.8	-41.9	-42.8	32.6	29.3
C3	red	96.2	2.8	40.7	40.6	53.5	53.8	27.3	24.5
D3	yellow	94.9	5.0	78.8	80.7	6.6	3.0	80.9	78.0
E3	magenta	98.3	2.8	51.8	54.2	49.2	47.9	-15.8	-15.3
F3	cyan	89.0	4.7	49.8	51.3	-25.1	-24.1	-25.6	-30.0
A4	white	40.9	6.1	94.2	94.9	-1.1	0.1	5.0	-1.0
B4	neutral 8	21.9	8.2	80.2	82.3	-2.5	-2.4	2.7	-5.2
C4	neutral 6.5	57.0	5.1	66.7	68.8	-2.8	-3.4	-0.3	-4.9
D4	neutral 5	82.6	2.8	46.8	48.7	-0.8	-1.0	0.9	-1.2
E4	neutral 3.5	92.5	1.5	33.2	34.0	-1.1	-1.2	-0.5	-1.7
F4	black	98.3	0.8	23.6	24.0	-0.2	-0.1	-2.0	-2.7
A5	media white	60.5	4.3	94.1	94.8	-0.6	0.1	3.0	-1.2
B5	skin highlight L*=89	58.2	11.2	85.8	88.9	14.6	11.1	19.7	9.6
C5	skin highlight L*=75	77.3	8.3	72.9	76.1	21.6	18.2	23.1	16.2
D5	skin shadow L*=25	94.4	1.5	30.9	31.4	13.7	14.7	8.2	7.3
E5	skin shadow L*=11	95.0	1.2	28.1	28.7	9.6	10.3	5.2	4.5
F5	Max Black	100.0	0.6	22.9	23.2	-0.2	-0.2	-1.0	-1.5
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		85.0	91.3	4.1					
Average Score for the Worst 10% (3 lowest scoring patches)		39.9	82.1	9.9					

83.5_{color} / 89.9_{tone}

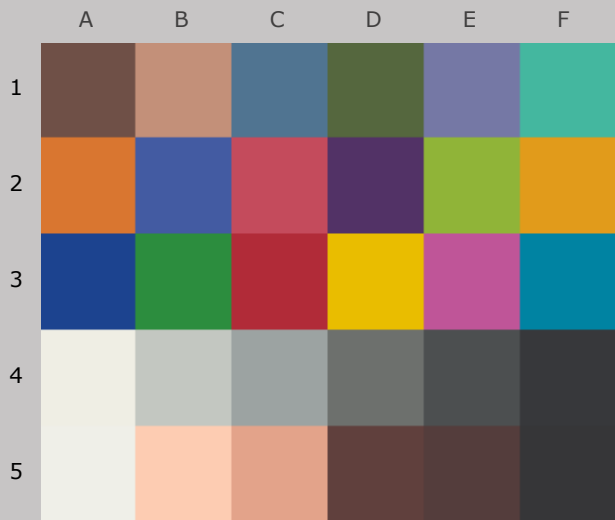


Original Print Colors
(measured before light exposure)




Colors after 120 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

120 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	93.4	2.1	37.4	38.8	11.6	12.1	11.0	9.5
B1	light Skin	77.0	7.4	64.4	67.6	18.0	15.7	19.8	13.6
C1	blue sky	91.1	3.8	47.1	50.0	-6.7	-6.9	-20.3	-22.7
D1	foliage	95.0	1.9	41.2	42.0	-13.4	-14.1	20.5	19.0
E1	blue flower	93.5	4.2	51.4	55.0	6.8	5.6	-24.8	-26.6
F1	bluish green	70.6	11.8	67.5	69.1	-37.9	-35.3	2.5	-8.9
A2	orange	95.2	4.1	60.4	62.3	36.3	33.3	54.0	52.1
B2	purplish blue	97.0	2.5	39.5	41.3	7.7	5.9	-41.7	-41.5
C2	moderate red	90.9	5.5	49.6	51.2	49.7	49.4	17.1	11.8
D2	purple	95.9	3.1	26.6	28.9	23.0	23.1	-25.2	-23.3
E2	yellow green	92.5	5.3	68.9	70.2	-26.4	-27.4	56.2	51.1
F2	orange yellow	93.9	5.5	69.8	72.3	19.8	15.5	69.4	66.9
A3	blue	95.1	3.0	29.4	30.2	8.5	5.7	-47.3	-46.7
B3	green	92.9	4.4	51.7	52.8	-41.9	-42.9	32.6	28.4
C3	red	95.6	3.2	40.7	40.6	53.5	53.9	27.3	24.2
D3	yellow	94.1	5.7	78.8	80.9	6.6	2.8	80.9	77.2
E3	magenta	97.5	3.1	51.8	54.4	49.2	47.8	-15.8	-14.7
F3	cyan	88.1	5.0	49.8	51.3	-25.1	-24.0	-25.6	-30.3
A4	white	43.5	5.9	94.2	94.6	-1.1	0.0	5.0	-0.8
B4	neutral 8	14.0	8.9	80.2	82.4	-2.5	-2.3	2.7	-5.9
C4	neutral 6.5	53.8	5.4	66.7	69.1	-2.8	-3.4	-0.3	-5.2
D4	neutral 5	81.5	2.8	46.8	48.4	-0.8	-1.0	0.9	-1.3
E4	neutral 3.5	92.5	1.6	33.2	34.2	-1.1	-1.1	-0.5	-1.7
F4	black	97.7	0.8	23.6	23.2	-0.2	-0.1	-2.0	-2.7
A5	media white	63.0	4.1	94.1	94.6	-0.6	0.0	3.0	-1.0
B5	skin highlight L*=89	51.8	12.8	85.8	89.1	14.6	10.8	19.7	8.0
C5	skin highlight L*=75	74.0	9.4	72.9	76.3	21.6	17.7	23.1	15.3
D5	skin shadow L*=25	93.0	1.7	30.9	31.3	13.7	14.8	8.2	7.1
E5	skin shadow L*=11	92.0	1.4	28.1	28.0	9.6	10.8	5.2	4.5
F5	Max Black	99.4	0.9	22.9	22.2	-0.2	-0.1	-1.0	-1.6
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		83.5	89.9	4.6					
Average Score for the Worst 10% (3 lowest scoring patches)		36.4	80.3	11.3					

80.5_{color} / 88.9_{tone}

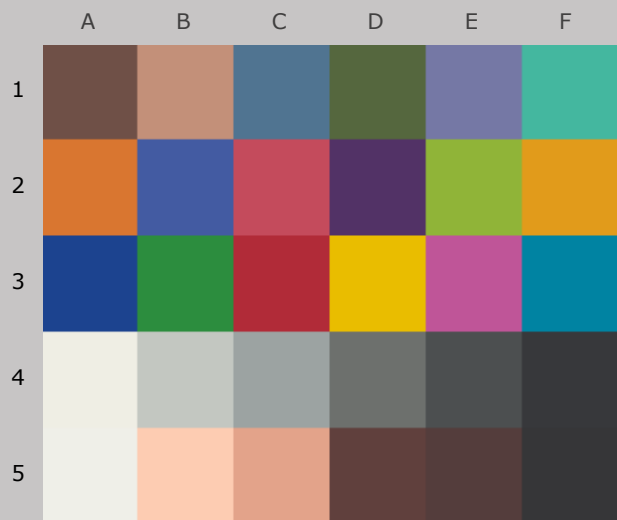

Original Print Colors
(measured before light exposure)



Colors after 140 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

140 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	89.5	3.0	37.4	39.4	11.6	11.9	11.0	8.8
B1	light Skin	72.0	8.8	64.4	68.1	18.0	15.5	19.8	12.2
C1	blue sky	88.7	4.6	47.1	50.6	-6.7	-6.8	-20.3	-23.3
D1	foliage	92.4	2.7	41.2	42.4	-13.4	-14.0	20.5	18.2
E1	blue flower	92.7	4.9	51.4	55.7	6.8	5.3	-24.8	-26.7
F1	bluish green	64.7	14.0	67.5	69.3	-37.9	-34.4	2.5	-11.0
A2	orange	94.3	4.8	60.4	62.7	36.3	32.9	54.0	51.6
B2	purplish blue	96.2	3.5	39.5	42.3	7.7	5.7	-41.7	-41.0
C2	moderate red	89.1	6.6	49.6	51.7	49.7	49.5	17.1	10.8
D2	purple	95.4	3.8	26.6	29.8	23.0	23.5	-25.2	-23.2
E2	yellow green	90.0	6.9	68.9	70.6	-26.4	-27.4	56.2	49.6
F2	orange yellow	92.6	6.6	69.8	72.7	19.8	15.0	69.4	66.0
A3	blue	93.7	4.0	29.4	31.3	8.5	5.2	-47.3	-46.2
B3	green	91.5	5.2	51.7	53.0	-41.9	-43.1	32.6	27.7
C3	red	94.1	4.1	40.7	41.0	53.5	53.9	27.3	23.3
D3	yellow	92.5	7.0	78.8	81.2	6.6	2.2	80.9	75.9
E3	magenta	97.1	3.9	51.8	55.1	49.2	47.7	-15.8	-14.5
F3	cyan	85.8	5.9	49.8	51.8	-25.1	-23.5	-25.6	-31.0
A4	white	40.5	6.2	94.2	94.8	-1.1	0.1	5.0	-1.1
B4	neutral 8	5.2	9.8	80.2	82.6	-2.5	-2.2	2.7	-6.8
C4	neutral 6.5	43.5	6.4	66.7	69.3	-2.8	-3.4	-0.3	-6.2
D4	neutral 5	76.6	3.6	46.8	49.1	-0.8	-1.0	0.9	-1.8
E4	neutral 3.5	89.6	2.2	33.2	34.8	-1.1	-1.1	-0.5	-2.0
F4	black	96.7	1.0	23.6	24.2	-0.2	-0.1	-2.0	-2.8
A5	media white	59.9	4.4	94.1	94.9	-0.6	0.1	3.0	-1.2
B5	skin highlight L*=89	42.6	15.1	85.8	89.6	14.6	10.7	19.7	5.7
C5	skin highlight L*=75	68.5	11.2	72.9	76.9	21.6	17.3	23.1	13.6
D5	skin shadow L*=25	90.5	2.2	30.9	31.7	13.7	14.9	8.2	6.7
E5	skin shadow L*=11	90.5	1.7	28.1	28.8	9.6	10.7	5.2	4.1
F5	Max Black	97.6	0.7	22.9	23.0	-0.2	-0.1	-1.0	-1.8

Summary Results

I*Color

I*tone

ΔE

Average Score for all patches

80.5

88.9


5.5

**Average Score for the Worst 10%
(3 lowest scoring patches)**

29.4


77.7

13.4



AARDENBURG IMAGING
& ARCHIVES

78.9_{color} / 88.2_{tone}

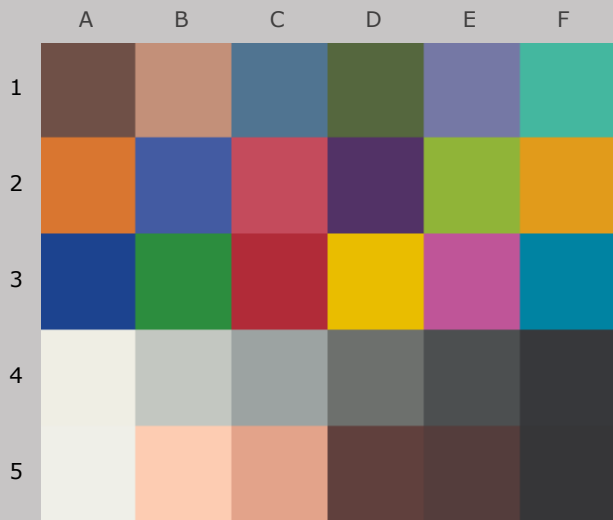


Original Print Colors
(measured before light exposure)




Colors after 160 Megalux-hours
light exposure


*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*

160 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	88.8	2.8	37.4	39.1	11.6	12.3	11.0	8.8
B1	light Skin	69.3	9.6	64.4	68.3	18.0	15.3	19.8	11.5
C1	blue sky	87.7	4.8	47.1	50.8	-6.7	-6.8	-20.3	-23.5
D1	foliage	91.5	2.9	41.2	42.5	-13.4	-14.0	20.5	18.0
E1	blue flower	92.3	5.1	51.4	55.8	6.8	5.2	-24.8	-26.7
F1	bluish green	60.6	15.6	67.5	69.4	-37.9	-34.0	2.5	-12.5
A2	orange	92.9	5.7	60.4	62.9	36.3	32.5	54.0	50.6
B2	purplish blue	95.7	3.8	39.5	42.5	7.7	5.5	-41.7	-40.8
C2	moderate red	87.9	7.2	49.6	51.9	49.7	49.4	17.1	10.3
D2	purple	92.9	4.8	26.6	30.3	23.0	23.5	-25.2	-22.3
E2	yellow green	89.1	7.4	68.9	70.6	-26.4	-27.5	56.2	49.0
F2	orange yellow	91.7	7.2	69.8	72.9	19.8	14.7	69.4	65.4
A3	blue	93.1	4.2	29.4	31.2	8.5	4.9	-47.3	-46.1
B3	green	89.8	6.1	51.7	53.2	-41.9	-42.7	32.6	26.7
C3	red	93.2	4.6	40.7	41.1	53.5	53.9	27.3	22.7
D3	yellow	91.8	7.6	78.8	81.4	6.6	2.1	80.9	75.3
E3	magenta	96.5	4.3	51.8	55.4	49.2	47.6	-15.8	-14.2
F3	cyan	84.6	6.3	49.8	51.7	-25.1	-23.4	-25.6	-31.4
A4	white	40.2	6.2	94.2	94.8	-1.1	0.1	5.0	-1.1
B4	neutral 8	3.0	10.0	80.2	82.7	-2.5	-2.2	2.7	-7.0
C4	neutral 6.5	38.2	6.9	66.7	69.4	-2.8	-3.3	-0.3	-6.7
D4	neutral 5	75.6	3.6	46.8	49.1	-0.8	-1.0	0.9	-1.9
E4	neutral 3.5	89.0	2.1	33.2	34.6	-1.1	-1.1	-0.5	-2.1
F4	black	95.9	1.1	23.6	24.2	-0.2	-0.1	-2.0	-2.9
A5	media white	60.0	4.3	94.1	94.8	-0.6	0.1	3.0	-1.2
B5	skin highlight L*=89	35.5	16.8	85.8	89.8	14.6	10.7	19.7	3.9
C5	skin highlight L*=75	65.1	12.3	72.9	77.1	21.6	17.0	23.1	12.6
D5	skin shadow L*=25	89.3	2.4	30.9	31.8	13.7	15.0	8.2	6.5
E5	skin shadow L*=11	88.9	1.8	28.1	28.8	9.6	10.8	5.2	4.0
F5	Max Black	98.0	0.7	22.9	23.1	-0.2	0.0	-1.0	-1.7
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		78.9	88.2						
Average Score for the Worst 10% (3 lowest scoring patches)		25.6	76.8						
ΔE				Page 18					

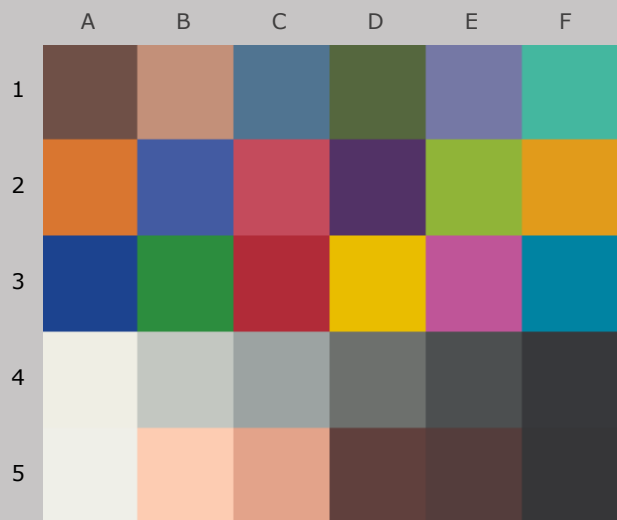


Original Print Colors
(measured before light exposure)

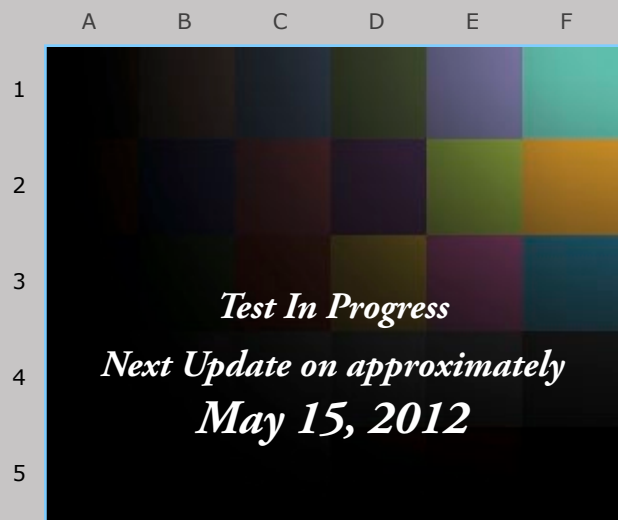

Next update is for 160 Megalux-hours
light exposure

*Epson Stylus Pro 4880, Epson Ultrachrome K3™ with Vivid Magenta Ink,
Breathing Color Chromata White™ Canvas with Clearshield® Type C Satin Overcoat*



AARDENBURG IMAGING
& ARCHIVES