

Aardenburg

144



IMAGING & ARCHIVES

Tested System:

ID#:276

Printer: Epson Stylus Pro 7890

Inks/Colorants: Epson OEM UltraChrome K3™ with Vivid Magenta

Media: Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil)

Coating(s): no additional coating

Sample #: AaI_20121116_SN001

Testing Status: 160 Megalux hours total light exposure

Testing Is ongoing, next update on approximately DEC 20, 2017

Conservation Display Rating (CDR)

Lower limit: 59 Megalux hours (for weakest 10% of the color patches)

Upper limit: 91 Megalux hours (for average of all the color patches)

Note: a CDR with narrow range (typically less than 2:1) indicates relatively even overall fading of the image. A wide range indicates faster fading in certain local colors/tones prior to general fading of most colors/tones in the entire image. Compare ratings for different systems directly and/or use the table on page 2 to estimate time (years) on display.

* Please read document AaI_2009_0118_TA-01.pdf, “An Overview of the AaI&A Conservation Display Ratings”, located on the Documents page of the AaI&A website for further explanation of the Conservation display ratings.

This report has been prepared for the exclusive use of members of Aardenburg Imaging & Archives. Members may share this information with other members, friends, colleagues, and individual clients. It may also be distributed to groups for educational purposes (classes, lectures, educational seminars. etc). However, all contents including but not limited to Conservation Display Ratings may not be posted to web sites and may not be reproduced or distributed for corporate research, marketing, or other promotional purposes without written permission from Aardenburg Imaging & Archives.

copyright ©2017

<http://www.aardenburg-imaging.com>


Aardenburg Imaging and Archives
Rev:8/17/17



About this Report

This report contains light fastness information about a sample test print produced by a specific digital printing system. “System” refers to all hardware, software, and materials used to make the finished print. The hardware, software, material components, and printmaker’s skills contribute to the final image quality and image permanence. The tested sample is made with current or recently discontinued stocks of commercially available products unless otherwise stated. Each sample has been prepared by Aardenburg Imaging & Archives or one of its members in accordance with customary print making practices unless otherwise noted. The sample may also contain additional finishing materials such as overcoats and laminates which are also noted when used. Finally, the sample has been tested under standardized conditions that are defined on the Sample Description page (see page 4). AaI&A makes every effort to ensure but cannot guarantee that the samples are properly identified and documented and that test results are accurate. For this reason, AaI&A also strives to test independently produced sample replicates in order to increase sampling confidence and to provide information on process variability. Please compare the results in this report to replicate test samples when the data become available.

Understanding this Report

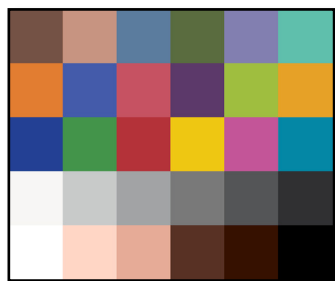

The magnitude and visual appearance of fading depends not only on the chosen printing system but the chosen image as well. In other words, different images are comprised of different colors, and the fading relationships between those colors dictate how the image will look as it fades. The sample print in this test report was made by reproducing the digital image shown on the left. It contains 30 standard colors. 24 of the colors are colorimetrically matched to the Macbeth ColorChecker™ chart viewed under D50 illumination. The remaining six colors supplement the ColorChecker™ array with four additional skin tone colors, one patch for paper white, and another for maximum black. The additional colors also round out the distribution of CIELAB L* (lightness) values in the test target.

Information about the fading characteristics of the product is provided in three ways:

1) You can visually assess the fading. The target images reproduced in this report are digitally reconstructed from the spectrally measured color data rather than scanning or otherwise reproducing the physical print by conventional techniques. This method ensures a colorimetrically accurate representation of the print appearance as the print fades. A calibrated monitor is recommended to experience the best possible reproduction of the test sample appearance. The side-by-side “before and after” presentation of the target images simulates looking at a perfect copy of the unexposed original print along side the same print after light exposure. You can also use Adobe Reader’s full screen mode to cycle through the pages and “animate” the fading.

2) I* Color and tonal accuracy scores are reported. This report includes I* metric scores that compare the color and tonal relationships of the light exposed samples to the color and tonal relationships existing in the original print prior to light exposure. Perfect I* scores of 100% can be approached when no significant fading occurs. Average scores above 90% generally indicate excellent retention of original quality, 80% good, 70% fair, etc., but your conclusions may vary depending on your image quality requirements. I* color rates the retained color accuracy (hue and chroma) while I* tone rates the retained tonal accuracy (lightness and contrast). The score is on a percentile scale where 100% is a perfect match between the comparison image (e.g., “after” light exposure) and the reference image (e.g., “before” any light exposure). 0% I* color means no color accuracy is left. 0% I* tone means essentially no tonality remains and all image information content is lost. Negative I* values have significance as well and contribute to the average I* score when they occur. Negative I* color values mean false color has occurred, for example, when a skin tone turns green or a neutral gray becomes distinctly colorful. Negative I* tone scores mean visual contrast between colors has become inverted (i.e., like the tonal relationships in a photographic film negative). Serious image quality problems must arise before false colors and/or tones appear. For more information on the I* metric, please refer to the AaI&A web site.

3) Color changes are also reported using the classic color difference model, ΔE . Note that ΔE values lose perceptual scaling significance when they become large (e.g., > 15). Also, the ΔE equation does not unambiguously measure changes in image contrast. This limitation is generally not a problem for paints and textiles, but can be a serious oversight when evaluating photographic images. Properly tracking changes in image contrast was a major reason behind the development of the I* metric.

Table to Convert Megalux-hours of Light Exposure to estimated “Years on Display” Light Fastness Ratings.												
Indoor Light Levels for Print Display		Multiply Mlux-hrs by	Megalux-hours in test									
Light Exposure	Description		10	20	30	40	50	60	70	80	90	100
≤ 10 Lux 24 hours per day	Interior rooms, storage areas, or hallways without windows, illuminated sparingly by artificial lighting	11.42	114	228	342	457	571	685	799	913	1027	1142
50 Lux 12 hours per day	“Museum Standard” display condition	4.57	46	91	137	183	228	274	325	365	411	457
120 Lux 12 hours per day “Kodak Display Years” (1)	Average home illumination level for photos is ~ 60 lux. 90% of all displayed photos do not exceed 120 lux (1).	1.90	19	38	57	76	95	114	133	152	171	190
228 Lux 12 hours per day	Relatively bright home or office. Note the simple 1:1 relationship between “years on display” and Mlux-hr values at this condition.	1.00	10	20	30	40	50	60	70	80	90	100
450 Lux 12 hours per day “WIR Display Years” (2) Also equals 500 lux for 11.8 hours per day	A bright home or commercial office building illumination level is 200-500 lux. Also, good illumination for color critical viewing and color matching tasks begins at about 500 lux.	0.51	5	10	15	20	25	30	35	41	46	51
2000 Lux 12 hours per day	Commercial Gallery. Also, critical color evaluation standards call for 2000 lux and a D50 illumination source.	0.114	1.1	2.3	3.4	4.6	5.7	6.8	8.0	9.1	10.3	11.4
5000 Lux 12 hours per day	E.g., Sunlight through a window striking print at an angle.	0.046	0.5	0.9	1.4	1.8	2.3	2.7	3.2	3.7	4.1	4.6
10,000 Lux 12 hours per day	South-facing window in U.S.A. , e.g., storefront display with photos directly facing window.	0.023	0.2	0.5	0.7	0.9	1.1	1.4	1.6	1.8	2.1	2.3

Light levels commonly encountered in the real world fluctuate widely throughout indoor print display environments and produce large variations in how long it takes for artwork to acquire light-induced damage. Use this table as a guide to estimate how many “years on display” (denoted in red text) it takes to accumulate an equivalent light exposure dosage. Review the test results to decide which Megalux-hour dose has caused fading to your level of concern (e.g., just noticeable, easily noticeable, objectionable, etc.). Then choose the “Light Exposure” description that best represents how your print is likely to be displayed. You may want to obtain a lux meter and make some measurements in your own display environment!

Note that as the years of display time increase, light-induced fading can be eclipsed by other serious aging mechanisms such as fading and/or staining caused by heat, humidity, and air pollutants. Mould damage can also occur at high humidity. Even when colorants remain water fast, direct contact with liquids may result in physical deformation and staining of the substrate. Also, temperature and especially strong seasonal humidity fluctuations can cause physical cracks and/or flaking, etc., over time. Handling damage such as scratching, abrasion, tears and creases, and catastrophic damage by smoke, fire, flood, etc., also destroy print quality over time. Thus, as illumination levels are reduced other forms of print degradation take on greater probability of occurrence.

(1) Eastman Kodak cited this exposure condition with a 90% confidence limit as a rationale for estimating print fading times of traditional color photo materials in typical home display environments. However, for light fading claims regarding its line of pigment-based inkjet printers, Kodak adopted the higher level of 450lux/12 hours per day which is also used by Wilhelm Imaging Research, Inc. (See below).

(2) Wilhelm Imaging Research (WIR) standardized its light fastness ratings on 450 lux for 12 hours per day in order to estimate the years on display necessary to reach “easily noticeable” fading. This average daily light exposure dosage, at an assumed 75°F/60%RH temperature and humidity level, has become a de facto industry standard for most industry-sponsored predictive “years of life” light fading estimates in the absence of a published International Standards Organization (ISO) test standard. The table above readily shows how much error occurs in such “print lifetime” predictions as actual real world light levels for prints on display routinely deviate above and below the assumed 450 lux intensity value.

Sample Description

Sample # AaI_20121116_SN001 **Batch #:** M1
Printer: Epson Stylus Pro 7890
Ink: Epson OEM UltraChrome K3™ with Vivid Magenta
Media: Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil)
Coating(s): no additional coating

Test Print Prepared by: AaI&A member
Printed: October 2, 2012
Initial Print colors measured February 17, 2013
Test Started: February 20, 2013

Test Image: AaI_StandardColorSet(v2)forSRGB.tif
RIP?Driver settings: Qimage, Print quality = Level 4 Superfine-720x1440dpi, High speed “on”, color = “off”(no color adjustment) Qimage manages color

Media Setting Epson Premium Luster (260)

Profile: RR UPSatin Ep7890.icc **Rendering** Perceptual
Profile type: generic, provided by vendor

Paper White Color (UV-included versus UV-excluded)

Optical Brighteners Present? <i>yes (low)</i>	L*		a*		b*	
Media Whitepoint Color	UV inc	UV exc	UV inc	UV exc	UV inc	UV exc
	94.4	94.4	0.3	-0.3	-4.1	-1.9
	UV-inc/UV-exc ΔL^*, Δa^*, Δb^* respectively					
	0.0		0.6		2.2	
	<i>Calculated differences, especially for Δb^*, indicate the role and magnitude of fluorescence on original paper color</i>					
Maximum Printed Black	L*	a*	b*	Optical Density (Dmax)		
	7.0	0.4	0.5	2.11		

Light source: Phillips Colortone F40T12/C50 – 5000°K full spectrum fluorescent. Color rendering Index (CRI) =92), soda lime glass filtered
Light Exposure Cycle: 8 hours on, 4 hours off, twice per 24 hours
CIELAB measurements: D50 2° observer, Xrite Gretag/Macbeth Spectrolino/Spectroscan

Average Illuminance during “on” cycle: 10797 Lux
Average Temperature: 24.5°C over full test duration, 25.7°C during light exposure.
Average Relative humidity: 55.8%RH over full test duration, 56.0%RH during light exposure.

Notes/Comments:**Replicates/Compare to:**

Compare to these other Red River Ultra Pro Satin 2.0 paper samples tested as part of a direct side-by-side light fade test for this paper:

ID# 273 – sample # AaI_20121030_SN001 – printed on an Epson 1400 printer using the Epson OEM Claria 79 dyebase ink set.


ID# 275 – sample # AaI_20121030_SN003 – printed on the same Epson 1400 printer and paper batch used to print sample # AaI_20121030_SN001 but using the MIS Associates D2 “Claria compatible” dyebase ink set.

ID# 277 – sample # AaI_20121130_SN002 – printed on an Epson R3000 using ConeColorPro® pigmented ink set (for the Epson R3000 printer).



MHMG 2015-06-07: The significant jump in b^* value on the whitepoint stability graphs at 70 Mluxhrs and partial recovery at 80 Mluxhrs were not measurement errors. The 70 Mluxhr measurements was delayed approximately six weeks after removing the sample from the light fade unit. The temporary "dark storage" period caused a phenomenon I call "light-induced low intensity staining (LILIS)". LILIS is additional media yellowing over and above the yellowing caused by loss of fluorescence as the optical brighteners (OBAs) fade. However, it may well be discoloration directly associated with the faded OBA degradation by-products. The widely held assertion that papers simply return to their "natural" color as the OBAs fade is now called into question with the LILIS effect. This additional yellow stain formation can also be partially or fully reversed with more light exposure of sufficient intensity as evidenced by the 80 Mluxhr exposure results which were measured immediately after removal of the sample from the light fade test unit. Unfortunately, the stain will return again with further storage in low intensity or dark storage environments.

Graphs:


Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

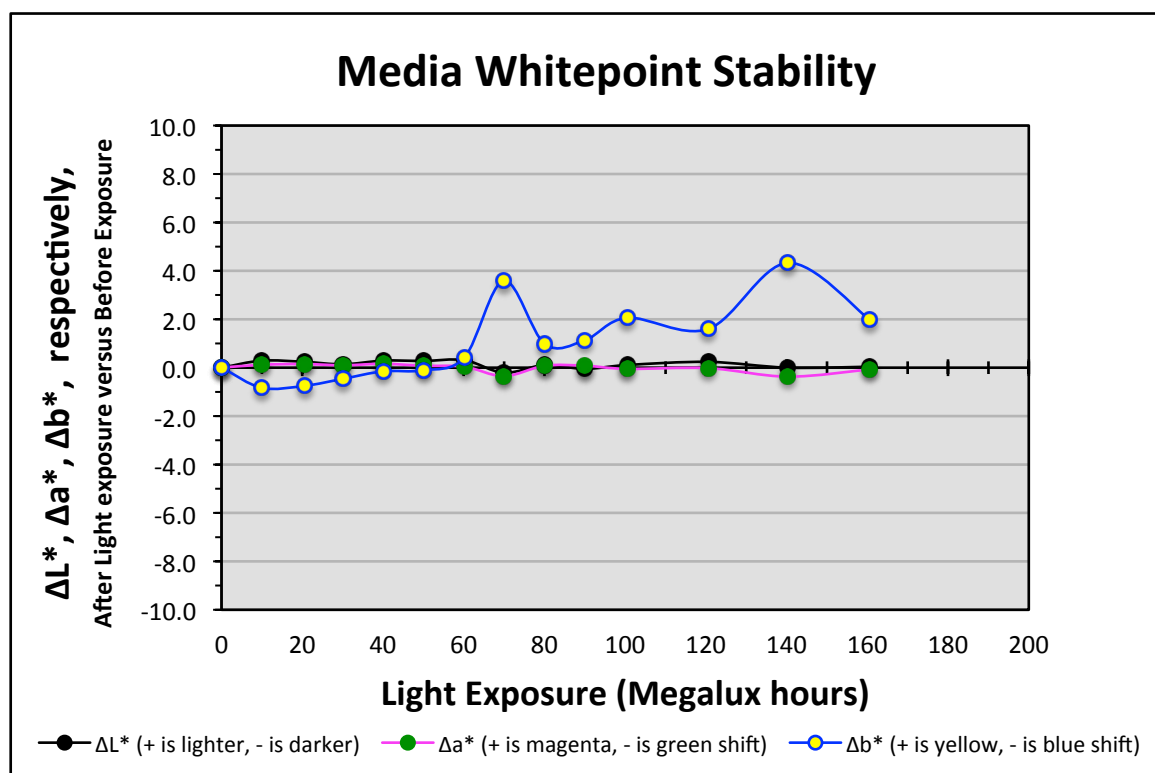

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

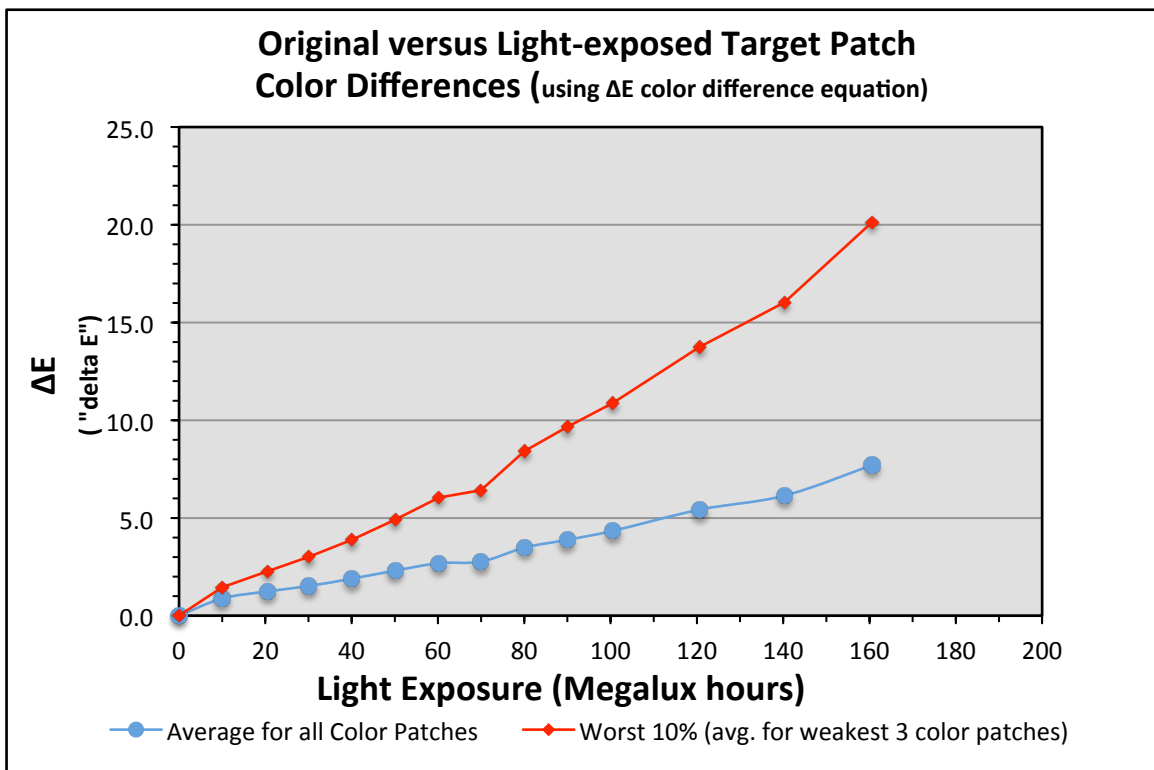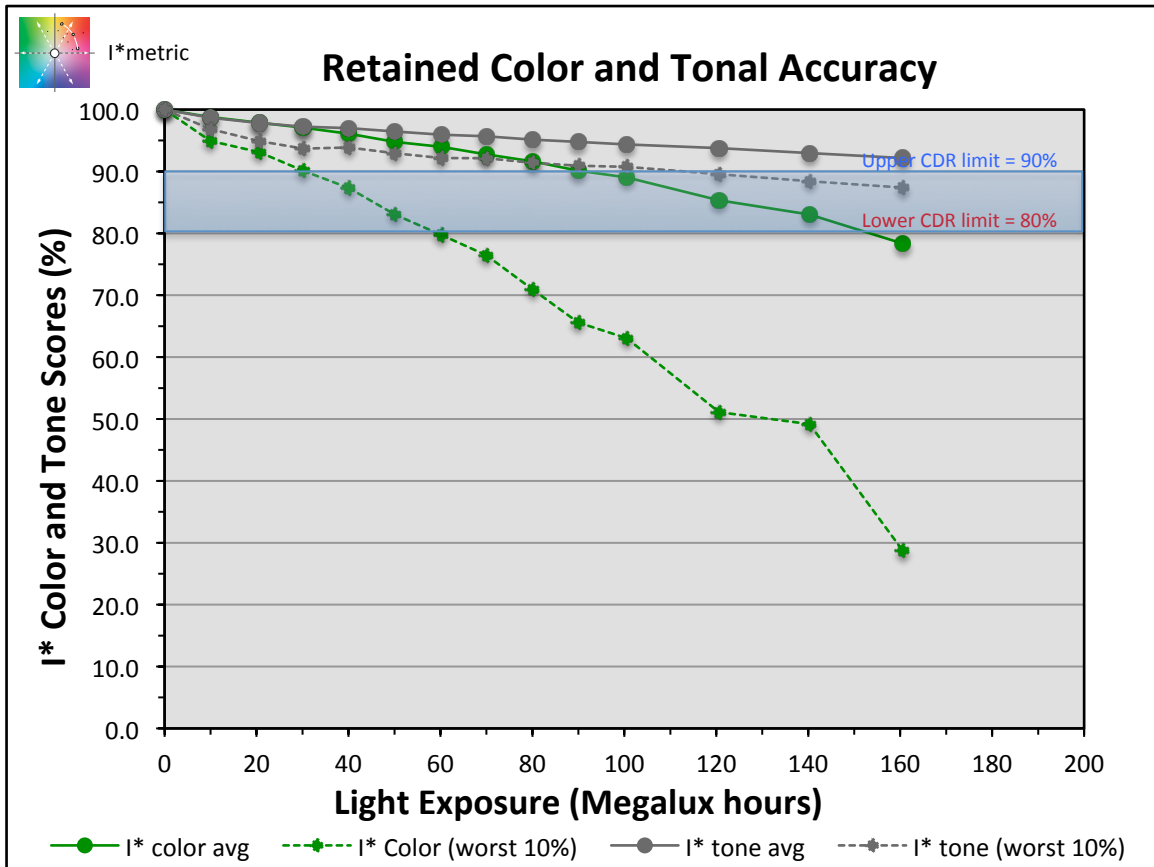

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

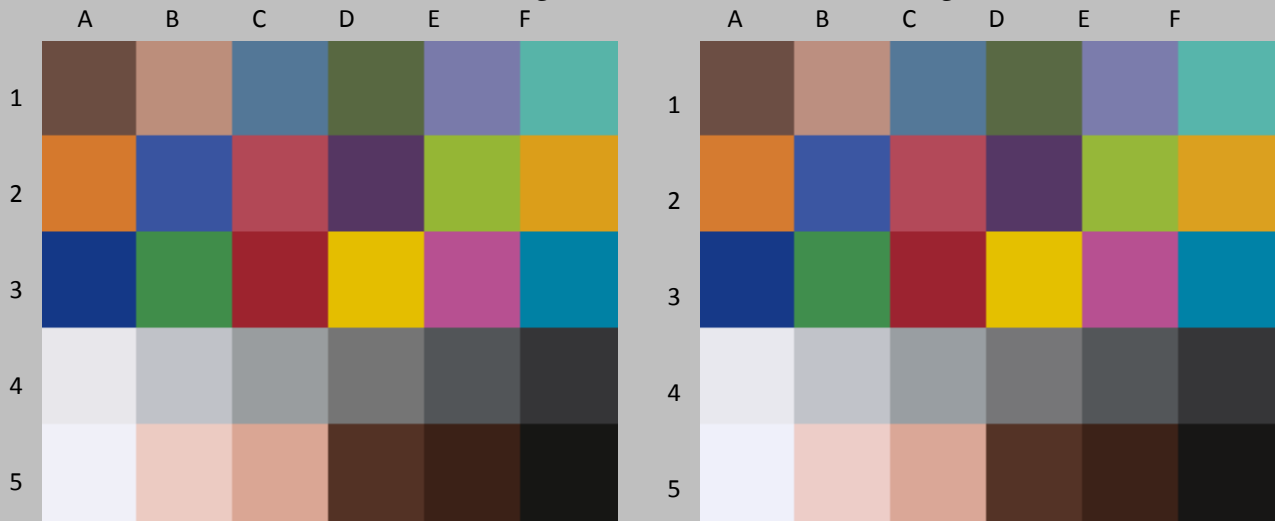


Original Print Colors before light exposure

Colors After light exposure


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	100.0	0.7	35.6	36.1	11.7	11.5	11.9	11.5
B1	Light Skin	97.5	1.2	63.0	63.5	16.2	15.8	16.5	15.5
C1	Blue sky	100.0	0.7	48.3	48.8	-5.8	-5.8	-22.0	-22.5
D1	Foliage	100.0	0.7	41.9	42.4	-12.0	-12.2	19.6	19.1
E1	blue flower	100.0	0.7	52.7	53.2	8.3	8.3	-26.0	-26.4
F1	bluish green	98.0	1.2	67.6	68.0	-31.3	-31.0	-3.0	-4.1
A1	orange	98.9	1.3	60.3	60.8	33.2	32.5	54.5	53.6
B2	purplish blue	100.0	0.6	37.0	37.5	9.5	9.3	-45.1	-45.3
C2	moderate red	98.7	1.2	45.8	46.1	44.9	44.6	15.0	13.9
D2	purple	99.7	0.8	27.8	28.3	21.0	21.0	-21.3	-21.9
E2	yellow green	99.2	1.1	69.9	70.3	-25.0	-25.3	58.1	57.2
F2	orange yellow	99.0	1.3	69.8	70.3	15.9	15.1	68.6	67.6
A3	blue	99.8	0.7	25.0	25.4	13.4	13.3	-48.7	-49.3
B3	green	99.2	1.0	52.4	52.8	-36.0	-36.2	28.1	27.2
C3	red	99.8	0.7	35.7	35.9	49.8	49.8	26.0	25.3
D3	yellow	99.6	1.0	78.3	78.8	2.6	1.7	90.7	90.8
E3	magenta	99.2	1.0	49.2	49.6	47.9	47.7	-14.6	-15.4
F3	cyan	99.6	0.8	49.2	49.7	-22.5	-22.3	-28.2	-28.8
A4	white	95.1	1.0	91.7	92.0	0.7	0.8	-2.2	-3.2
B4	neutral 8	99.4	0.7	78.3	78.7	-0.2	-0.2	-2.6	-3.2
C4	neutral 6.5	97.2	0.9	64.2	64.6	-0.9	-0.8	-2.2	-3.0
D4	neutral 5	97.7	0.9	49.3	49.8	-0.2	-0.3	-0.3	-1.0
E4	neutral 3.5	100.0	0.7	36.0	36.5	-0.5	-0.6	-1.5	-2.0
F4	black	100.0	0.6	22.2	22.7	-0.3	-0.4	-0.6	-1.0
A5	paper white	96.4	0.9	94.8	95.1	0.6	0.7	-3.7	-4.6
B5	Skin highlight L*=88	93.2	1.5	84.5	84.9	10.8	10.6	8.7	7.3
C5	Skin highlight L* =75	96.4	1.5	72.5	73.1	18.3	17.9	17.3	16.0
D5	Skin shadow L*=28	100.0	0.4	24.6	25.0	13.9	13.8	15.3	15.3
E5	Skin shadow L*=13	100.0	0.5	16.0	16.4	11.8	11.8	11.8	12.1
F5	Maximum Black	100.0	0.3	7.0	7.3	0.4	0.3	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	10 Megalux hours				
Average Score for all patches		98.8	98.7	0.9					
Worst 10% (3 lowest scoring patches)		94.9	96.9	1.4					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

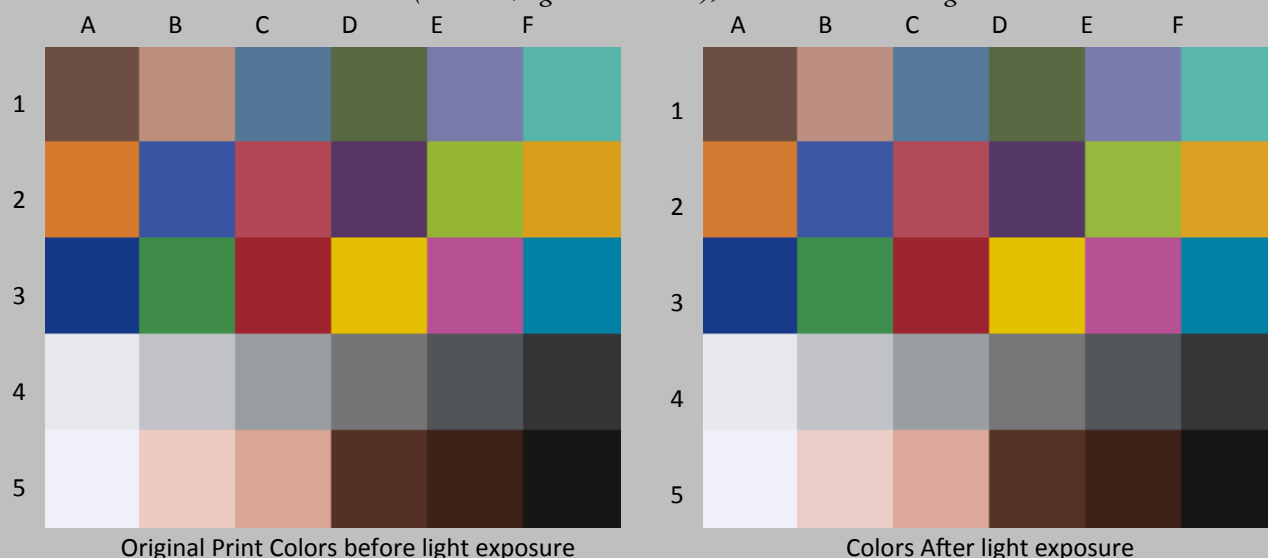


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	97.3	1.2	35.6	36.3	11.7	11.5	11.9	11.0
B1	Light Skin	94.9	1.8	63.0	63.7	16.2	15.7	16.5	14.9
C1	Blue sky	99.8	0.9	48.3	49.0	-5.8	-5.7	-22.0	-22.5
D1	Foliage	98.4	1.1	41.9	42.5	-12.0	-12.2	19.6	18.7
E1	blue flower	100.0	0.8	52.7	53.5	8.3	8.3	-26.0	-26.3
F1	bluish green	96.9	1.6	67.6	68.1	-31.3	-30.9	-3.0	-4.4
A1	orange	97.4	2.2	60.3	60.9	33.2	32.1	54.5	52.6
B2	purplish blue	100.0	0.8	37.0	37.7	9.5	9.1	-45.1	-45.3
C2	moderate red	97.1	1.9	45.8	46.1	44.9	44.5	15.0	13.2
D2	purple	98.7	1.1	27.8	28.4	21.0	20.9	-21.3	-22.2
E2	yellow green	98.0	1.9	69.9	70.5	-25.0	-25.5	58.1	56.4
F2	orange yellow	97.6	2.3	69.8	70.4	15.9	14.7	68.6	66.7
A3	blue	99.4	1.0	25.0	25.6	13.4	13.2	-48.7	-49.5
B3	green	97.7	1.6	52.4	53.0	-36.0	-36.2	28.1	26.5
C3	red	99.1	1.0	35.7	35.9	49.8	49.7	26.0	24.9
D3	yellow	99.1	1.5	78.3	79.1	2.6	1.2	90.7	90.6
E3	magenta	98.5	1.3	49.2	49.6	47.9	47.5	-14.6	-15.7
F3	cyan	99.4	0.9	49.2	49.8	-22.5	-22.2	-28.2	-28.8
A4	white	94.9	1.0	91.7	92.0	0.7	0.7	-2.2	-3.2
B4	neutral 8	100.0	0.8	78.3	78.8	-0.2	-0.2	-2.6	-3.1
C4	neutral 6.5	96.6	1.0	64.2	64.7	-0.9	-0.8	-2.2	-3.1
D4	neutral 5	96.2	1.1	49.3	49.9	-0.2	-0.3	-0.3	-1.2
E4	neutral 3.5	98.9	1.0	36.0	36.8	-0.5	-0.6	-1.5	-2.1
F4	black	99.1	0.9	22.2	22.9	-0.3	-0.3	-0.6	-1.2
A5	paper white	97.2	0.8	94.8	95.0	0.6	0.7	-3.7	-4.5
B5	Skin highlight L*=88	91.1	1.8	84.5	85.1	10.8	10.4	8.7	7.0
C5	Skin highlight L* =75	93.4	2.3	72.5	73.4	18.3	17.7	17.3	15.2
D5	Skin shadow L*=28	100.0	0.6	24.6	25.1	13.9	13.7	15.3	15.1
E5	Skin shadow L*=13	100.0	0.6	16.0	16.5	11.8	11.7	11.8	12.0
F5	Maximum Black	100.0	0.5	7.0	7.4	0.4	0.4	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	20 Megalux hours				
Average Score for all patches		97.9	97.8	1.2					
Worst 10% (3 lowest scoring patches)		93.1	94.9	2.3					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

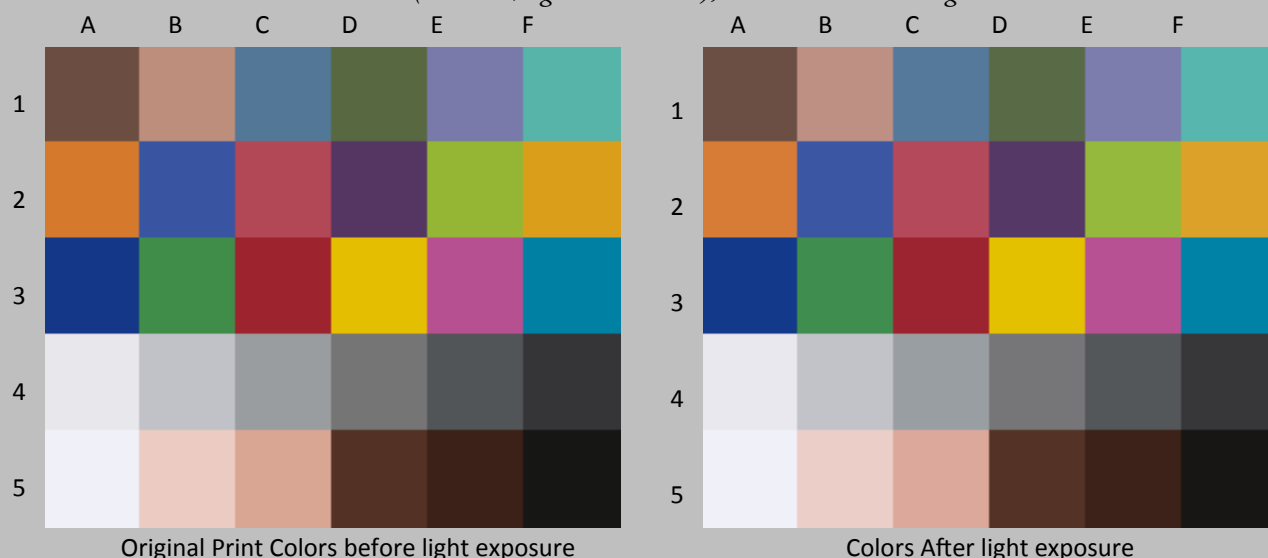


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	95.4	1.6	35.6	36.5	11.7	11.4	11.9	10.7
B1	Light Skin	92.5	2.4	63.0	63.9	16.2	15.8	16.5	14.3
C1	Blue sky	99.4	1.1	48.3	49.1	-5.8	-5.6	-22.0	-22.6
D1	Foliage	97.0	1.4	41.9	42.7	-12.0	-12.2	19.6	18.4
E1	blue flower	100.0	1.0	52.7	53.7	8.3	8.5	-26.0	-26.2
F1	bluish green	95.8	1.9	67.6	68.2	-31.3	-30.8	-3.0	-4.7
A1	orange	96.2	3.0	60.3	61.0	33.2	32.0	54.5	51.9
B2	purplish blue	100.0	0.9	37.0	37.8	9.5	9.1	-45.1	-45.3
C2	moderate red	95.9	2.5	45.8	46.2	44.9	44.5	15.0	12.6
D2	purple	97.6	1.4	27.8	28.5	21.0	21.0	-21.3	-22.5
E2	yellow green	96.9	2.5	69.9	70.6	-25.0	-25.6	58.1	55.8
F2	orange yellow	96.7	2.9	69.8	70.5	15.9	14.5	68.6	66.1
A3	blue	98.8	1.3	25.0	25.7	13.4	13.3	-48.7	-49.8
B3	green	96.7	2.1	52.4	53.0	-36.0	-36.2	28.1	26.1
C3	red	98.6	1.3	35.7	35.8	49.8	49.8	26.0	24.7
D3	yellow	98.6	2.0	78.3	79.3	2.6	0.8	90.7	90.4
E3	magenta	98.0	1.6	49.2	49.7	47.9	47.5	-14.6	-16.0
F3	cyan	99.3	1.0	49.2	49.9	-22.5	-22.1	-28.2	-28.8
A4	white	95.5	1.0	91.7	92.0	0.7	0.8	-2.2	-3.1
B4	neutral 8	100.0	0.7	78.3	78.9	-0.2	-0.3	-2.6	-3.0
C4	neutral 6.5	96.3	1.0	64.2	64.7	-0.9	-0.7	-2.2	-3.1
D4	neutral 5	94.9	1.2	49.3	50.0	-0.2	-0.2	-0.3	-1.3
E4	neutral 3.5	97.1	1.1	36.0	36.8	-0.5	-0.6	-1.5	-2.3
F4	black	97.6	1.1	22.2	23.0	-0.3	-0.3	-0.6	-1.4
A5	paper white	100.0	0.5	94.8	94.9	0.6	0.7	-3.7	-4.2
B5	Skin highlight L*=88	87.8	2.3	84.5	85.1	10.8	10.5	8.7	6.6
C5	Skin highlight L* =75	90.1	3.2	72.5	73.5	18.3	17.7	17.3	14.4
D5	Skin shadow L*=28	100.0	0.7	24.6	25.2	13.9	13.8	15.3	15.0
E5	Skin shadow L*=13	100.0	0.6	16.0	16.5	11.8	11.8	11.8	12.1
F5	Maximum Black	100.0	0.4	7.0	7.4	0.4	0.4	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	30 Megalux hours				
Average Score for all patches		97.1	97.2	1.5					
Worst 10% (3 lowest scoring patches)		90.1	93.7	3.0					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

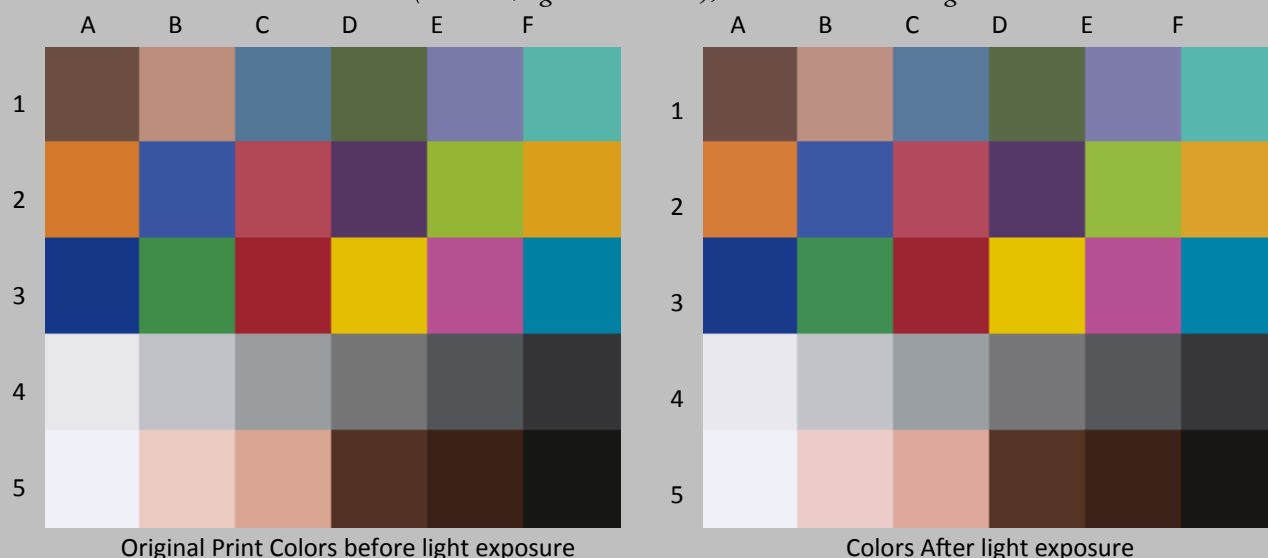


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	93.8	1.9	35.6	36.6	11.7	11.5	11.9	10.4
B1	Light Skin	90.3	3.0	63.0	64.1	16.2	15.9	16.5	13.8
C1	Blue sky	98.8	1.2	48.3	49.2	-5.8	-5.4	-22.0	-22.7
D1	Foliage	96.1	1.6	41.9	42.8	-12.0	-12.2	19.6	18.2
E1	blue flower	100.0	1.2	52.7	53.9	8.3	8.5	-26.0	-26.3
F1	bluish green	93.9	2.5	67.6	68.4	-31.3	-30.6	-3.0	-5.3
A1	orange	94.9	3.8	60.3	61.2	33.2	32.0	54.5	51.0
B2	purplish blue	100.0	1.1	37.0	38.0	9.5	9.2	-45.1	-45.4
C2	moderate red	94.5	3.1	45.8	46.4	44.9	44.6	15.0	11.9
D2	purple	96.5	1.8	27.8	28.7	21.0	21.2	-21.3	-22.8
E2	yellow green	95.4	3.5	69.9	70.8	-25.0	-25.7	58.1	54.8
F2	orange yellow	95.2	4.0	69.8	70.7	15.9	14.2	68.6	65.0
A3	blue	98.0	1.7	25.0	25.8	13.4	13.5	-48.7	-50.2
B3	green	95.3	2.7	52.4	53.2	-36.0	-36.3	28.1	25.4
C3	red	97.4	2.0	35.7	36.0	49.8	49.9	26.0	24.0
D3	yellow	98.3	2.4	78.3	79.5	2.6	0.6	90.7	90.1
E3	magenta	97.4	1.9	49.2	49.9	47.9	47.6	-14.6	-16.3
F3	cyan	98.8	1.2	49.2	50.0	-22.5	-22.0	-28.2	-29.0
A4	white	96.2	1.0	91.7	92.1	0.7	0.8	-2.2	-3.1
B4	neutral 8	100.0	0.9	78.3	79.0	-0.2	-0.2	-2.6	-3.0
C4	neutral 6.5	95.9	1.2	64.2	65.0	-0.9	-0.5	-2.2	-3.1
D4	neutral 5	93.3	1.5	49.3	50.2	-0.2	-0.1	-0.3	-1.5
E4	neutral 3.5	95.2	1.4	36.0	36.9	-0.5	-0.5	-1.5	-2.5
F4	black	96.4	1.2	22.2	23.0	-0.3	-0.3	-0.6	-1.5
A5	paper white	100.0	0.4	94.8	95.1	0.6	0.7	-3.7	-3.9
B5	Skin highlight L*=88	84.0	2.8	84.5	85.3	10.8	10.5	8.7	6.0
C5	Skin highlight L* =75	87.7	3.8	72.5	73.7	18.3	17.8	17.3	13.8
D5	Skin shadow L*=28	100.0	0.9	24.6	25.4	13.9	13.8	15.3	14.9
E5	Skin shadow L*=13	99.8	0.8	16.0	16.5	11.8	12.0	11.8	12.3
F5	Maximum Black	100.0	0.4	7.0	7.3	0.4	0.5	0.5	0.7
Summary Results		I* Color	I* tone	ΔE	40 Megalux hours				
Average Score for all patches		96.1	97.0	1.9					
Worst 10% (3 lowest scoring patches)		87.3	93.9	3.9					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

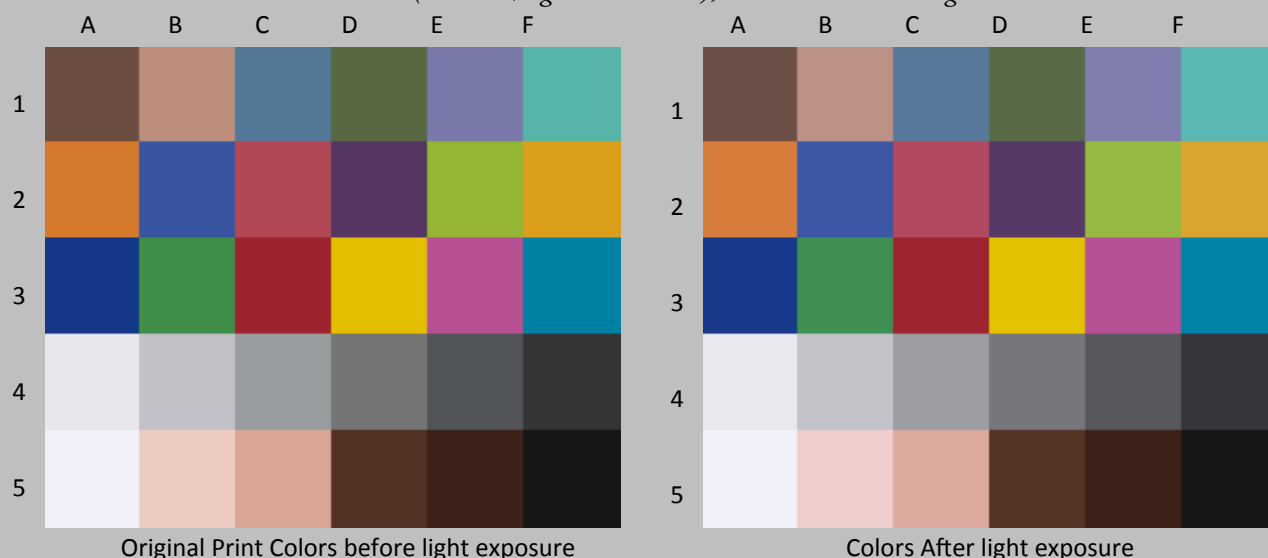


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	91.1	2.3	35.6	36.8	11.7	11.4	11.9	10.0
B1	Light Skin	86.3	3.9	63.0	64.3	16.2	15.9	16.5	12.9
C1	Blue sky	98.4	1.4	48.3	49.4	-5.8	-5.3	-22.0	-22.7
D1	Foliage	94.7	2.0	41.9	42.9	-12.0	-12.2	19.6	17.9
E1	blue flower	100.0	1.4	52.7	54.1	8.3	8.6	-26.0	-26.3
F1	bluish green	92.8	2.9	67.6	68.5	-31.3	-30.4	-3.0	-5.6
A1	orange	93.3	4.9	60.3	61.4	33.2	31.8	54.5	50.0
B2	purplish blue	100.0	1.2	37.0	38.1	9.5	9.2	-45.1	-45.5
C2	moderate red	93.1	3.8	45.8	46.4	44.9	44.5	15.0	11.3
D2	purple	95.3	2.2	27.8	28.9	21.0	21.2	-21.3	-23.2
E2	yellow green	94.5	4.2	69.9	71.0	-25.0	-25.8	58.1	54.2
F2	orange yellow	94.0	4.9	69.8	70.9	15.9	14.0	68.6	64.3
A3	blue	97.4	2.0	25.0	25.9	13.4	13.8	-48.7	-50.5
B3	green	93.9	3.4	52.4	53.4	-36.0	-36.2	28.1	24.8
C3	red	97.2	2.1	35.7	36.1	49.8	50.0	26.0	23.9
D3	yellow	97.6	3.0	78.3	79.7	2.6	0.1	90.7	89.7
E3	magenta	96.4	2.4	49.2	50.0	47.9	47.6	-14.6	-16.8
F3	cyan	99.1	1.2	49.2	50.2	-22.5	-22.0	-28.2	-28.8
A4	white	94.5	1.1	91.7	92.1	0.7	0.8	-2.2	-3.2
B4	neutral 8	100.0	0.9	78.3	79.1	-0.2	-0.3	-2.6	-3.0
C4	neutral 6.5	94.5	1.4	64.2	65.1	-0.9	-0.4	-2.2	-3.2
D4	neutral 5	91.3	1.7	49.3	50.3	-0.2	-0.1	-0.3	-1.7
E4	neutral 3.5	92.6	1.7	36.0	37.1	-0.5	-0.5	-1.5	-2.7
F4	black	94.4	1.4	22.2	23.2	-0.3	-0.2	-0.6	-1.7
A5	paper white	100.0	0.3	94.8	95.1	0.6	0.6	-3.7	-3.9
B5	Skin highlight L*=88	79.9	3.4	84.5	85.4	10.8	10.5	8.7	5.5
C5	Skin highlight L* =75	82.9	5.0	72.5	74.0	18.3	17.7	17.3	12.6
D5	Skin shadow L*=28	98.4	1.3	24.6	25.6	13.9	13.6	15.3	14.5
E5	Skin shadow L*=13	100.0	0.7	16.0	16.7	11.8	11.9	11.8	12.1
F5	Maximum Black	100.0	0.8	7.0	7.8	0.4	0.4	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	50 Megalux hours				
Average Score for all patches		94.8	96.5	2.3					
Worst 10% (3 lowest scoring patches)		83.0	93.0	4.9					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

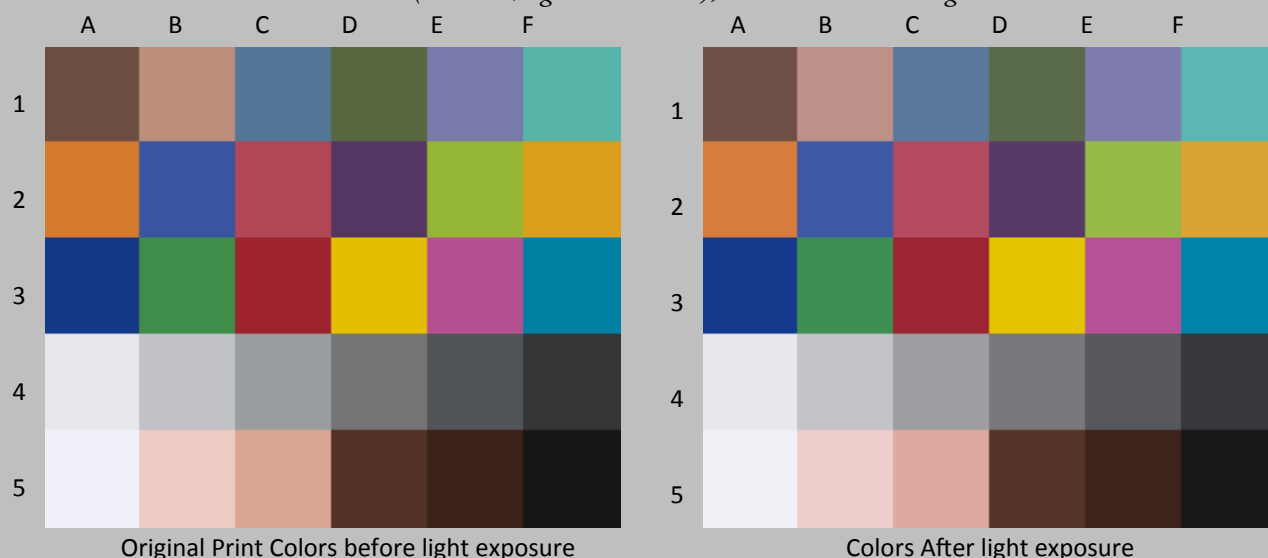


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	88.7	2.7	35.6	36.9	11.7	11.5	11.9	9.6
B1	Light Skin	83.1	4.7	63.0	64.5	16.2	16.0	16.5	12.1
C1	Blue sky	99.0	1.5	48.3	49.6	-5.8	-5.3	-22.0	-22.6
D1	Foliage	93.0	2.4	41.9	43.1	-12.0	-12.2	19.6	17.5
E1	blue flower	100.0	1.6	52.7	54.3	8.3	8.6	-26.0	-26.1
F1	bluish green	91.8	3.3	67.6	68.7	-31.3	-30.2	-3.0	-5.9
A1	orange	91.6	6.0	60.3	61.5	33.2	31.7	54.5	48.9
B2	purplish blue	100.0	1.4	37.0	38.3	9.5	9.1	-45.1	-45.2
C2	moderate red	91.6	4.5	45.8	46.6	44.9	44.6	15.0	10.6
D2	purple	94.6	2.5	27.8	29.1	21.0	21.4	-21.3	-23.4
E2	yellow green	92.8	5.3	69.9	71.2	-25.0	-25.9	58.1	53.1
F2	orange yellow	92.2	6.1	69.8	71.1	15.9	13.8	68.6	63.0
A3	blue	96.8	2.3	25.0	26.1	13.4	13.9	-48.7	-50.7
B3	green	92.4	4.1	52.4	53.5	-36.0	-36.2	28.1	24.1
C3	red	96.6	2.5	35.7	36.2	49.8	50.1	26.0	23.5
D3	yellow	97.1	3.6	78.3	80.0	2.6	-0.2	90.7	89.3
E3	magenta	96.0	2.7	49.2	50.1	47.9	47.7	-14.6	-17.1
F3	cyan	99.4	1.3	49.2	50.3	-22.5	-21.9	-28.2	-28.6
A4	white	98.1	0.8	91.7	92.2	0.7	0.8	-2.2	-2.9
B4	neutral 8	100.0	1.0	78.3	79.2	-0.2	-0.3	-2.6	-2.7
C4	neutral 6.5	95.8	1.4	64.2	65.3	-0.9	-0.4	-2.2	-3.0
D4	neutral 5	90.3	1.8	49.3	50.4	-0.2	0.0	-0.3	-1.7
E4	neutral 3.5	91.2	1.9	36.0	37.3	-0.5	-0.5	-1.5	-2.9
F4	black	93.1	1.7	22.2	23.4	-0.3	-0.2	-0.6	-1.8
A5	paper white	100.0	0.5	94.8	95.1	0.6	0.6	-3.7	-3.3
B5	Skin highlight L*=88	77.1	3.8	84.5	85.5	10.8	10.6	8.7	5.1
C5	Skin highlight L* =75	79.0	6.0	72.5	74.2	18.3	17.8	17.3	11.5
D5	Skin shadow L*=28	98.0	1.4	24.6	25.7	13.9	13.8	15.3	14.4
E5	Skin shadow L*=13	100.0	0.8	16.0	16.8	11.8	12.1	11.8	12.1
F5	Maximum Black	100.0	0.9	7.0	7.9	0.4	0.4	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	60 Megalux hours				
Average Score for all patches		94.0	96.0	2.7					
Worst 10% (3 lowest scoring patches)		79.7	92.2	6.0					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

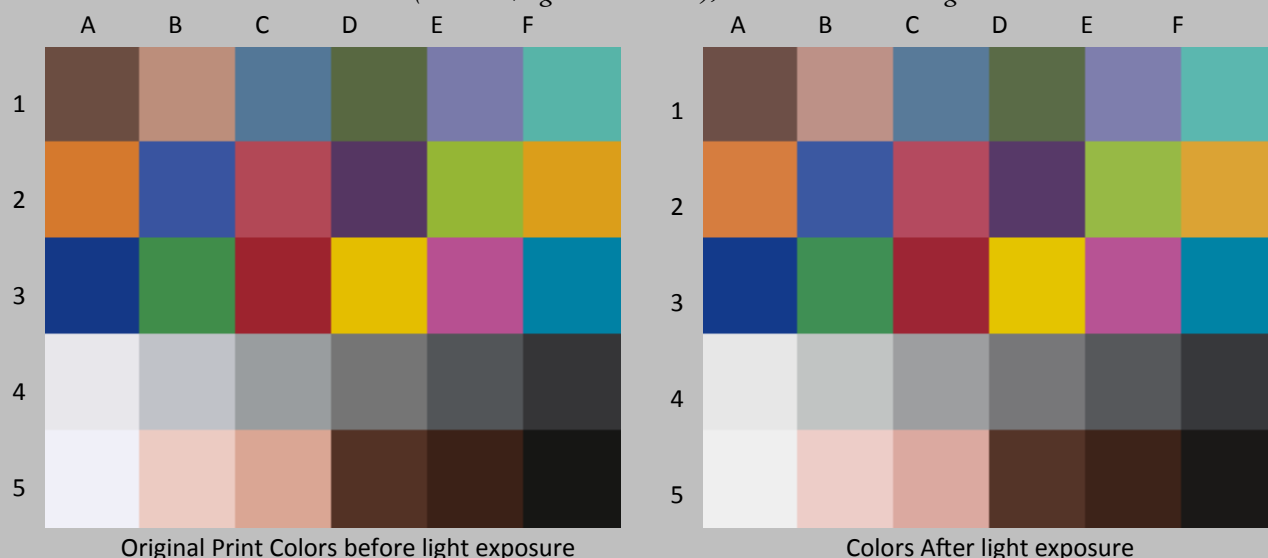

Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	89.0	2.7	35.6	36.9	11.7	11.6	11.9	9.6
B1	Light Skin	84.5	4.3	63.0	64.4	16.2	16.1	16.5	12.4
C1	Blue sky	98.7	1.5	48.3	49.5	-5.8	-5.6	-22.0	-21.2
D1	Foliage	93.5	2.3	41.9	43.0	-12.0	-12.0	19.6	17.6
E1	blue flower	96.3	2.1	52.7	54.2	8.3	8.2	-26.0	-24.5
F1	bluish green	95.0	2.3	67.6	68.5	-31.3	-30.2	-3.0	-4.7
A1	orange	90.4	6.7	60.3	61.4	33.2	31.8	54.5	48.1
B2	purplish blue	97.5	2.1	37.0	38.2	9.5	8.5	-45.1	-43.8
C2	moderate red	91.5	4.6	45.8	46.5	44.9	44.6	15.0	10.5
D2	purple	96.3	2.0	27.8	29.1	21.0	21.2	-21.3	-22.9
E2	yellow green	91.9	5.7	69.9	71.1	-25.0	-25.5	58.1	52.5
F2	orange yellow	91.2	6.8	69.8	71.0	15.9	14.0	68.6	62.1
A3	blue	98.4	1.7	25.0	26.1	13.4	13.3	-48.7	-50.0
B3	green	91.7	4.4	52.4	53.4	-36.0	-35.9	28.1	23.8
C3	red	96.4	2.5	35.7	36.1	49.8	50.0	26.0	23.5
D3	yellow	97.1	3.5	78.3	79.9	2.6	0.0	90.7	88.9
E3	magenta	97.9	1.7	49.2	50.0	47.9	47.3	-14.6	-16.0
F3	cyan	98.7	1.3	49.2	50.1	-22.5	-22.3	-28.2	-27.2
A4	white	81.4	2.3	91.7	91.7	0.7	0.5	-2.2	0.1
B4	neutral 8	82.5	2.3	78.3	78.9	-0.2	-0.6	-2.6	-0.5
C4	neutral 6.5	96.1	1.3	64.2	65.1	-0.9	-0.5	-2.2	-1.5
D4	neutral 5	98.7	1.2	49.3	50.3	-0.2	0.0	-0.3	-0.9
E4	neutral 3.5	96.5	1.5	36.0	37.2	-0.5	-0.4	-1.5	-2.4
F4	black	95.0	1.6	22.2	23.4	-0.3	-0.2	-0.6	-1.6
A5	paper white	67.3	3.6	94.8	94.6	0.6	0.2	-3.7	-0.2
B5	Skin highlight L*=88	90.1	2.0	84.5	85.1	10.8	10.6	8.7	6.9
C5	Skin highlight L* =75	80.8	5.5	72.5	73.9	18.3	17.8	17.3	12.0
D5	Skin shadow L*=28	98.1	1.4	24.6	25.6	13.9	13.8	15.3	14.4
E5	Skin shadow L*=13	100.0	0.9	16.0	16.8	11.8	12.0	11.8	12.2
F5	Maximum Black	100.0	1.2	7.0	8.2	0.4	0.6	0.5	0.7
Summary Results		I* Color	I* tone	ΔE	70 Megalux hours				
Average Score for all patches		92.8	95.7	2.8					
Worst 10% (3 lowest scoring patches)		76.5	92.1	6.4					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

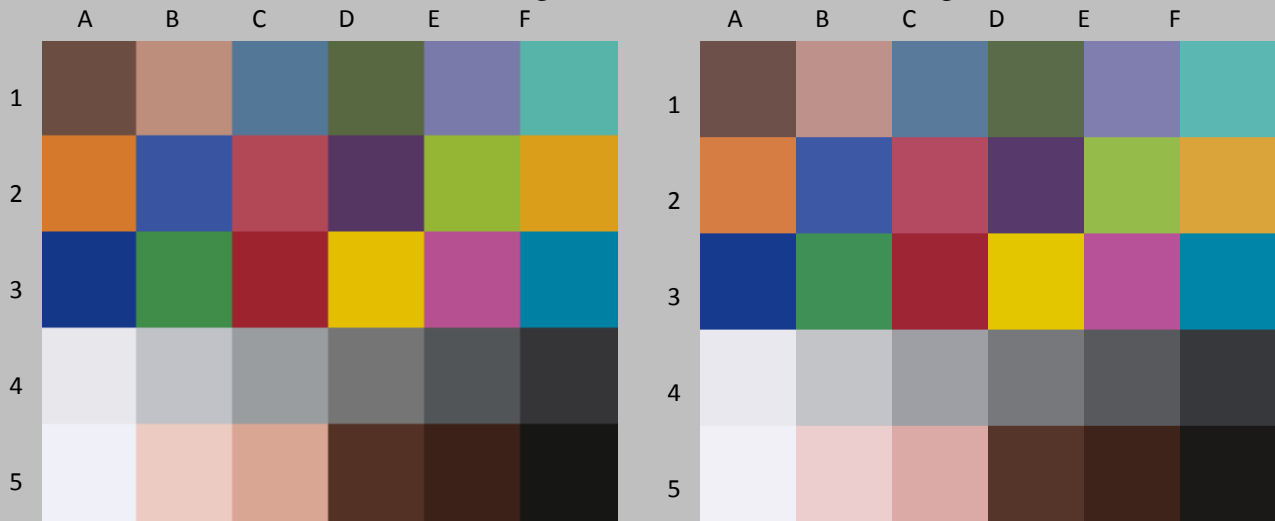


Original Print Colors before light exposure

Colors After light exposure


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	84.7	3.4	35.6	37.1	11.7	11.7	11.9	8.9
B1	Light Skin	76.1	6.3	63.0	64.7	16.2	16.3	16.5	10.5
C1	Blue sky	99.5	1.6	48.3	49.8	-5.8	-5.2	-22.0	-22.2
D1	Foliage	90.3	3.0	41.9	43.2	-12.0	-12.0	19.6	16.8
E1	blue flower	100.0	1.9	52.7	54.5	8.3	8.7	-26.0	-26.0
F1	bluish green	89.3	4.1	67.6	68.8	-31.3	-29.7	-3.0	-6.5
A1	orange	87.7	8.5	60.3	61.6	33.2	31.5	54.5	46.3
B2	purplish blue	100.0	1.4	37.0	38.4	9.5	9.2	-45.1	-44.9
C2	moderate red	89.1	5.7	45.8	46.7	44.9	44.6	15.0	9.4
D2	purple	93.3	2.9	27.8	29.2	21.0	21.6	-21.3	-23.7
E2	yellow green	89.5	7.3	69.9	71.4	-25.0	-25.7	58.1	51.0
F2	orange yellow	88.6	8.6	69.8	71.3	15.9	13.6	68.6	60.4
A3	blue	96.6	2.5	25.0	26.3	13.4	14.0	-48.7	-50.8
B3	green	89.5	5.4	52.4	53.6	-36.0	-35.9	28.1	22.7
C3	red	94.8	3.5	35.7	36.2	49.8	49.9	26.0	22.5
D3	yellow	96.0	4.6	78.3	80.2	2.6	-0.6	90.7	88.0
E3	magenta	94.9	3.2	49.2	50.2	47.9	47.8	-14.6	-17.6
F3	cyan	99.2	1.4	49.2	50.4	-22.5	-21.7	-28.2	-28.1
A4	white	97.1	0.8	91.7	92.1	0.7	1.0	-2.2	-2.9
B4	neutral 8	100.0	1.0	78.3	79.3	-0.2	-0.2	-2.6	-2.5
C4	neutral 6.5	95.7	1.6	64.2	65.4	-0.9	-0.2	-2.2	-2.9
D4	neutral 5	89.1	2.1	49.3	50.6	-0.2	0.2	-0.3	-1.8
E4	neutral 3.5	90.0	2.1	36.0	37.5	-0.5	-0.3	-1.5	-3.0
F4	black	91.3	2.0	22.2	23.7	-0.3	-0.2	-0.6	-1.9
A5	paper white	94.9	1.0	94.8	94.9	0.6	0.6	-3.7	-2.8
B5	Skin highlight L*=88	66.3	5.3	84.5	85.4	10.8	11.0	8.7	3.6
C5	Skin highlight L* =75	70.3	8.2	72.5	74.3	18.3	18.0	17.3	9.3
D5	Skin shadow L*=28	95.3	1.9	24.6	25.8	13.9	13.9	15.3	13.8
E5	Skin shadow L*=13	100.0	1.2	16.0	17.2	11.8	11.8	11.8	11.9
F5	Maximum Black	100.0	2.0	7.0	9.0	0.4	0.5	0.5	0.7
Summary Results		I* Color	I* tone	ΔE	80 Megalux hours				
Average Score for all patches		91.6	95.1	3.5					
Worst 10% (3 lowest scoring patches)		70.9	91.4	8.4					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

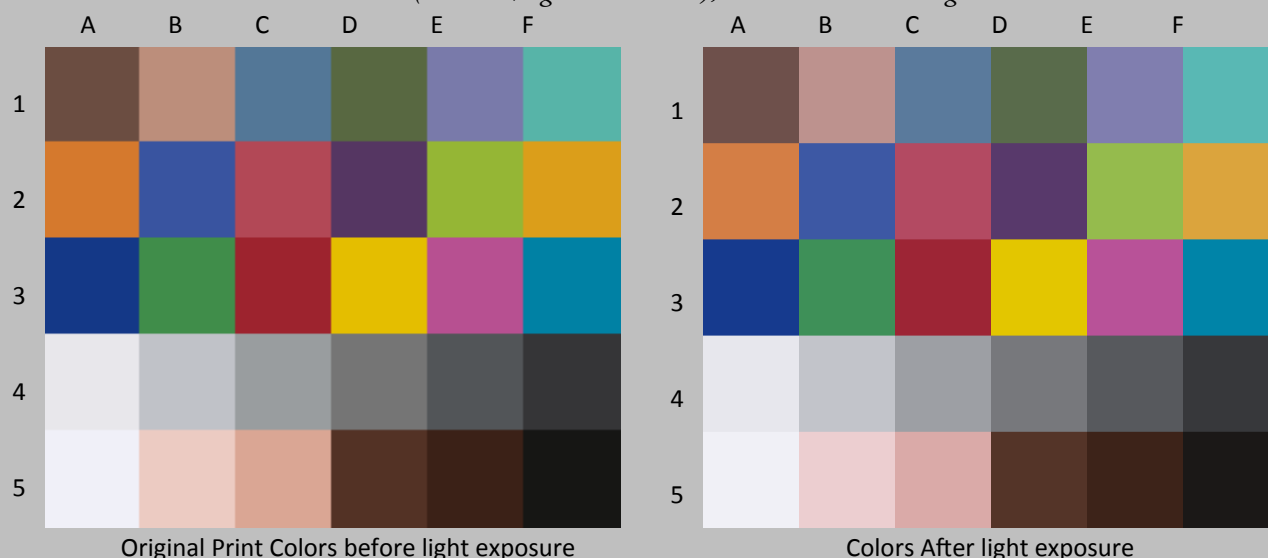


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	82.3	3.8	35.6	37.1	11.7	11.8	11.9	8.5
B1	Light Skin	71.7	7.3	63.0	64.8	16.2	16.4	16.5	9.5
C1	Blue sky	99.3	1.7	48.3	49.9	-5.8	-5.2	-22.0	-22.3
D1	Foliage	88.6	3.4	41.9	43.2	-12.0	-12.0	19.6	16.5
E1	blue flower	100.0	2.0	52.7	54.6	8.3	8.8	-26.0	-26.2
F1	bluish green	87.3	4.7	67.6	68.9	-31.3	-29.5	-3.0	-7.1
A1	orange	85.8	9.7	60.3	61.7	33.2	31.5	54.5	45.1
B2	purplish blue	100.0	1.5	37.0	38.4	9.5	9.1	-45.1	-44.9
C2	moderate red	87.5	6.5	45.8	46.7	44.9	44.7	15.0	8.6
D2	purple	92.1	3.2	27.8	29.3	21.0	21.8	-21.3	-24.1
E2	yellow green	87.8	8.4	69.9	71.5	-25.0	-25.7	58.1	49.9
F2	orange yellow	86.8	9.9	69.8	71.3	15.9	13.5	68.6	59.1
A3	blue	95.7	2.9	25.0	26.3	13.4	14.3	-48.7	-51.2
B3	green	88.1	6.1	52.4	53.6	-36.0	-35.8	28.1	22.1
C3	red	94.0	3.9	35.7	36.2	49.8	50.0	26.0	22.1
D3	yellow	95.4	5.1	78.3	80.3	2.6	-0.7	90.7	87.4
E3	magenta	94.0	3.6	49.2	50.2	47.9	47.8	-14.6	-18.1
F3	cyan	99.2	1.4	49.2	50.5	-22.5	-21.7	-28.2	-28.0
A4	white	95.2	1.0	91.7	92.0	0.7	1.1	-2.2	-3.1
B4	neutral 8	100.0	0.9	78.3	79.2	-0.2	-0.3	-2.6	-2.6
C4	neutral 6.5	94.5	1.6	64.2	65.4	-0.9	-0.2	-2.2	-3.0
D4	neutral 5	87.4	2.2	49.3	50.6	-0.2	0.2	-0.3	-2.0
E4	neutral 3.5	88.1	2.2	36.0	37.5	-0.5	-0.3	-1.5	-3.2
F4	black	89.5	2.1	22.2	23.6	-0.3	0.0	-0.6	-2.1
A5	paper white	93.3	1.1	94.8	94.7	0.6	0.6	-3.7	-2.6
B5	Skin highlight L*=88	59.7	6.2	84.5	85.4	10.8	11.2	8.7	2.6
C5	Skin highlight L* =75	65.3	9.4	72.5	74.3	18.3	18.2	17.3	8.1
D5	Skin shadow L*=28	94.6	2.0	24.6	25.7	13.9	13.9	15.3	13.7
E5	Skin shadow L*=13	100.0	1.0	16.0	17.0	11.8	11.9	11.8	12.1
F5	Maximum Black	100.0	1.7	7.0	8.7	0.4	0.5	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	90 Megalux hours				
Average Score for all patches		90.1	94.8	3.9					
Worst 10% (3 lowest scoring patches)		65.6	90.9	9.7					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

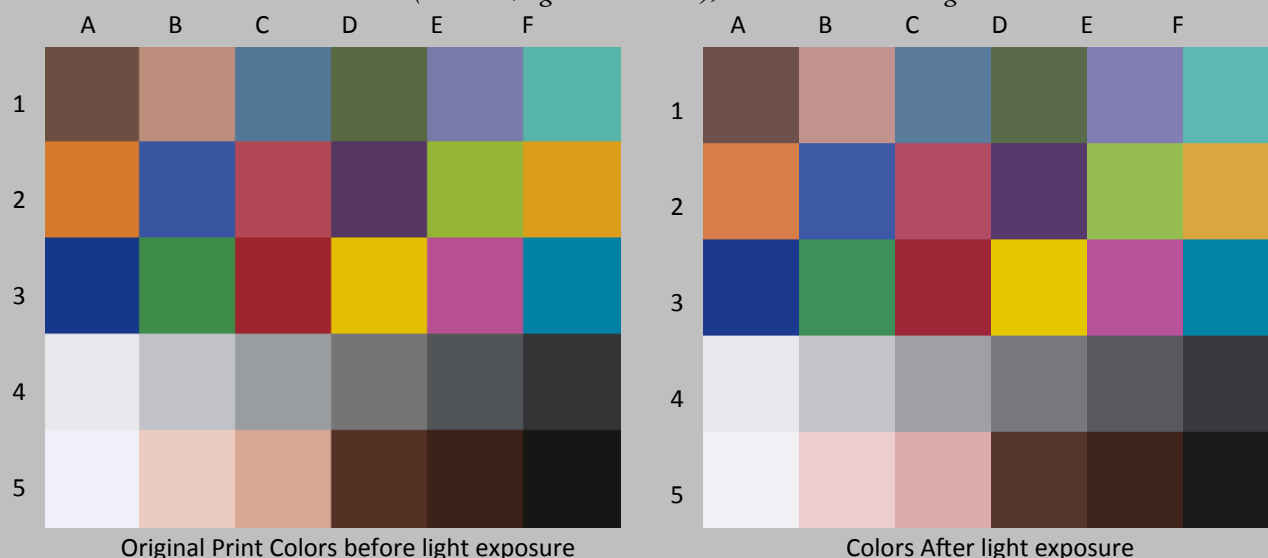


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	80.2	4.2	35.6	37.3	11.7	11.8	11.9	8.1
B1	Light Skin	68.2	8.1	63.0	65.0	16.2	16.6	16.5	8.7
C1	Blue sky	99.4	1.9	48.3	50.1	-5.8	-5.1	-22.0	-22.0
D1	Foliage	87.5	3.6	41.9	43.3	-12.0	-11.9	19.6	16.2
E1	blue flower	100.0	2.3	52.7	54.9	8.3	8.8	-26.0	-26.0
F1	bluish green	86.2	5.1	67.6	69.1	-31.3	-29.3	-3.0	-7.4
A1	orange	83.8	11.0	60.3	61.9	33.2	31.5	54.5	43.8
B2	purplish blue	100.0	1.6	37.0	38.5	9.5	9.1	-45.1	-44.7
C2	moderate red	86.1	7.2	45.8	46.8	44.9	45.0	15.0	7.9
D2	purple	90.9	3.6	27.8	29.5	21.0	22.0	-21.3	-24.4
E2	yellow green	85.9	9.6	69.9	71.8	-25.0	-25.6	58.1	48.7
F2	orange yellow	84.7	11.4	69.8	71.6	15.9	13.4	68.6	57.6
A3	blue	95.0	3.3	25.0	26.4	13.4	14.5	-48.7	-51.5
B3	green	86.3	6.9	52.4	53.8	-36.0	-35.7	28.1	21.3
C3	red	93.0	4.5	35.7	36.4	49.8	50.1	26.0	21.6
D3	yellow	94.9	5.6	78.3	80.6	2.6	-0.9	90.7	86.9
E3	magenta	93.6	3.9	49.2	50.4	47.9	48.0	-14.6	-18.3
F3	cyan	99.1	1.7	49.2	50.7	-22.5	-21.8	-28.2	-27.7
A4	white	100.0	0.5	91.7	92.1	0.7	1.0	-2.2	-2.4
B4	neutral 8	99.6	1.3	78.3	79.4	-0.2	-0.3	-2.6	-2.1
C4	neutral 6.5	96.0	1.8	64.2	65.8	-0.9	-0.1	-2.2	-2.7
D4	neutral 5	86.8	2.4	49.3	50.8	-0.2	0.3	-0.3	-2.0
E4	neutral 3.5	87.3	2.4	36.0	37.7	-0.5	-0.2	-1.5	-3.2
F4	black	89.0	2.3	22.2	23.9	-0.3	0.0	-0.6	-2.1
A5	paper white	83.6	2.1	94.8	94.9	0.6	0.5	-3.7	-1.7
B5	Skin highlight L*=88	59.1	6.3	84.5	85.6	10.8	11.3	8.7	2.6
C5	Skin highlight L* =75	61.9	10.3	72.5	74.6	18.3	18.2	17.3	7.2
D5	Skin shadow L*=28	93.2	2.3	24.6	25.8	13.9	14.0	15.3	13.4
E5	Skin shadow L*=13	100.0	1.1	16.0	17.1	11.8	12.1	11.8	12.0
F5	Maximum Black	100.0	2.0	7.0	9.0	0.4	0.5	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	100 Megalux hours				
Average Score for all patches		89.0	94.4	4.3					
Worst 10% (3 lowest scoring patches)		63.1	90.8	10.9					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

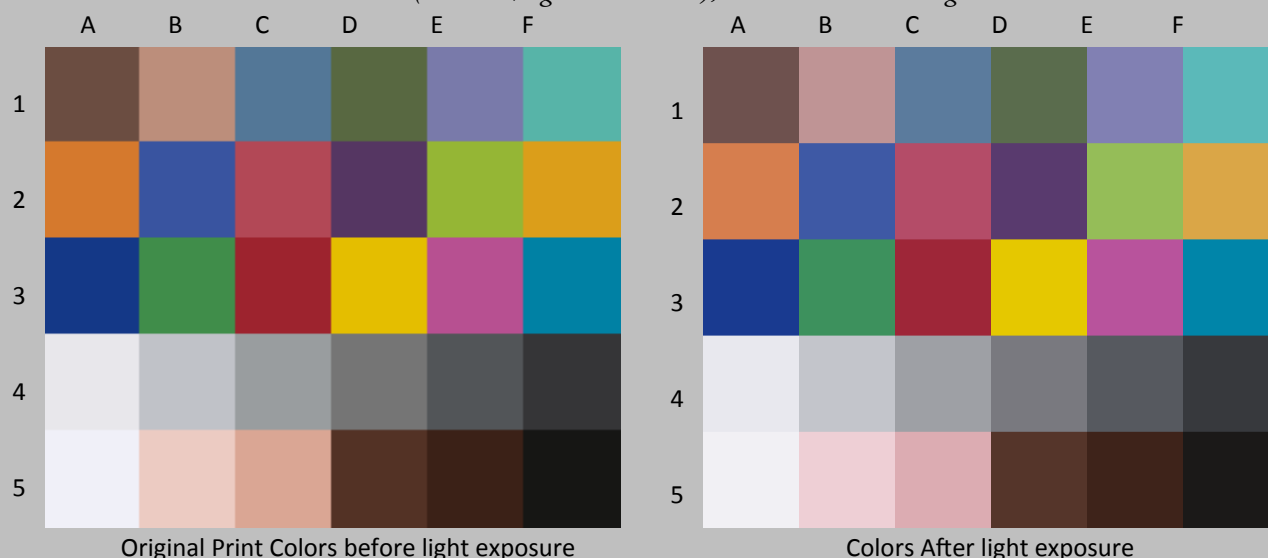


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	73.8	5.2	35.6	37.5	11.7	12.0	11.9	7.1
B1	Light Skin	57.7	10.5	63.0	65.4	16.2	17.1	16.5	6.3
C1	Blue sky	98.0	2.3	48.3	50.3	-5.8	-4.9	-22.0	-22.4
D1	Foliage	83.8	4.5	41.9	43.5	-12.0	-11.8	19.6	15.4
E1	blue flower	97.8	2.8	52.7	55.2	8.3	9.2	-26.0	-26.7
F1	bluish green	81.0	6.7	67.6	69.4	-31.3	-28.7	-3.0	-8.9
A1	orange	79.4	13.8	60.3	62.1	33.2	31.5	54.5	41.0
B2	purplish blue	100.0	1.8	37.0	38.8	9.5	9.4	-45.1	-45.1
C2	moderate red	82.5	8.9	45.8	47.0	44.9	45.2	15.0	6.2
D2	purple	88.7	4.4	27.8	29.9	21.0	22.2	-21.3	-25.0
E2	yellow green	81.8	12.3	69.9	72.2	-25.0	-25.6	58.1	46.1
F2	orange yellow	80.7	14.3	69.8	71.9	15.9	13.3	68.6	54.7
A3	blue	92.8	4.5	25.0	26.7	13.4	15.2	-48.7	-52.4
B3	green	82.4	8.7	52.4	54.1	-36.0	-35.5	28.1	19.6
C3	red	91.4	5.4	35.7	36.5	49.8	50.2	26.0	20.7
D3	yellow	93.4	7.1	78.3	81.0	2.6	-1.4	90.7	85.6
E3	magenta	91.1	5.2	49.2	50.7	47.9	48.3	-14.6	-19.5
F3	cyan	99.0	1.9	49.2	50.9	-22.5	-21.7	-28.2	-28.0
A4	white	94.6	1.2	91.7	92.3	0.7	1.2	-2.2	-3.1
B4	neutral 8	100.0	1.3	78.3	79.6	-0.2	-0.2	-2.6	-2.7
C4	neutral 6.5	90.2	2.4	64.2	66.0	-0.9	0.1	-2.2	-3.3
D4	neutral 5	80.2	3.0	49.3	51.0	-0.2	0.5	-0.3	-2.6
E4	neutral 3.5	81.0	3.0	36.0	37.8	-0.5	-0.1	-1.5	-3.8
F4	black	83.9	2.7	22.2	24.0	-0.3	0.2	-0.6	-2.6
A5	paper white	88.4	1.6	94.8	95.0	0.6	0.5	-3.7	-2.1
B5	Skin highlight L*=88	45.1	8.2	84.5	85.8	10.8	11.7	8.7	0.7
C5	Skin highlight L* =75	50.5	13.2	72.5	74.9	18.3	18.7	17.3	4.3
D5	Skin shadow L*=28	91.0	2.8	24.6	26.0	13.9	14.0	15.3	13.0
E5	Skin shadow L*=13	100.0	1.3	16.0	17.2	11.8	12.1	11.8	12.0
F5	Maximum Black	100.0	2.2	7.0	9.1	0.4	0.6	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	120 Megalux hours				
Average Score for all patches		85.3	93.8	5.4					
Worst 10% (3 lowest scoring patches)		51.1	89.6	13.7					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

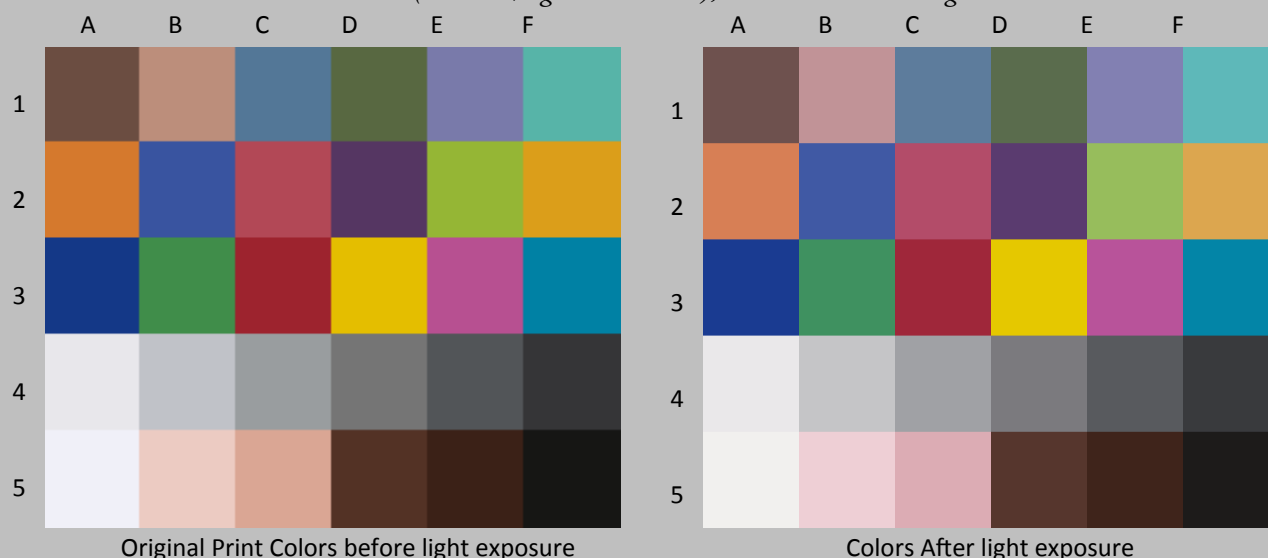


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	70.9	5.8	35.6	37.7	11.7	12.1	11.9	6.6
B1	Light Skin	52.4	11.8	63.0	65.6	16.2	17.5	16.5	5.1
C1	Blue sky	97.9	2.5	48.3	50.6	-5.8	-5.0	-22.0	-21.3
D1	Foliage	81.5	5.0	41.9	43.6	-12.0	-11.6	19.6	14.9
E1	blue flower	98.6	2.9	52.7	55.5	8.3	9.1	-26.0	-25.6
F1	bluish green	80.1	7.0	67.6	69.5	-31.3	-28.3	-3.0	-9.0
A1	orange	75.3	16.4	60.3	62.2	33.2	31.6	54.5	38.4
B2	purplish blue	97.7	2.5	37.0	39.0	9.5	9.0	-45.1	-43.6
C2	moderate red	80.8	9.7	45.8	47.2	44.9	45.3	15.0	5.5
D2	purple	89.0	4.4	27.8	30.0	21.0	22.5	-21.3	-24.8
E2	yellow green	77.9	14.7	69.9	72.3	-25.0	-25.0	58.1	43.7
F2	orange yellow	76.7	17.1	69.8	72.1	15.9	13.6	68.6	51.8
A3	blue	93.8	4.1	25.0	26.9	13.4	15.0	-48.7	-51.9
B3	green	79.2	10.2	52.4	54.1	-36.0	-34.9	28.1	18.1
C3	red	90.5	5.9	35.7	36.7	49.8	50.1	26.0	20.1
D3	yellow	91.7	8.5	78.3	81.2	2.6	-1.3	90.7	83.7
E3	magenta	92.6	4.5	49.2	50.8	47.9	48.2	-14.6	-18.8
F3	cyan	96.6	2.5	49.2	51.0	-22.5	-22.0	-28.2	-26.5
A4	white	87.5	1.7	91.7	92.1	0.7	0.9	-2.2	-0.5
B4	neutral 8	85.9	2.2	78.3	79.5	-0.2	-0.4	-2.6	-0.8
C4	neutral 6.5	95.8	2.2	64.2	66.2	-0.9	0.0	-2.2	-2.1
D4	neutral 5	86.4	2.6	49.3	51.2	-0.2	0.6	-0.3	-1.9
E4	neutral 3.5	84.3	2.9	36.0	38.1	-0.5	0.1	-1.5	-3.4
F4	black	84.9	2.9	22.2	24.4	-0.3	0.3	-0.6	-2.4
A5	paper white	59.5	4.3	94.8	94.8	0.6	0.2	-3.7	0.6
B5	Skin highlight L*=88	49.1	7.7	84.5	85.8	10.8	11.8	8.7	1.2
C5	Skin highlight L* =75	46.0	14.3	72.5	75.1	18.3	18.9	17.3	3.2
D5	Skin shadow L*=28	88.6	3.3	24.6	26.3	13.9	14.1	15.3	12.5
E5	Skin shadow L*=13	100.0	1.6	16.0	17.6	11.8	12.0	11.8	11.6
F5	Maximum Black	100.0	2.9	7.0	9.8	0.4	0.7	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	140 Megalux hours				
Average Score for all patches		83.0	93.0	6.1					
Worst 10% (3 lowest scoring patches)		49.2	88.4	16.0					

Epson Stylus Pro 7890, Epson OEM UltraChrome K3™ with Vivid Magenta, Red River Ultra Pro Satin 2.0 (68lb - 270gsm - 10.4 mil), no additional coating

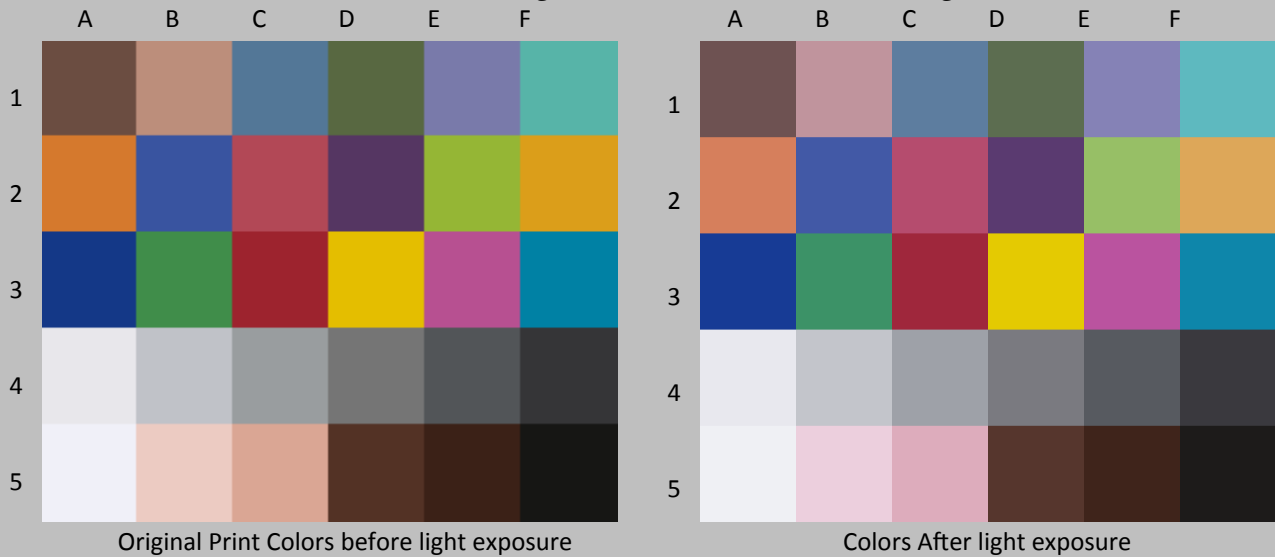

Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	62.1	7.2	35.6	38.0	11.7	12.3	11.9	5.1
B1	Light Skin	37.1	15.3	63.0	66.1	16.2	18.1	16.5	1.6
C1	Blue sky	96.5	2.9	48.3	50.9	-5.8	-4.5	-22.0	-22.4
D1	Foliage	75.7	6.4	41.9	43.8	-12.0	-11.5	19.6	13.5
E1	blue flower	95.1	3.7	52.7	55.9	8.3	9.8	-26.0	-27.2
F1	bluish green	70.7	10.0	67.6	69.8	-31.3	-27.3	-3.0	-11.8
A1	orange	69.2	20.3	60.3	62.4	33.2	31.7	54.5	34.4
B2	purplish blue	99.8	2.4	37.0	39.3	9.5	9.8	-45.1	-44.6
C2	moderate red	75.3	12.3	45.8	47.4	44.9	45.5	15.0	2.9
D2	purple	83.8	5.9	27.8	30.2	21.0	23.2	-21.3	-26.2
E2	yellow green	71.5	18.8	69.9	72.8	-25.0	-24.9	58.1	39.6
F2	orange yellow	70.7	21.3	69.8	72.4	15.9	13.5	68.6	47.6
A3	blue	89.8	6.0	25.0	27.1	13.4	16.2	-48.7	-53.6
B3	green	73.3	12.8	52.4	54.4	-36.0	-34.5	28.1	15.5
C3	red	87.6	7.5	35.7	36.7	49.8	50.2	26.0	18.5
D3	yellow	88.9	11.1	78.3	81.6	2.6	-1.9	90.7	81.2
E3	magenta	87.6	6.9	49.2	51.0	47.9	48.9	-14.6	-21.2
F3	cyan	97.8	2.5	49.2	51.4	-22.5	-21.4	-28.2	-27.6
A4	white	94.4	1.1	91.7	92.2	0.7	1.2	-2.2	-3.1
B4	neutral 8	100.0	1.4	78.3	79.6	-0.2	-0.1	-2.6	-3.0
C4	neutral 6.5	83.0	3.1	64.2	66.5	-0.9	0.3	-2.2	-4.0
D4	neutral 5	71.9	3.8	49.3	51.4	-0.2	1.0	-0.3	-3.3
E4	neutral 3.5	73.1	3.8	36.0	38.2	-0.5	0.3	-1.5	-4.5
F4	black	77.4	3.5	22.2	24.4	-0.3	0.5	-0.6	-3.1
A5	paper white	84.4	2.0	94.8	94.8	0.6	0.5	-3.7	-1.8
B5	Skin highlight L*=88	20.8	11.6	84.5	86.0	10.8	12.5	8.7	-2.7
C5	Skin highlight L* =75	28.2	18.8	72.5	75.3	18.3	19.7	17.3	-1.2
D5	Skin shadow L*=28	84.5	4.1	24.6	26.3	13.9	14.2	15.3	11.6
E5	Skin shadow L*=13	100.0	1.6	16.0	17.6	11.8	12.0	11.8	11.6
F5	Maximum Black	100.0	3.0	7.0	10.0	0.4	0.7	0.5	0.6
Summary Results		I* Color	I* tone	ΔE	160 Megalux hours				
Average Score for all patches		78.3	92.2	7.7					
Worst 10% (3 lowest scoring patches)		28.7	87.4	20.1					

The 180 Megalux hour Update will be posted on approximately DEC 20, 2017.

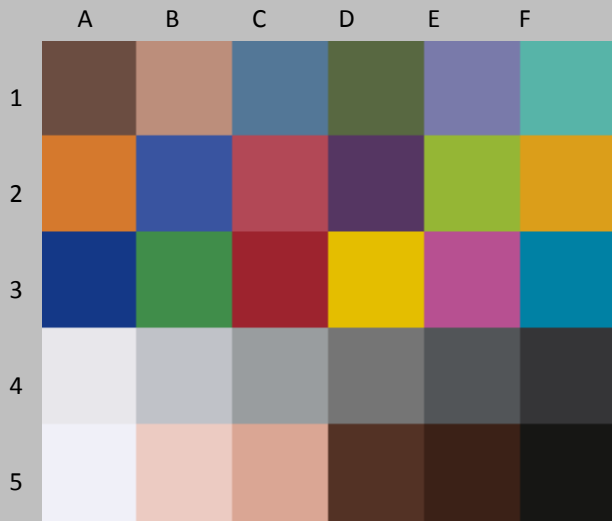

Original Print Colors before light exposure



Colors After light exposure

Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin			35.6		11.7		11.9	
B1	Light Skin			63.0		16.2		16.5	
C1	Blue sky			48.3		-5.8		-22.0	
D1	Foliage			41.9		-12.0		19.6	
E1	blue flower			52.7		8.3		-26.0	
F1	bluish green			67.6		-31.3		-3.0	
A1	orange			60.3		33.2		54.5	
B2	purplish blue			37.0		9.5		-45.1	
C2	moderate red			45.8		44.9		15.0	
D2	purple			27.8		21.0		-21.3	
E2	yellow green			69.9		-25.0		58.1	
F2	orange yellow			69.8		15.9		68.6	
A3	blue			25.0		13.4		-48.7	
B3	green			52.4		-36.0		28.1	
C3	red			35.7		49.8		26.0	
D3	yellow			78.3		2.6		90.7	
E3	magenta			49.2		47.9		-14.6	
F3	cyan			49.2		-22.5		-28.2	
A4	white			91.7		0.7		-2.2	
B4	neutral 8			78.3		-0.2		-2.6	
C4	neutral 6.5			64.2		-0.9		-2.2	
D4	neutral 5			49.3		-0.2		-0.3	
E4	neutral 3.5			36.0		-0.5		-1.5	
F4	black			22.2		-0.3		-0.6	
A5	paper white			94.8		0.6		-3.7	
B5	Skin highlight L*=88			84.5		10.8		8.7	
C5	Skin highlight L* =75			72.5		18.3		17.3	
D5	Skin shadow L*=28			24.6		13.9		15.3	
E5	Skin shadow L*=13			16.0		11.8		11.8	
F5	Maximum Black			7.0		0.4		0.5	
Summary Results		I* Color	I* tone	ΔE	180 Megalux hours				
Average Score for all patches									
Worst 10% (3 lowest scoring patches)									