

Aardenburg
144



IMAGING & ARCHIVES

Tested System:

ID#: 314

Printer: Epson SureColor P600

Inks/Colorants: Epson OEM Ultrachrome HD

Media: Hahnemuhle Photo Rag Pearl 320gsm

Coating(s): no additional coating

Sample #: AaI_20150503_SN005

Testing Status: 200 Megalux hours total light exposure

Testing is complete - there are no more updates

Conservation Display Rating (CDR)

Lower limit: 99 Megalux hours (for weakest 10% of the color patches)

Upper limit: 124 Megalux hours (for average of all the color patches)

Note: a CDR with narrow range (typically less than 2:1) indicates relatively even overall fading of the image. A wide range indicates faster fading in certain local colors/tones prior to general fading of most colors/tones in the entire image. Compare ratings for different systems directly and/or use the table on page 2 to estimate time (years) on display.

* Please read document AaI_2009_0118_TA-01.pdf, **"An Overview of the AaI&A Conservation Display Ratings"**,

This report has been prepared for the exclusive use of members of Aardenburg Imaging & Archives. Members may share this information with other members, friends, colleagues, and individual clients. It may also be distributed to groups for educational purposes (classes, lectures, educational seminars, etc). However, all contents including but not limited to Conservation Display Ratings may not be posted to web sites and may not be reproduced or distributed for corporate research, marketing, or other



About this Report

This report contains light fastness information about a sample test print produced by a specific digital printing system. “System” refers to all hardware, software, and materials used to make the finished print. The hardware, software, material components, and printmaker’s skills contribute to the final image quality and image permanence. The tested sample is made with current or recently discontinued stocks of commercially available products unless otherwise stated. Each sample has been prepared by Aardenburg Imaging & Archives or one of its members in accordance with customary print making practices unless otherwise noted. The sample may also contain additional finishing materials such as overcoats and laminates which are also noted when used. Finally, the sample has been tested under standardized conditions that are defined on the Sample Description page (see page 4). AaI&A makes every effort to ensure but cannot guarantee that the samples are properly identified and documented and that test results are accurate. For this reason, AaI&A also strives to test independently produced sample replicates in order to increase sampling confidence and to provide information on process variability. Please compare the results in this report to replicate test samples when the data become available.



The magnitude and visual appearance of fading depends not only on the chosen printing system but the chosen image as well. In other words, different images are comprised of different colors, and the fading relationships between those colors dictate how the image will look as it fades. The sample print in this test report was made by reproducing the digital image shown on the left. It contains 30 standard colors. 24 of the colors are colorimetrically matched to the Macbeth ColorChecker™ chart viewed under D50 illumination. The remaining six colors supplement the ColorChecker™ array with four additional skin tone colors, one patch for paper white, and another for maximum black. The additional colors

Information about the fading characteristics of the product is provided in three ways:

1) You can visually assess the fading. The target images reproduced in this report are digitally reconstructed from the spectrally measured color data rather than scanning or otherwise reproducing the physical print by conventional techniques. This method ensures a colorimetrically accurate representation of the print appearance as the print fades. A calibrated monitor is recommended to experience the best possible reproduction of the test sample appearance. The side-by-side “before and after” presentation of the target images simulates looking at a perfect copy of the unexposed original print along side the same print after light exposure. You can also use Adobe Reader’s full screen mode to cycle through the pages and “animate” the fading.

2) I* Color and tonal accuracy scores are reported. This report includes I* metric scores that compare the color and tonal relationships of the light exposed samples to the color and tonal relationships existing in the original print prior to light exposure. Perfect I* scores of 100% can be approached when no significant fading occurs. Average scores above 90% generally indicate excellent retention of original quality, 80% good, 70% fair, etc., but your conclusions may vary depending on your image quality requirements. I* color rates the retained color accuracy (hue and chroma) while I* tone rates the retained tonal accuracy (lightness and contrast). The score is on a percentile scale where 100% is a perfect match between the comparison image (e.g., “after” light exposure) and the reference image (e.g., “before” any light exposure). 0% I* color means no color accuracy is left. 0% I* tone means essentially no tonality remains and all image information content is lost. Negative I* values have significance as well and contribute to the average I* score when they occur. Negative I* color values mean false color has occurred, for example, when a skin tone turns green or a neutral gray becomes distinctly colorful. Negative I* tone scores mean visual contrast between colors has become inverted (i.e., like the tonal relationships in a photographic film negative). Serious image quality problems must arise before false colors and/or tones appear. For more information on the I* metric, please refer to the AaI&A web site.

3) Color changes are also reported using the classic color difference model, ΔE . Note that ΔE values lose perceptual scaling significance when they become large (e.g., > 15). Also, the ΔE equation does not unambiguously measure changes in image contrast. This limitation is generally not a problem for paints and textiles, but can be a serious oversight when evaluating

Table to Convert Megalux-hours of Light Exposure to estimated “Years on Display” Light Fastness Ratings.												
Indoor Light Levels for Print Display		Multiply Mlux-hrs by	Megalux-hours in test									
Light Exposure	Description		10	20	30	40	50	60	70	80	90	100
≤ 10 Lux 24 hours per day	Interior rooms, storage areas, or hallways without windows, illuminated sparingly by artificial lighting	11.42	114	228	342	457	571	685	799	913	1027	1142
50 Lux 12 hours per day	“Museum Standard” display condition	4.57	46	91	137	183	228	274	325	365	411	457
120 Lux 12 hours per day “Kodak Display Years” (1)	Average home illumination level for photos is ~ 60 lux. 90% of all displayed photos do not exceed 120 lux (1).	1.90	19	38	57	76	95	114	133	152	171	190
228 Lux 12 hours per day	Relatively bright home or office. Note the simple 1:1 relationship between “years on display” and Mlux-hr values at this condition.	1.00	10	20	30	40	50	60	70	80	90	100
450 Lux 12 hours per day “WIR Display Years” (2) Also equals 500 lux for 11.8 hours per day	A bright home or commercial office building illumination level is 200-500 lux. Also, good illumination for color critical viewing and color matching tasks begins at about 500 lux.	0.51	5	10	15	20	25	30	35	41	46	51
2000 Lux 12 hours per day	Commercial Gallery. Also, critical color evaluation standards call for 2000 lux and a D50 illumination source.	0.114	1.1	2.3	3.4	4.6	5.7	6.8	8.0	9.1	10.3	11.4
5000 Lux 12 hours per day	E.g., Sunlight through a window striking print at an angle.	0.046	0.5	0.9	1.4	1.8	2.3	2.7	3.2	3.7	4.1	4.6
10,000 Lux 12 hours per day	South-facing window in U.S.A. , e.g., storefront display with photos directly facing window.	0.023	0.2	0.5	0.7	0.9	1.1	1.4	1.6	1.8	2.1	2.3

Light levels commonly encountered in the real world fluctuate widely throughout indoor print display environments and produce large variations in how long it takes for artwork to acquire light-induced damage. Use this table as a guide to estimate how many “years on display” (denoted in red text) it takes to accumulate an equivalent light exposure dosage. Review the test results to decide which Megalux-hour dose has caused fading to your level of concern (e.g., just noticeable, easily noticeable, objectionable, etc.). Then choose the “Light Exposure” description that best represents how your print is likely to be displayed. You may want to obtain a lux meter and make some measurements in your own display environment!

Note that as the years of display time increase, light-induced fading can be eclipsed by other serious aging mechanisms such as fading and/or staining caused by heat, humidity, and air pollutants. Mould damage can also occur at high humidity. Even when colorants remain water fast, direct contact with liquids may result in physical deformation and staining of the substrate. Also, temperature and especially strong seasonal humidity fluctuations can cause physical cracks and/or flaking, etc., over time. Handling damage such as scratching, abrasion, tears and creases, and catastrophic damage by smoke, fire, flood, etc., also destroy print quality over time. Thus, as illumination levels are reduced other forms of print degradation take on greater probability of occurrence.

(1) Eastman Kodak cited this exposure condition with a 90% confidence limit as a rationale for estimating print fading times of traditional color photo materials in typical home display environments. However, for light fading claims regarding its line of pigment-based inkjet printers, Kodak adopted the higher level of 450lux/12 hours per day which is also used by Wilhelm Imaging Research, Inc. (See below).

(2) Wilhelm Imaging Research (WIR) standardized its light fastness ratings on 450 lux for 12 hours per day in order to estimate the years on display necessary to reach “easily noticeable” fading. This average daily light exposure dosage, at an assumed 75°F/60%RH temperature and humidity level, has become a de facto industry standard for most industry-sponsored predictive “years of life” light fading estimates in the absence of a published International Standards Organization (ISO) test standard. The table above readily shows how much error occurs in such “print lifetime” predictions as actual real world light levels for prints on display routinely deviate above and below the assumed 450 lux intensity value.

Sample Description

Sample # AaI_20150503_SN005 **Batch #:** N1
Printer: Epson SureColor P600
Ink: Epson OEM Ultrachrome HD
Media: Hahnemuhle Photo Rag Pearl 320gsm
Coating(s): no additional coating

Test Print Prepared by: AaI&A member
Printed: May 3, 2015
Initial Print colors measured May 13, 2015
Test Started: May 13, 2015

Test Image: AaI_StandardColorSet(v2)forSRGB.tif
RIP?Driver settings: 5760 dpi, HS off, 16 bit

Media Setting Ultra Premium Luster

Profile: AaI_P600_HnPhRagPearl_1.icc **Rendering** perceptual
Profile type: custom

Paper White Color (UV-included versus UV-excluded)

<i>Optical Brighteners Present?</i>	L*		a*		b*	
<i>no</i>						
Media Whitepoint Color	UV inc	UV exc	UV inc	UV exc	UV inc	UV exc
	97.6	97.8	0.4	0.3	1.4	1.5
	<i>UV-inc/UV-exc ΔL*, Δa*, Δb* respectively</i>					
	0.1		0.1		0.2	
	<i>Calculated differences, especially for Δb*, indicate the role and magnitude of fluorescence on original paper color</i>					
Maximum Printed Black	L*	a*	b*	Optical Density (Dmax)		
	5.7	-0.2	-2.1	2.20		

Light source: Phillips Colortone F40T12/C50 – 5000°K full spectrum fluorescent. Color rendering Index (CRI) =92), soda lime glass filtered
Light Exposure Cycle: 8 hours on, 4 hours off, twice per 24 hours
CIELAB measurements: D50 2° observer, Xrite Gretag/Macbeth Spectrolino/Spectroscan

Average Illuminance during “on” cycle: 10640 Lux
Average Temperature: 24.3°C over full test duration, 25.1°C during light exposure.
Average Relative humidity: 57.6%RH over full test duration, 56.9%RH during light exposure.

Compare this sample to sample # AaI_20150503_SN006 (ID# 315 in the AaI&A database) which is printed with the newer Epson Ultrachrome HD ink set on the same paper batch and run side-by-side in test.

Conclusions:

This sample is part of Batch N in the Aardenburg light fade test results database. Batch N contains six printer/ink/media combinations intended to look at differences in the newer Epson UltraChrome HD ink set versus the older Epson K3 ink set as well as the Canon Lucia EX ink set on two media, Epson WaterColor Paper Textured 320gsm and Hahnemuhle Photo Rag Pearl 320gsm. To find all six test reports easily in the Aardenburg test results database, filter the database for [batch] = "N".

The 200 Megalux hour test cycle is now complete, and the Conservation Display ratings are as follows:

Epson K3 ink:

Hahnemuhle Photo Rag Pearl..... 59-83 Megalux hours
Epson WaterColor Paper Textured..... 55-82 Megalux hours

Epson HD ink:


Hahnemuhle Photo Rag Pearl..... 99-124 Megalux hours
Epson WaterColor Paper Textured..... 123-154 Megalux hours

Canon Lucia EX ink:



Hahnemuhle Photo Rag Pearl..... 118-165 Megalux hours
Epson WaterColor Paper Textured..... 109-200+ Megalux hours

Epson's newer HD ink set clearly outperformed the older K3 set in the early stages of fading where little or no noticeable fade takes place (i.e., the basis for the Conservation Display ratings). However, once the fading reached a point where it becomes more noticeable, the HD ink set began to show a significantly faster fading rate. Compare the graphs on page 6 in each of the six test printer/ink/media combinations to evaluate the nonlinearity in the fading curves. The Canon Lucia EX ink set exhibited a more linear response over the full 200 Mluxhr cycle which enabled it to achieve superior overall fade resistance with respect to the two media types tested.

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

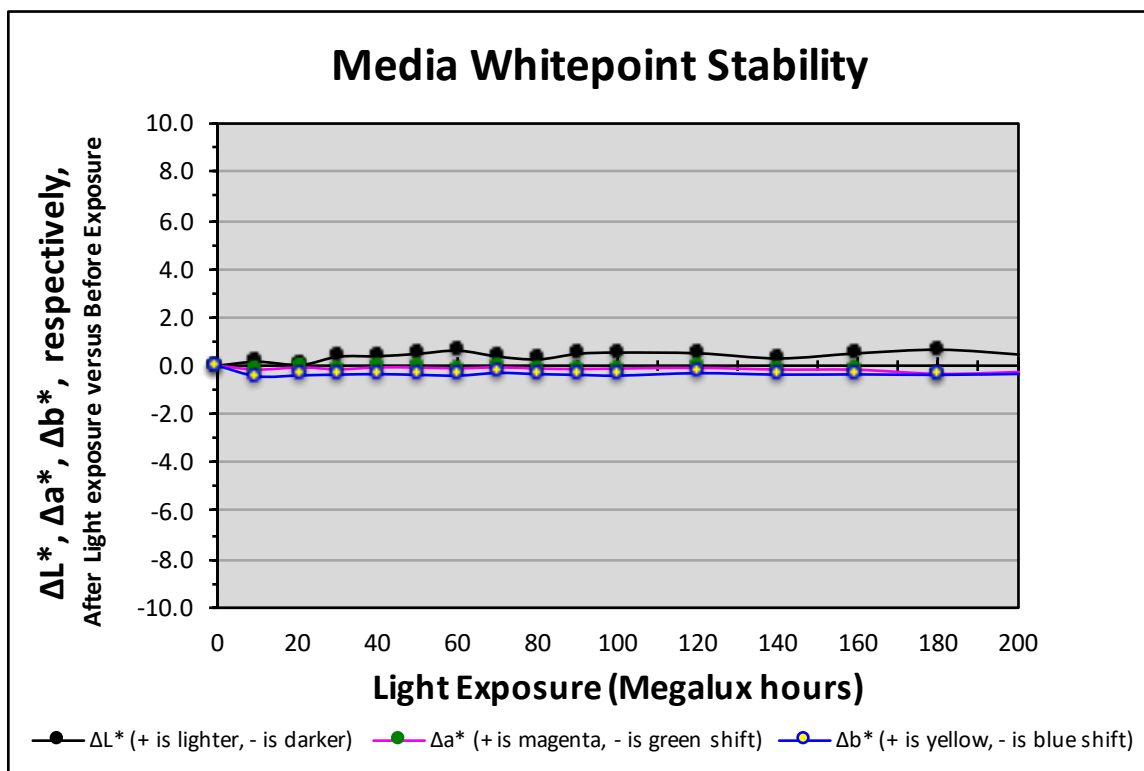


Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

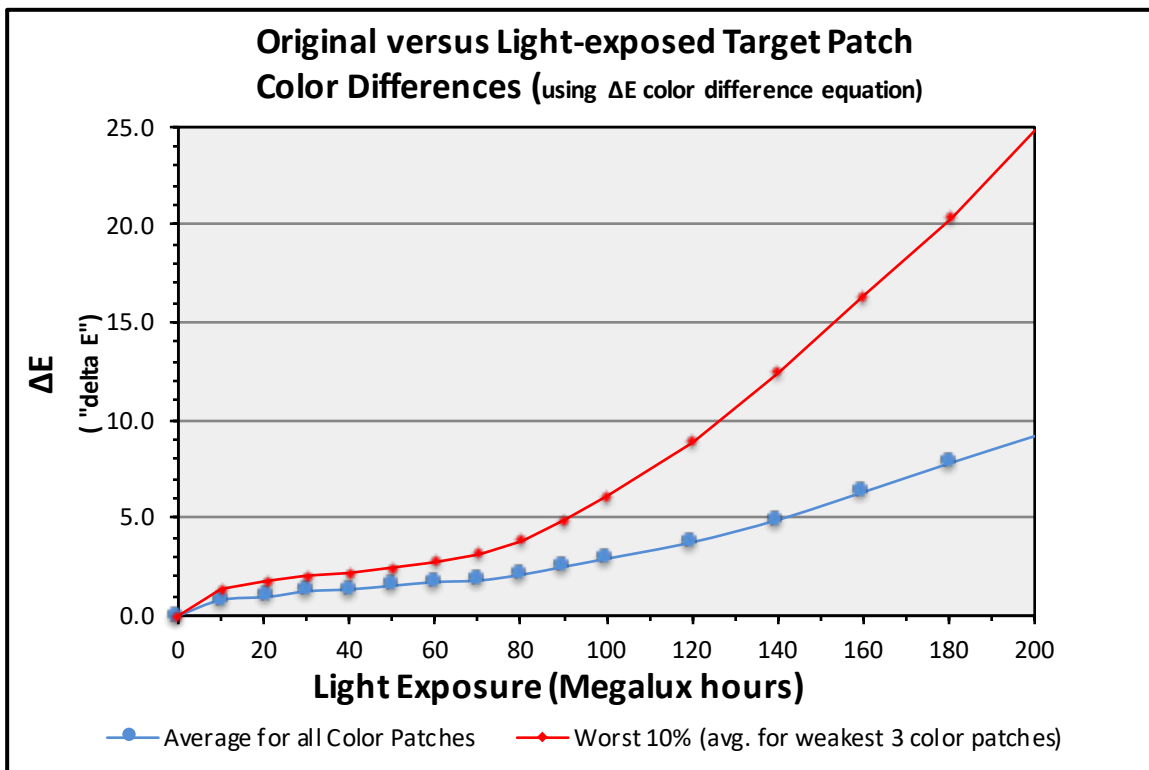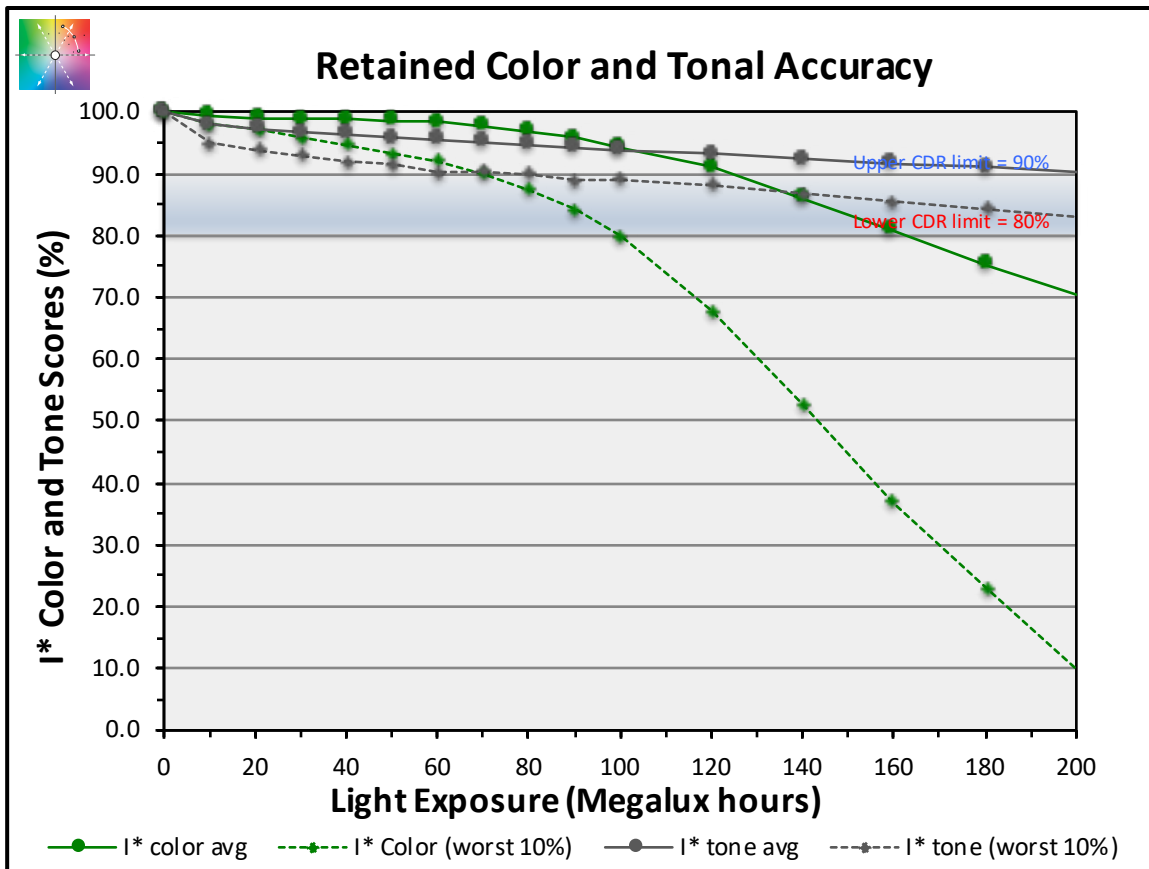


Values:

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

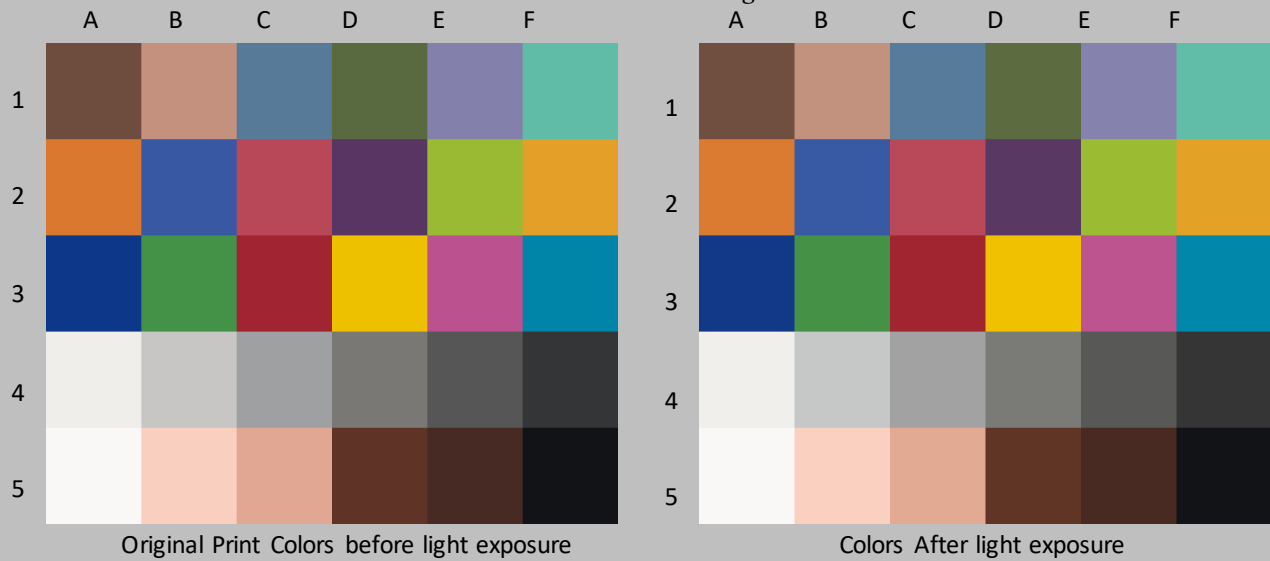


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	99.0	1.1	36.3	37.1	13.5	13.3	13.5	14.2
B1	Light Skin	98.3	1.2	64.6	65.3	17.6	16.7	18.1	18.5
C1	Blue sky	99.2	1.0	49.6	50.3	-6.3	-6.9	-21.2	-20.9
D1	Foliage	99.1	0.9	42.5	43.0	-11.7	-12.1	21.1	21.8
E1	blue flower	98.7	1.2	55.1	55.9	8.6	7.9	-22.9	-22.4
F1	bluish green	100.0	0.4	69.9	70.2	-32.1	-32.2	1.1	0.9
A1	orange	99.4	1.0	61.3	61.7	35.7	34.9	54.9	55.2
B2	purplish blue	98.7	1.4	38.0	38.9	8.1	7.1	-45.4	-44.8
C2	moderate red	100.0	0.7	46.8	47.3	47.3	47.0	15.8	16.2
D2	purple	99.7	0.8	28.4	28.9	22.6	22.3	-20.8	-20.3
E2	yellow green	100.0	0.5	71.5	71.8	-24.7	-24.8	60.3	60.7
F2	orange yellow	99.3	1.1	70.9	71.2	18.9	18.1	67.3	67.9
A3	blue	98.5	1.4	24.7	25.3	13.3	12.1	-49.6	-49.1
B3	green	100.0	0.4	54.1	54.3	-37.0	-37.2	31.3	31.5
C3	red	100.0	0.5	36.5	36.7	51.0	51.2	25.2	25.6
D3	yellow	99.9	0.7	80.1	80.3	6.3	5.8	91.2	91.4
E3	magenta	98.8	1.2	50.5	51.0	49.0	48.2	-13.0	-12.3
F3	cyan	100.0	0.7	49.5	50.1	-29.9	-30.2	-30.1	-29.9
A4	white	100.0	0.4	94.3	94.4	0.5	0.3	1.8	1.5
B4	neutral 8	100.0	0.6	79.9	80.4	-0.2	-0.6	0.6	0.5
C4	neutral 6.5	100.0	0.7	66.0	66.5	0.4	0.1	-0.6	-0.4
D4	neutral 5	97.4	1.0	50.8	51.5	0.1	-0.6	2.0	2.4
E4	neutral 3.5	99.7	0.9	36.4	37.1	0.0	-0.2	0.1	0.6
F4	black	100.0	0.4	21.8	22.0	-0.1	-0.2	-0.6	-0.3
A5	paper white	100.0	0.5	97.5	97.7	0.5	0.3	1.4	1.0
B5	Skin highlight L*=88	99.9	0.5	86.8	86.9	13.1	12.6	14.1	14.0
C5	Skin highlight L*=75	98.4	1.1	73.7	74.4	20.0	19.1	20.4	20.6
D5	Skin shadow L*=28	98.5	1.0	27.2	27.5	18.7	18.8	17.1	18.0
E5	Skin shadow L*=13	98.2	0.8	20.7	20.7	13.7	14.0	10.2	10.9
F5	Maximum Black	100.0	0.1	5.7	5.8	-0.2	-0.2	-2.1	-2.0
Summary Results		I* Color	I* tone	ΔE	10 Megalux hours				
Average Score for all patches		99.3	97.9	0.8					
Worst 10% (3 lowest scoring patches)		98.0	94.8	1.3					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

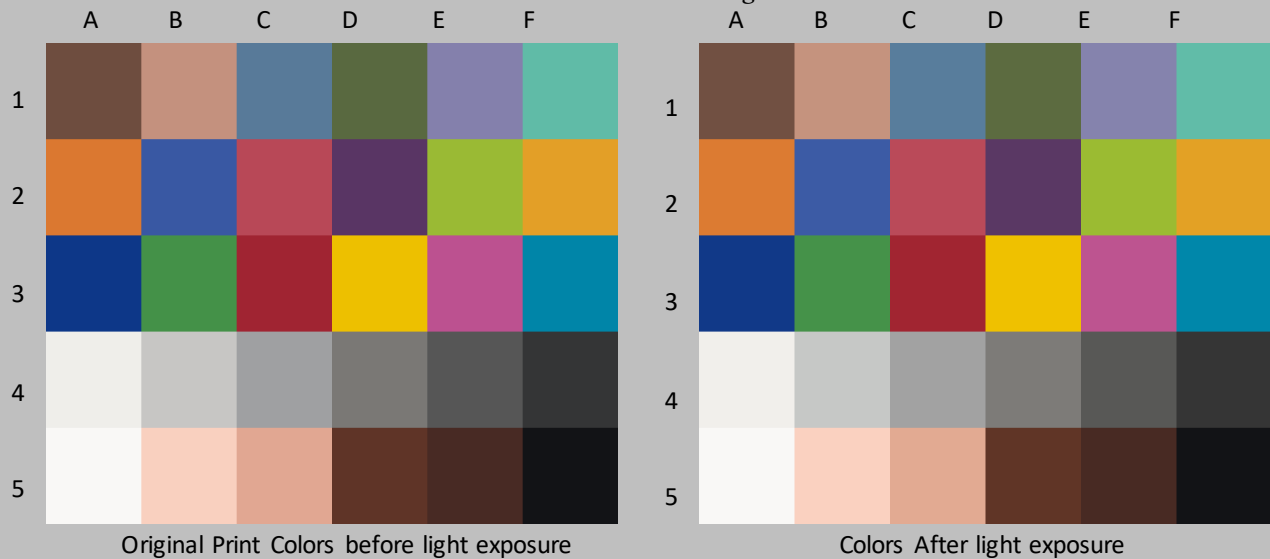


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	98.6	1.1	36.3	37.1	13.5	13.3	13.5	14.3
B1	Light Skin	98.1	1.3	64.6	65.5	17.6	16.8	18.1	18.7
C1	Blue sky	98.9	1.2	49.6	50.5	-6.3	-6.9	-21.2	-20.7
D1	Foliage	99.2	0.9	42.5	43.1	-11.7	-12.0	21.1	21.8
E1	blue flower	97.6	1.5	55.1	56.1	8.6	7.9	-22.9	-22.1
F1	bluish green	100.0	0.4	69.9	70.3	-32.1	-32.1	1.1	0.9
A1	orange	99.0	1.3	61.3	61.8	35.7	34.7	54.9	55.5
B2	purplish blue	97.8	1.8	38.0	39.1	8.1	6.9	-45.4	-44.4
C2	moderate red	99.8	0.8	46.8	47.3	47.3	47.1	15.8	16.4
D2	purple	99.3	1.0	28.4	29.1	22.6	22.4	-20.8	-20.2
E2	yellow green	100.0	0.5	71.5	71.9	-24.7	-24.8	60.3	60.5
F2	orange yellow	99.1	1.2	70.9	71.3	18.9	17.9	67.3	67.8
A3	blue	97.6	1.8	24.7	25.4	13.3	11.8	-49.6	-48.7
B3	green	100.0	0.4	54.1	54.4	-37.0	-37.0	31.3	31.4
C3	red	99.8	0.7	36.5	36.8	51.0	51.3	25.2	25.8
D3	yellow	99.5	1.0	80.1	80.4	6.3	5.7	91.2	91.8
E3	magenta	98.7	1.3	50.5	51.1	49.0	48.2	-13.0	-12.2
F3	cyan	99.9	0.9	49.5	50.2	-29.9	-30.3	-30.1	-29.8
A4	white	100.0	0.3	94.3	94.4	0.5	0.3	1.8	1.6
B4	neutral 8	99.8	0.7	79.9	80.4	-0.2	-0.7	0.6	0.5
C4	neutral 6.5	99.0	0.9	66.0	66.7	0.4	0.2	-0.6	-0.1
D4	neutral 5	98.3	1.1	50.8	51.6	0.1	-0.4	2.0	2.4
E4	neutral 3.5	99.0	1.1	36.4	37.2	0.0	-0.3	0.1	0.6
F4	black	100.0	0.6	21.8	22.2	-0.1	-0.2	-0.6	-0.1
A5	paper white	100.0	0.4	97.5	97.6	0.5	0.4	1.4	1.0
B5	Skin highlight L*=88	99.8	0.6	86.8	86.9	13.1	12.6	14.1	14.0
C5	Skin highlight L*=75	97.6	1.4	73.7	74.5	20.0	18.8	20.4	20.6
D5	Skin shadow L*=28	97.3	1.3	27.2	27.6	18.7	18.9	17.1	18.2
E5	Skin shadow L*=13	96.0	1.2	20.7	20.7	13.7	14.2	10.2	11.3
F5	Maximum Black	100.0	0.2	5.7	5.8	-0.2	-0.2	-2.1	-1.9
Summary Results		I* Color	I* tone	ΔE	20 Megalux hours				
Average Score for all patches		99.0	97.2	1.0					
Worst 10% (3 lowest scoring patches)		97.0	93.7	1.7					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

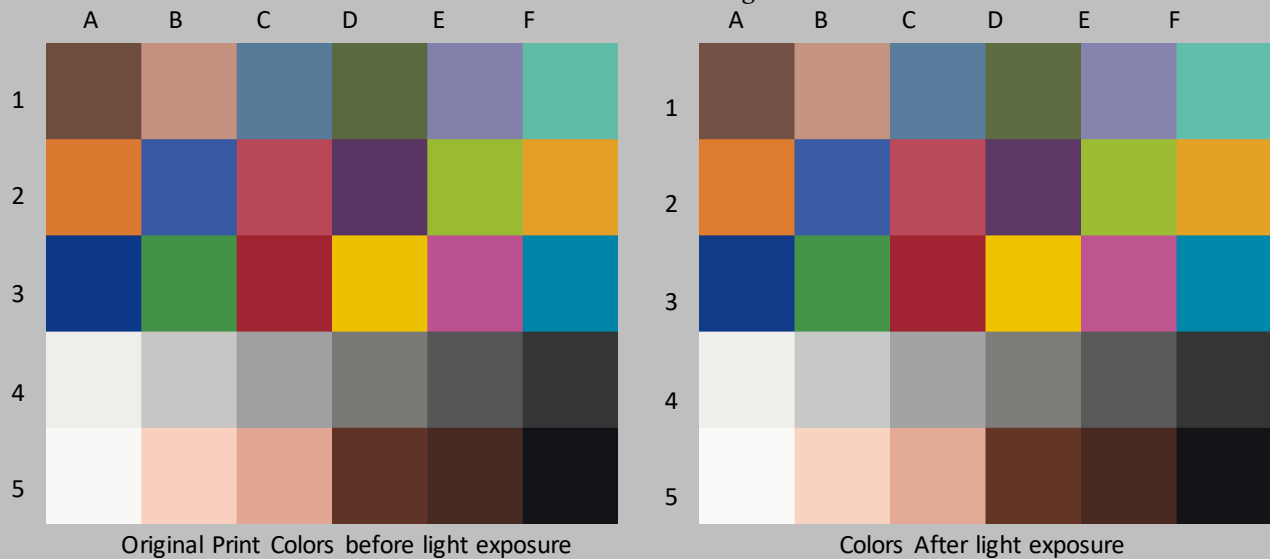


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	98.8	1.4	36.3	37.5	13.5	13.4	13.5	14.2
B1	Light Skin	97.9	1.6	64.6	65.9	17.6	16.6	18.1	18.5
C1	Blue sky	98.4	1.6	49.6	50.9	-6.3	-7.0	-21.2	-20.7
D1	Foliage	98.5	1.3	42.5	43.5	-11.7	-12.0	21.1	21.9
E1	blue flower	97.3	1.8	55.1	56.5	8.6	7.9	-22.9	-22.0
F1	bluish green	100.0	0.8	69.9	70.6	-32.1	-32.1	1.1	0.9
A1	orange	98.8	1.5	61.3	62.1	35.7	34.7	54.9	55.6
B2	purplish blue	97.5	2.1	38.0	39.3	8.1	6.7	-45.4	-44.4
C2	moderate red	100.0	0.9	46.8	47.6	47.3	47.1	15.8	16.0
D2	purple	100.0	1.1	28.4	29.3	22.6	22.6	-20.8	-20.3
E2	yellow green	100.0	0.8	71.5	72.2	-24.7	-24.8	60.3	60.8
F2	orange yellow	99.0	1.4	70.9	71.6	18.9	17.8	67.3	67.8
A3	blue	97.5	2.0	24.7	25.7	13.3	11.8	-49.6	-48.7
B3	green	100.0	0.7	54.1	54.7	-37.0	-37.1	31.3	31.4
C3	red	99.5	0.8	36.5	36.9	51.0	51.6	25.2	25.7
D3	yellow	99.1	1.5	80.1	80.7	6.3	5.5	91.2	92.2
E3	magenta	99.1	1.3	50.5	51.4	49.0	48.4	-13.0	-12.3
F3	cyan	99.7	1.2	49.5	50.5	-29.9	-30.4	-30.1	-29.8
A4	white	100.0	0.5	94.3	94.7	0.5	0.2	1.8	1.6
B4	neutral 8	98.3	1.1	79.9	80.8	-0.2	-0.8	0.6	0.5
C4	neutral 6.5	98.0	1.4	66.0	67.2	0.4	0.2	-0.6	0.0
D4	neutral 5	98.7	1.4	50.8	52.1	0.1	-0.4	2.0	2.4
E4	neutral 3.5	99.9	1.4	36.4	37.7	0.0	-0.2	0.1	0.6
F4	black	100.0	0.8	21.8	22.5	-0.1	-0.2	-0.6	-0.1
A5	paper white	100.0	0.5	97.5	97.9	0.5	0.3	1.4	1.0
B5	Skin highlight L*=88	99.0	0.9	86.8	87.3	13.1	12.5	14.1	13.9
C5	Skin highlight L*=75	97.1	1.8	73.7	75.0	20.0	18.7	20.4	20.3
D5	Skin shadow L*=28	96.1	1.7	27.2	27.9	18.7	19.1	17.1	18.5
E5	Skin shadow L*=13	93.7	1.6	20.7	21.0	13.7	14.3	10.2	11.6
F5	Maximum Black	100.0	0.4	5.7	6.1	-0.2	-0.2	-2.1	-2.0
Summary Results		I* Color	I* tone	ΔE	30 Megalux hours				
Average Score for all patches		98.7	96.7	1.2					
Worst 10% (3 lowest scoring patches)		95.6	92.9	2.0					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

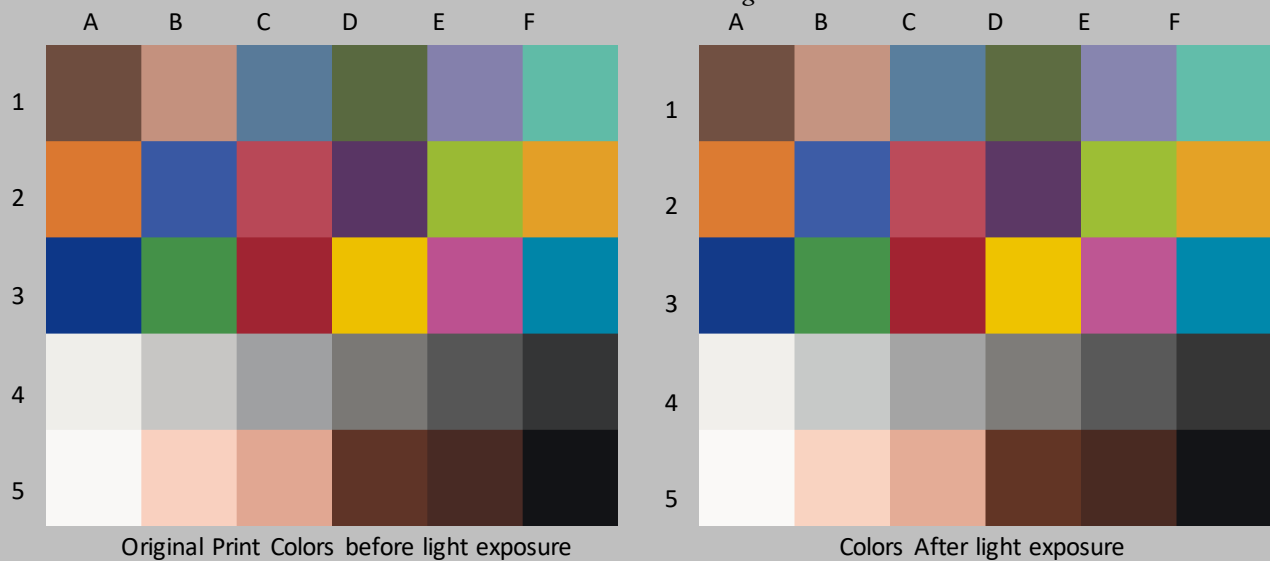


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	99.2	1.4	36.3	37.4	13.5	13.5	13.5	14.2
B1	Light Skin	98.4	1.7	64.6	66.0	17.6	16.7	18.1	18.0
C1	Blue sky	98.9	1.6	49.6	51.0	-6.3	-6.9	-21.2	-20.7
D1	Foliage	99.5	1.2	42.5	43.6	-11.7	-12.0	21.1	21.7
E1	blue flower	97.4	1.9	55.1	56.7	8.6	7.9	-22.9	-22.0
F1	bluish green	100.0	0.9	69.9	70.7	-32.1	-32.0	1.1	0.8
A1	orange	98.8	1.6	61.3	62.1	35.7	34.5	54.9	55.4
B2	purplish blue	97.0	2.3	38.0	39.4	8.1	6.6	-45.4	-44.2
C2	moderate red	100.0	0.9	46.8	47.7	47.3	47.4	15.8	15.8
D2	purple	100.0	1.2	28.4	29.6	22.6	22.6	-20.8	-20.4
E2	yellow green	100.0	0.9	71.5	72.4	-24.7	-24.9	60.3	60.6
F2	orange yellow	98.9	1.6	70.9	71.8	18.9	17.7	67.3	67.5
A3	blue	97.5	2.0	24.7	25.7	13.3	11.7	-49.6	-48.7
B3	green	100.0	0.7	54.1	54.8	-37.0	-37.0	31.3	31.2
C3	red	99.3	1.0	36.5	36.9	51.0	51.8	25.2	25.7
D3	yellow	98.8	1.7	80.1	80.8	6.3	5.4	91.2	92.5
E3	magenta	99.5	1.3	50.5	51.6	49.0	48.5	-13.0	-12.6
F3	cyan	99.8	1.3	49.5	50.6	-29.9	-30.4	-30.1	-29.8
A4	white	100.0	0.5	94.3	94.7	0.5	0.2	1.8	1.6
B4	neutral 8	98.3	1.2	79.9	80.9	-0.2	-0.8	0.6	0.4
C4	neutral 6.5	98.0	1.6	66.0	67.4	0.4	0.3	-0.6	0.0
D4	neutral 5	100.0	1.6	50.8	52.2	0.1	-0.4	2.0	2.2
E4	neutral 3.5	100.0	1.5	36.4	37.8	0.0	-0.2	0.1	0.4
F4	black	100.0	1.0	21.8	22.7	-0.1	-0.1	-0.6	-0.1
A5	paper white	100.0	0.5	97.5	97.9	0.5	0.4	1.4	1.0
B5	Skin highlight L*=88	98.7	1.0	86.8	87.4	13.1	12.5	14.1	13.8
C5	Skin highlight L*=75	96.5	2.1	73.7	75.3	20.0	18.6	20.4	19.9
D5	Skin shadow L*=28	95.4	1.8	27.2	27.9	18.7	19.3	17.1	18.7
E5	Skin shadow L*=13	91.9	2.0	20.7	21.3	13.7	14.4	10.2	11.9
F5	Maximum Black	100.0	0.4	5.7	6.2	-0.2	-0.2	-2.1	-2.1
Summary Results		I* Color	I* tone	ΔE	40 Megalux hours				
Average Score for all patches		98.7	96.3	1.3					
Worst 10% (3 lowest scoring patches)		94.6	91.9	2.2					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

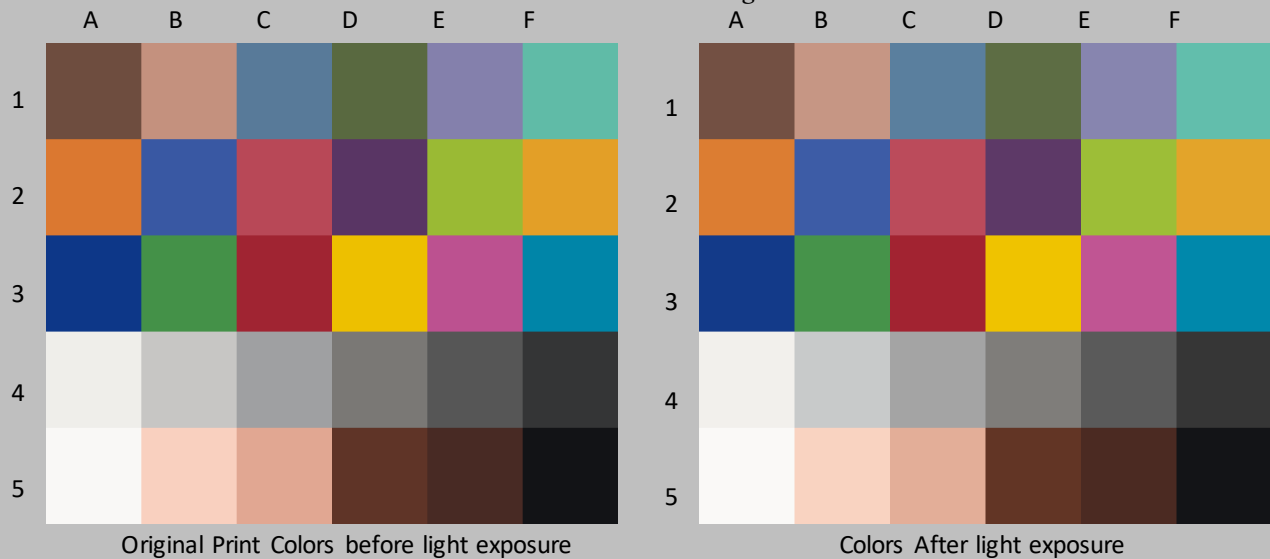


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	100.0	1.5	36.3	37.8	13.5	13.5	13.5	13.9
B1	Light Skin	97.2	2.1	64.6	66.3	17.6	16.7	18.1	17.4
C1	Blue sky	99.3	1.7	49.6	51.2	-6.3	-6.8	-21.2	-20.8
D1	Foliage	100.0	1.3	42.5	43.8	-11.7	-12.0	21.1	21.5
E1	blue flower	98.0	2.0	55.1	56.9	8.6	8.0	-22.9	-22.1
F1	bluish green	99.5	1.2	69.9	70.9	-32.1	-31.9	1.1	0.4
A1	orange	98.8	1.7	61.3	62.3	35.7	34.4	54.9	55.0
B2	purplish blue	97.0	2.5	38.0	39.6	8.1	6.6	-45.4	-44.2
C2	moderate red	99.9	1.2	46.8	47.9	47.3	47.4	15.8	15.3
D2	purple	100.0	1.3	28.4	29.7	22.6	22.7	-20.8	-20.6
E2	yellow green	100.0	1.1	71.5	72.6	-24.7	-25.0	60.3	60.3
F2	orange yellow	98.7	1.8	70.9	72.0	18.9	17.5	67.3	67.3
A3	blue	97.2	2.3	24.7	26.0	13.3	11.6	-49.6	-48.5
B3	green	100.0	1.0	54.1	55.0	-37.0	-37.1	31.3	30.9
C3	red	99.3	1.1	36.5	37.0	51.0	51.9	25.2	25.6
D3	yellow	98.4	2.1	80.1	81.0	6.3	5.2	91.2	92.8
E3	magenta	99.9	1.3	50.5	51.7	49.0	48.5	-13.0	-12.8
F3	cyan	100.0	1.4	49.5	50.7	-29.9	-30.3	-30.1	-29.9
A4	white	100.0	0.6	94.3	94.8	0.5	0.2	1.8	1.6
B4	neutral 8	97.3	1.3	79.9	81.0	-0.2	-0.9	0.6	0.3
C4	neutral 6.5	98.7	1.8	66.0	67.6	0.4	0.3	-0.6	0.0
D4	neutral 5	100.0	1.7	50.8	52.4	0.1	-0.3	2.0	1.9
E4	neutral 3.5	100.0	1.6	36.4	37.9	0.0	-0.1	0.1	0.2
F4	black	100.0	1.1	21.8	22.8	-0.1	-0.1	-0.6	-0.2
A5	paper white	100.0	0.6	97.5	98.0	0.5	0.4	1.4	1.0
B5	Skin highlight L*=88	97.8	1.2	86.8	87.5	13.1	12.4	14.1	13.5
C5	Skin highlight L*=75	95.3	2.6	73.7	75.5	20.0	18.4	20.4	19.3
D5	Skin shadow L*=28	94.5	2.1	27.2	28.0	18.7	19.4	17.1	18.9
E5	Skin shadow L*=13	89.4	2.3	20.7	21.1	13.7	14.6	10.2	12.3
F5	Maximum Black	100.0	0.4	5.7	6.1	-0.2	-0.2	-2.1	-2.0
Summary Results		I* Color	I* tone	ΔE	50 Megalux hours				
Average Score for all patches		98.5	95.8	1.5					
Worst 10% (3 lowest scoring patches)		93.1	91.5	2.5					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

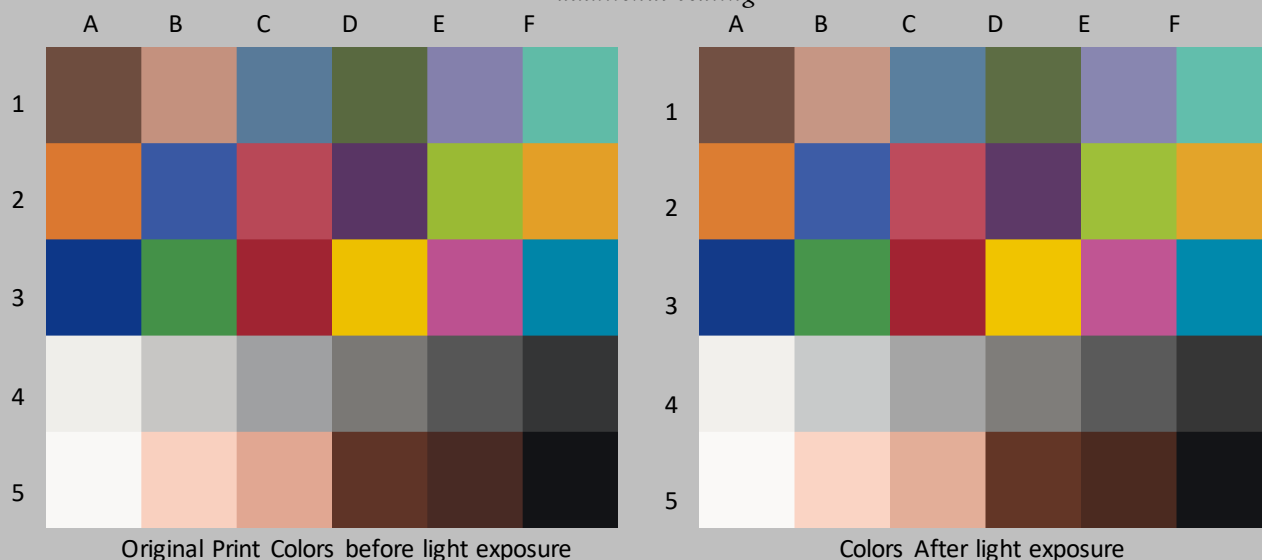


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	100.0	1.4	36.3	37.7	13.5	13.5	13.5	13.7
B1	Light Skin	95.4	2.4	64.6	66.3	17.6	16.7	18.1	16.8
C1	Blue sky	99.7	1.7	49.6	51.2	-6.3	-6.8	-21.2	-20.8
D1	Foliage	100.0	1.4	42.5	43.9	-11.7	-12.0	21.1	21.4
E1	blue flower	98.5	2.2	55.1	57.1	8.6	8.0	-22.9	-22.3
F1	bluish green	99.0	1.4	69.9	71.0	-32.1	-31.9	1.1	0.3
A1	orange	98.5	1.9	61.3	62.5	35.7	34.3	54.9	54.6
B2	purplish blue	96.9	2.6	38.0	39.8	8.1	6.6	-45.4	-44.2
C2	moderate red	98.8	1.6	46.8	48.0	47.3	47.6	15.8	14.8
D2	purple	100.0	1.4	28.4	29.7	22.6	23.0	-20.8	-20.9
E2	yellow green	100.0	1.4	71.5	72.9	-24.7	-25.1	60.3	60.1
F2	orange yellow	98.3	2.2	70.9	72.3	18.9	17.3	67.3	66.9
A3	blue	97.1	2.4	24.7	26.1	13.3	11.6	-49.6	-48.5
B3	green	99.7	1.2	54.1	55.1	-37.0	-37.2	31.3	30.7
C3	red	99.0	1.2	36.5	37.0	51.0	52.1	25.2	25.4
D3	yellow	98.0	2.6	80.1	81.2	6.3	5.1	91.2	93.1
E3	magenta	100.0	1.5	50.5	51.9	49.0	48.7	-13.0	-13.3
F3	cyan	100.0	1.5	49.5	50.9	-29.9	-30.3	-30.1	-29.9
A4	white	100.0	0.7	94.3	94.9	0.5	0.2	1.8	1.6
B4	neutral 8	96.2	1.5	79.9	81.1	-0.2	-1.0	0.6	0.2
C4	neutral 6.5	99.7	1.9	66.0	67.8	0.4	0.3	-0.6	-0.1
D4	neutral 5	99.1	1.9	50.8	52.6	0.1	-0.3	2.0	1.6
E4	neutral 3.5	100.0	1.7	36.4	38.0	0.0	-0.1	0.1	0.1
F4	black	100.0	1.1	21.8	22.9	-0.1	0.0	-0.6	-0.3
A5	paper white	100.0	0.8	97.5	98.1	0.5	0.3	1.4	1.0
B5	Skin highlight L*=88	96.5	1.5	86.8	87.8	13.1	12.3	14.1	13.3
C5	Skin highlight L*=75	93.4	3.1	73.7	75.8	20.0	18.4	20.4	18.6
D5	Skin shadow L*=28	94.3	2.1	27.2	28.0	18.7	19.4	17.1	18.9
E5	Skin shadow L*=13	88.1	2.5	20.7	21.1	13.7	14.7	10.2	12.5
F5	Maximum Black	100.0	0.7	5.7	6.4	-0.2	-0.2	-2.1	-2.0
Summary Results		I* Color	I* tone	ΔE	60 Megalux hours				
Average Score for all patches		98.2	95.5	1.7					
Worst 10% (3 lowest scoring patches)		92.0	90.2	2.8					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

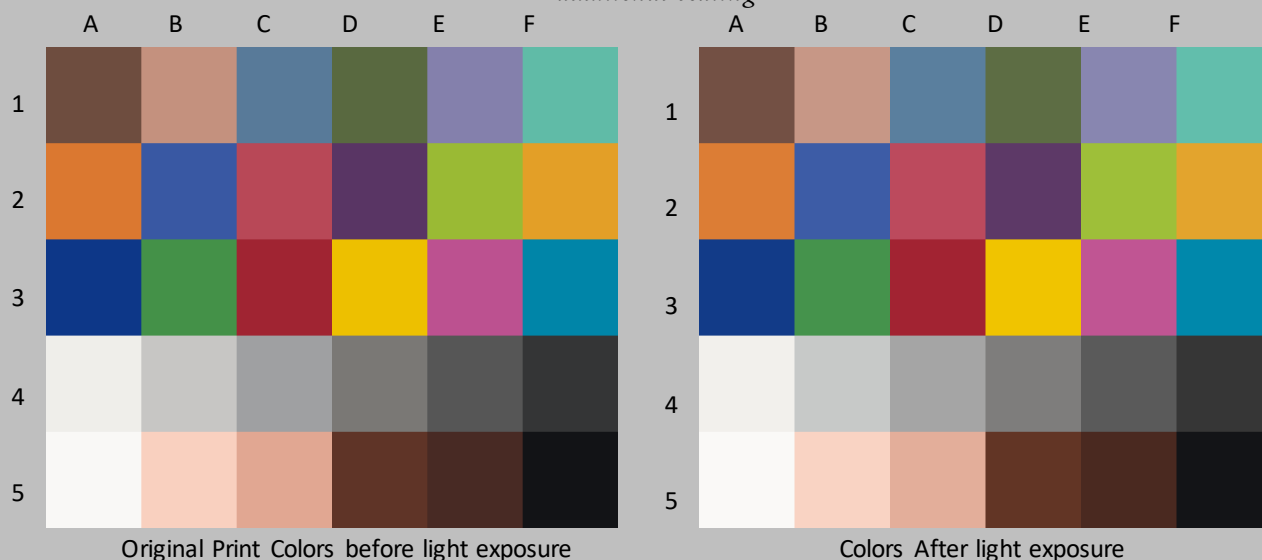


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	100.0	1.5	36.3	37.8	13.5	13.6	13.5	13.4
B1	Light Skin	92.6	3.1	64.6	66.6	17.6	16.7	18.1	15.9
C1	Blue sky	100.0	1.8	49.6	51.3	-6.3	-6.7	-21.2	-20.9
D1	Foliage	100.0	1.3	42.5	43.8	-11.7	-11.9	21.1	21.0
E1	blue flower	98.5	2.2	55.1	57.1	8.6	8.0	-22.9	-22.2
F1	bluish green	98.3	1.5	69.9	70.9	-32.1	-31.8	1.1	0.1
A1	orange	97.9	2.2	61.3	62.5	35.7	34.2	54.9	53.9
B2	purplish blue	96.5	2.7	38.0	39.7	8.1	6.5	-45.4	-43.9
C2	moderate red	97.5	2.1	46.8	48.0	47.3	47.6	15.8	14.1
D2	purple	100.0	1.4	28.4	29.7	22.6	23.0	-20.8	-21.1
E2	yellow green	99.4	1.6	71.5	72.8	-24.7	-25.2	60.3	59.6
F2	orange yellow	97.8	2.4	70.9	72.2	18.9	17.2	67.3	66.3
A3	blue	96.7	2.6	24.7	26.0	13.3	11.5	-49.6	-48.3
B3	green	98.9	1.4	54.1	55.0	-37.0	-37.0	31.3	30.3
C3	red	99.1	1.1	36.5	36.9	51.0	52.1	25.2	25.1
D3	yellow	97.9	2.6	80.1	81.1	6.3	5.0	91.2	93.1
E3	magenta	99.6	1.5	50.5	51.8	49.0	48.5	-13.0	-13.5
F3	cyan	100.0	1.3	49.5	50.7	-29.9	-30.1	-30.1	-29.7
A4	white	100.0	0.5	94.3	94.7	0.5	0.3	1.8	1.8
B4	neutral 8	96.5	1.3	79.9	80.9	-0.2	-0.9	0.6	0.2
C4	neutral 6.5	99.6	1.9	66.0	67.8	0.4	0.3	-0.6	-0.1
D4	neutral 5	96.9	1.9	50.8	52.5	0.1	-0.2	2.0	1.3
E4	neutral 3.5	100.0	1.7	36.4	38.0	0.0	-0.1	0.1	-0.2
F4	black	100.0	1.1	21.8	22.9	-0.1	0.1	-0.6	-0.4
A5	paper white	100.0	0.5	97.5	97.9	0.5	0.4	1.4	1.1
B5	Skin highlight L*=88	95.3	1.6	86.8	87.5	13.1	12.4	14.1	12.9
C5	Skin highlight L*=75	91.0	3.6	73.7	75.7	20.0	18.3	20.4	17.8
D5	Skin shadow L*=28	94.2	2.1	27.2	28.0	18.7	19.5	17.1	18.9
E5	Skin shadow L*=13	86.1	2.9	20.7	20.9	13.7	14.9	10.2	12.8
F5	Maximum Black	100.0	0.6	5.7	6.3	-0.2	-0.2	-2.1	-1.8
Summary Results		I* Color	I* tone	ΔE	70 Megalux hours				
Average Score for all patches		97.7	95.1	1.8					
Worst 10% (3 lowest scoring patches)		89.9	90.3	3.2					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

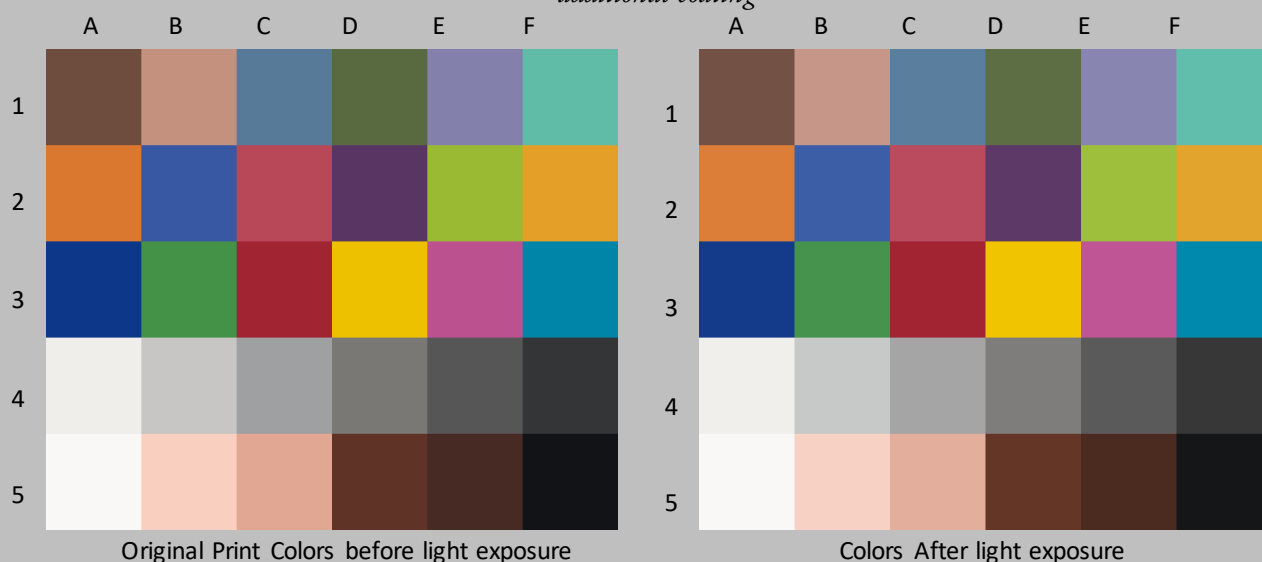


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	99.8	1.9	36.3	38.1	13.5	13.5	13.5	13.0
B1	Light Skin	88.7	4.0	64.6	66.7	17.6	16.7	18.1	14.9
C1	Blue sky	100.0	2.0	49.6	51.5	-6.3	-6.7	-21.2	-21.0
D1	Foliage	100.0	1.6	42.5	44.0	-11.7	-12.0	21.1	20.8
E1	blue flower	99.2	2.2	55.1	57.2	8.6	8.1	-22.9	-22.5
F1	bluish green	96.9	1.9	69.9	71.0	-32.1	-31.7	1.1	-0.4
A1	orange	96.8	3.0	61.3	62.7	35.7	34.0	54.9	53.0
B2	purplish blue	96.3	2.9	38.0	39.9	8.1	6.5	-45.4	-43.9
C2	moderate red	95.7	2.9	46.8	48.0	47.3	47.5	15.8	13.2
D2	purple	99.6	1.6	28.4	29.9	22.6	23.0	-20.8	-21.3
E2	yellow green	98.7	1.9	71.5	72.8	-24.7	-25.2	60.3	59.1
F2	orange yellow	97.0	2.9	70.9	72.2	18.9	17.0	67.3	65.6
A3	blue	96.4	2.8	24.7	26.2	13.3	11.4	-49.6	-48.1
B3	green	98.0	1.8	54.1	55.1	-37.0	-37.0	31.3	29.9
C3	red	98.9	1.2	36.5	37.0	51.0	52.0	25.2	24.7
D3	yellow	97.8	2.7	80.1	81.1	6.3	4.8	91.2	93.1
E3	magenta	98.8	1.8	50.5	51.9	49.0	48.6	-13.0	-14.0
F3	cyan	100.0	1.5	49.5	50.9	-29.9	-30.0	-30.1	-29.7
A4	white	100.0	0.5	94.3	94.6	0.5	0.2	1.8	1.7
B4	neutral 8	95.3	1.4	79.9	80.9	-0.2	-1.0	0.6	0.1
C4	neutral 6.5	100.0	2.0	66.0	68.0	0.4	0.3	-0.6	-0.4
D4	neutral 5	92.5	2.2	50.8	52.5	0.1	-0.2	2.0	0.9
E4	neutral 3.5	98.8	1.9	36.4	38.1	0.0	0.0	0.1	-0.5
F4	black	100.0	1.2	21.8	23.0	-0.1	0.2	-0.6	-0.3
A5	paper white	100.0	0.5	97.5	97.8	0.5	0.3	1.4	1.0
B5	Skin highlight L*=88	92.5	2.0	86.8	87.2	13.1	12.3	14.1	12.3
C5	Skin highlight L*=75	87.4	4.6	73.7	75.8	20.0	18.2	20.4	16.7
D5	Skin shadow L*=28	95.6	1.9	27.2	28.2	18.7	19.3	17.1	18.6
E5	Skin shadow L*=13	85.6	3.0	20.7	21.0	13.7	14.8	10.2	13.0
F5	Maximum Black	100.0	1.2	5.7	6.9	-0.2	0.1	-2.1	-1.7
Summary Results		I* Color	I* tone	ΔE	80 Megalux hours				
Average Score for all patches		96.9	94.7	2.1					
Worst 10% (3 lowest scoring patches)		87.2	89.8	3.8					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

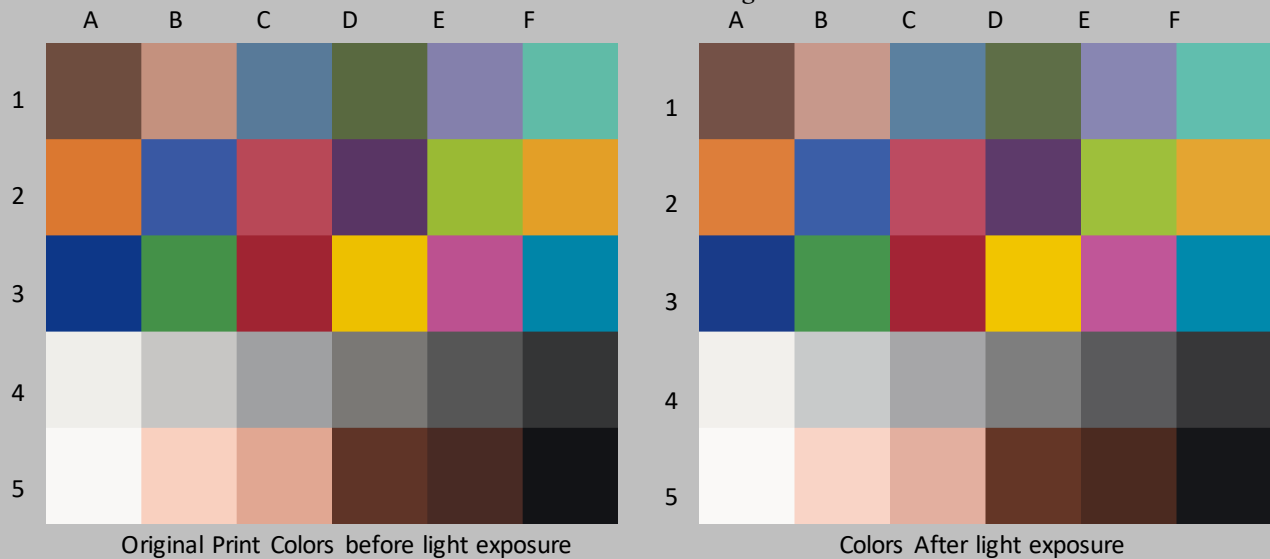


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	97.1	2.1	36.3	38.1	13.5	13.6	13.5	12.5
B1	Light Skin	84.2	5.1	64.6	67.0	17.6	16.8	18.1	13.7
C1	Blue sky	100.0	2.1	49.6	51.6	-6.3	-6.7	-21.2	-21.1
D1	Foliage	99.0	1.8	42.5	44.2	-11.7	-12.0	21.1	20.4
E1	blue flower	100.0	2.4	55.1	57.4	8.6	8.2	-22.9	-22.7
F1	bluish green	95.9	2.2	69.9	71.2	-32.1	-31.5	1.1	-0.7
A1	orange	95.7	3.7	61.3	62.9	35.7	34.0	54.9	52.2
B2	purplish blue	96.4	3.0	38.0	40.1	8.1	6.5	-45.4	-43.9
C2	moderate red	93.9	3.8	46.8	48.2	47.3	47.7	15.8	12.3
D2	purple	98.4	2.0	28.4	30.1	22.6	23.2	-20.8	-21.7
E2	yellow green	98.1	2.4	71.5	73.1	-24.7	-25.3	60.3	58.7
F2	orange yellow	96.0	3.7	70.9	72.5	18.9	16.7	67.3	64.8
A3	blue	96.7	2.8	24.7	26.4	13.3	11.5	-49.6	-48.3
B3	green	97.3	2.2	54.1	55.4	-37.0	-37.0	31.3	29.5
C3	red	98.3	1.6	36.5	37.2	51.0	52.2	25.2	24.3
D3	yellow	97.4	3.2	80.1	81.5	6.3	4.6	91.2	93.4
E3	magenta	97.7	2.3	50.5	52.2	49.0	48.8	-13.0	-14.7
F3	cyan	100.0	1.7	49.5	51.1	-29.9	-29.9	-30.1	-29.8
A4	white	100.0	0.6	94.3	94.8	0.5	0.2	1.8	1.6
B4	neutral 8	94.0	1.7	79.9	81.2	-0.2	-1.0	0.6	-0.1
C4	neutral 6.5	100.0	2.3	66.0	68.3	0.4	0.3	-0.6	-0.6
D4	neutral 5	87.5	2.7	50.8	52.9	0.1	-0.2	2.0	0.4
E4	neutral 3.5	94.5	2.3	36.4	38.4	0.0	0.1	0.1	-0.9
F4	black	100.0	1.5	21.8	23.2	-0.1	0.2	-0.6	-0.6
A5	paper white	100.0	0.6	97.5	98.0	0.5	0.3	1.4	1.0
B5	Skin highlight L*=88	90.8	2.5	86.8	87.8	13.1	12.3	14.1	12.0
C5	Skin highlight L*=75	83.6	5.7	73.7	76.2	20.0	18.2	20.4	15.5
D5	Skin shadow L*=28	94.5	2.2	27.2	28.3	18.7	19.5	17.1	18.8
E5	Skin shadow L*=13	84.3	3.2	20.7	21.3	13.7	14.8	10.2	13.2
F5	Maximum Black	100.0	1.7	5.7	7.4	-0.2	0.0	-2.1	-1.7
Summary Results		I* Color	I* tone	ΔE	90 Megalux hours				
Average Score for all patches		95.7	94.3	2.5					
Worst 10% (3 lowest scoring patches)		84.0	88.9	4.9					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

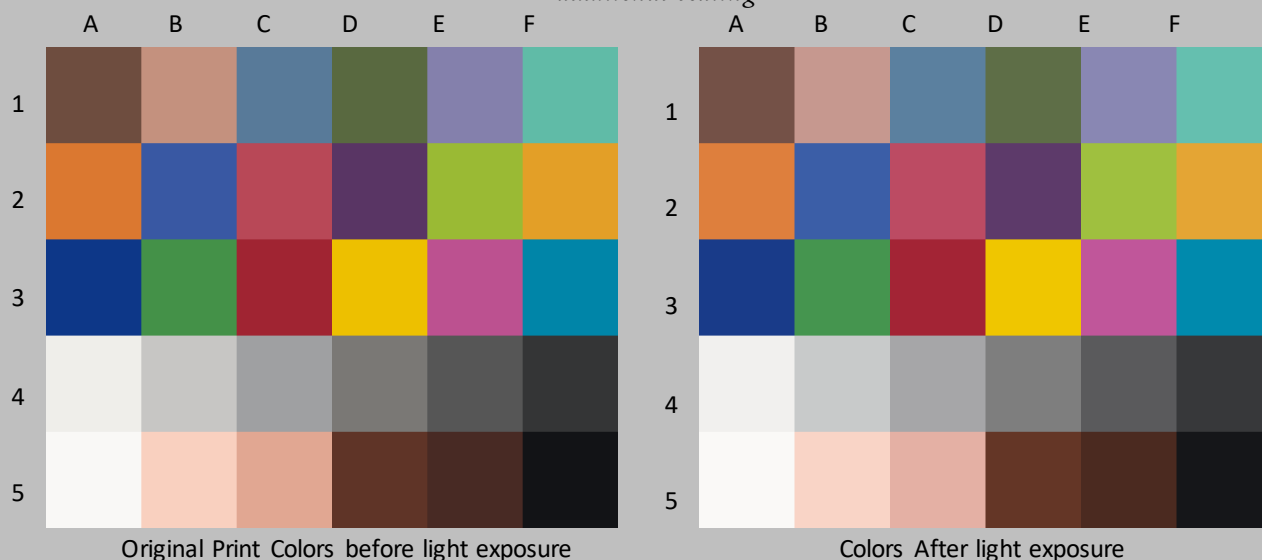


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	93.5	2.6	36.3	38.2	13.5	13.7	13.5	11.8
B1	Light Skin	78.5	6.5	64.6	67.2	17.6	17.0	18.1	12.2
C1	Blue sky	100.0	2.2	49.6	51.8	-6.3	-6.5	-21.2	-21.3
D1	Foliage	97.2	2.2	42.5	44.3	-11.7	-11.9	21.1	20.0
E1	blue flower	100.0	2.6	55.1	57.7	8.6	8.3	-22.9	-23.1
F1	bluish green	94.6	2.6	69.9	71.3	-32.1	-31.4	1.1	-1.1
A1	orange	94.3	4.6	61.3	63.0	35.7	33.9	54.9	51.2
B2	purplish blue	96.5	3.0	38.0	40.2	8.1	6.5	-45.4	-44.0
C2	moderate red	91.6	4.9	46.8	48.3	47.3	47.9	15.8	11.2
D2	purple	96.9	2.4	28.4	30.3	22.6	23.3	-20.8	-22.1
E2	yellow green	97.1	3.0	71.5	73.3	-24.7	-25.4	60.3	58.1
F2	orange yellow	94.9	4.5	70.9	72.7	18.9	16.6	67.3	63.9
A3	blue	96.8	2.8	24.7	26.5	13.3	11.5	-49.6	-48.3
B3	green	96.5	2.6	54.1	55.5	-37.0	-37.1	31.3	29.1
C3	red	97.6	2.1	36.5	37.4	51.0	52.2	25.2	23.8
D3	yellow	97.1	3.5	80.1	81.6	6.3	4.4	91.2	93.6
E3	magenta	96.0	3.1	50.5	52.3	49.0	49.0	-13.0	-15.5
F3	cyan	100.0	1.8	49.5	51.2	-29.9	-29.8	-30.1	-30.0
A4	white	100.0	0.8	94.3	94.9	0.5	0.1	1.8	1.5
B4	neutral 8	93.0	1.8	79.9	81.2	-0.2	-1.0	0.6	-0.2
C4	neutral 6.5	100.0	2.5	66.0	68.4	0.4	0.4	-0.6	-0.9
D4	neutral 5	81.5	3.2	50.8	53.0	0.1	0.0	2.0	-0.2
E4	neutral 3.5	90.3	2.6	36.4	38.5	0.0	0.1	0.1	-1.3
F4	black	100.0	1.7	21.8	23.5	-0.1	0.3	-0.6	-0.7
A5	paper white	100.0	0.7	97.5	98.1	0.5	0.3	1.4	1.0
B5	Skin highlight L*=88	88.6	2.9	86.8	87.9	13.1	12.3	14.1	11.5
C5	Skin highlight L*=75	79.2	6.9	73.7	76.4	20.0	18.3	20.4	14.1
D5	Skin shadow L*=28	94.4	2.2	27.2	28.2	18.7	19.6	17.1	18.8
E5	Skin shadow L*=13	82.9	3.5	20.7	21.3	13.7	15.0	10.2	13.4
F5	Maximum Black	99.7	1.9	5.7	7.6	-0.2	0.0	-2.1	-1.6
Summary Results		I* Color	I* tone	ΔE	100 Megalux hours				
Average Score for all patches		94.3	93.9	2.9					
Worst 10% (3 lowest scoring patches)		79.7	88.9	6.1					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

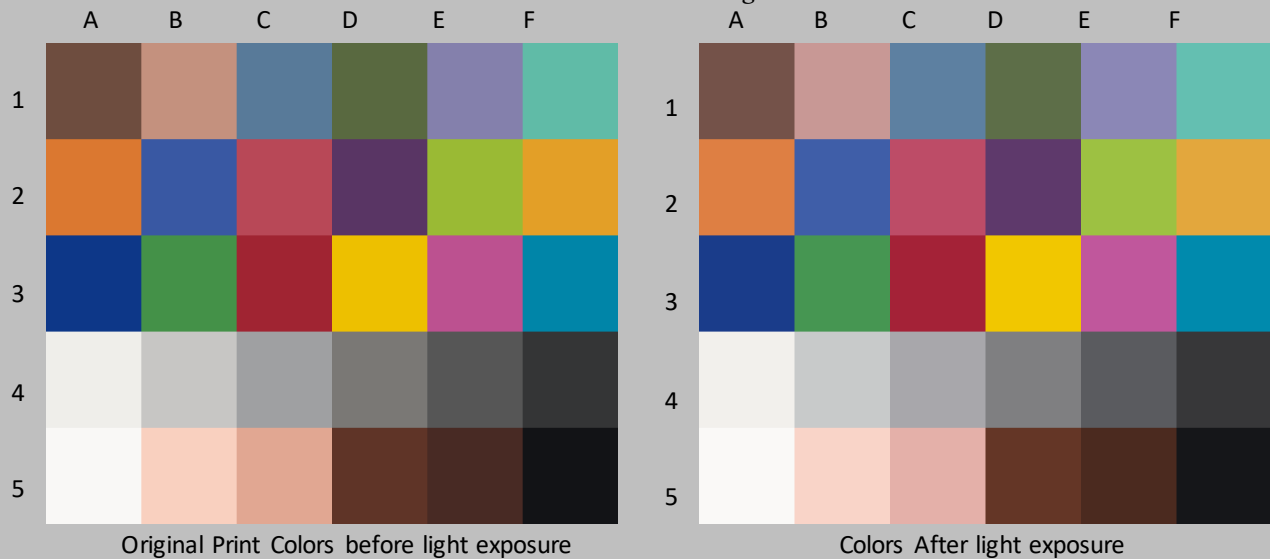


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	86.7	3.7	36.3	38.4	13.5	13.9	13.5	10.5
B1	Light Skin	65.3	9.7	64.6	67.5	17.6	17.5	18.1	8.9
C1	Blue sky	99.9	2.4	49.6	51.9	-6.3	-6.3	-21.2	-21.7
D1	Foliage	93.4	2.9	42.5	44.5	-11.7	-11.9	21.1	19.0
E1	blue flower	98.0	2.9	55.1	57.9	8.6	8.6	-22.9	-23.9
F1	bluish green	92.3	3.4	69.9	71.4	-32.1	-31.2	1.1	-1.8
A1	orange	90.5	7.0	61.3	63.3	35.7	33.8	54.9	48.5
B2	purplish blue	96.5	3.1	38.0	40.3	8.1	6.5	-45.4	-44.0
C2	moderate red	86.7	7.3	46.8	48.5	47.3	48.3	15.8	8.8
D2	purple	93.5	3.2	28.4	30.4	22.6	23.8	-20.8	-23.0
E2	yellow green	94.7	4.5	71.5	73.6	-24.7	-25.6	60.3	56.5
F2	orange yellow	91.5	6.8	70.9	73.1	18.9	16.3	67.3	61.4
A3	blue	97.1	2.7	24.7	26.5	13.3	11.6	-49.6	-48.5
B3	green	94.3	3.6	54.1	55.7	-37.0	-37.1	31.3	28.1
C3	red	96.2	2.8	36.5	37.4	51.0	52.6	25.2	23.1
D3	yellow	96.8	3.9	80.1	81.9	6.3	4.0	91.2	93.7
E3	magenta	93.0	4.5	50.5	52.5	49.0	49.4	-13.0	-17.0
F3	cyan	100.0	1.9	49.5	51.3	-29.9	-29.6	-30.1	-30.2
A4	white	100.0	0.7	94.3	94.9	0.5	0.1	1.8	1.5
B4	neutral 8	91.2	1.9	79.9	81.3	-0.2	-1.0	0.6	-0.5
C4	neutral 6.5	95.2	2.9	66.0	68.7	0.4	0.5	-0.6	-1.6
D4	neutral 5	68.3	4.3	50.8	53.2	0.1	0.2	2.0	-1.5
E4	neutral 3.5	80.8	3.3	36.4	38.6	0.0	0.3	0.1	-2.2
F4	black	96.9	1.7	21.8	23.3	-0.1	0.4	-0.6	-1.2
A5	paper white	100.0	0.6	97.5	98.0	0.5	0.4	1.4	1.1
B5	Skin highlight L*=88	84.0	3.8	86.8	88.0	13.1	12.4	14.1	10.6
C5	Skin highlight L* =75	69.6	9.6	73.7	76.7	20.0	18.6	20.4	11.3
D5	Skin shadow L*=28	94.7	2.2	27.2	28.4	18.7	19.8	17.1	18.6
E5	Skin shadow L*=13	79.5	4.0	20.7	21.0	13.7	15.3	10.2	13.8
F5	Maximum Black	99.8	1.6	5.7	7.3	-0.2	0.0	-2.1	-1.6
Summary Results		I* Color	I* tone	ΔE	120 Megalux hours				
Average Score for all patches		90.9	93.2	3.8					
Worst 10% (3 lowest scoring patches)		67.7	88.2	8.9					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

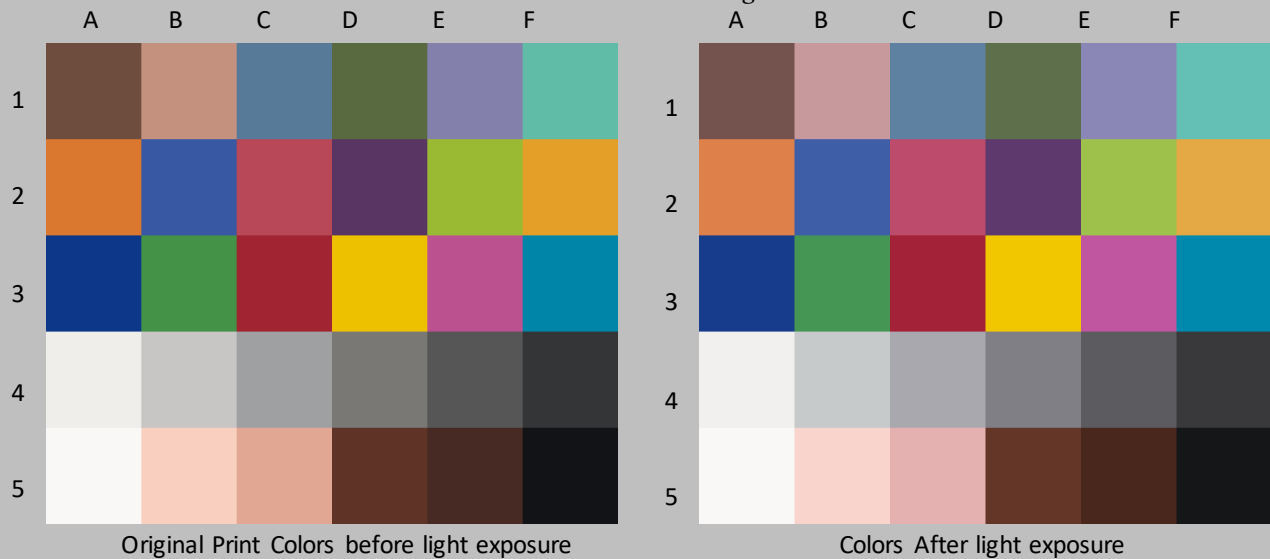


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	77.5	5.3	36.3	38.5	13.5	14.1	13.5	8.8
B1	Light Skin	49.4	13.7	64.6	67.9	17.6	18.2	18.1	4.9
C1	Blue sky	97.0	2.7	49.6	52.1	-6.3	-6.1	-21.2	-22.3
D1	Foliage	88.7	3.8	42.5	44.5	-11.7	-12.0	21.1	17.9
E1	blue flower	94.3	3.5	55.1	58.1	8.6	9.0	-22.9	-24.7
F1	bluish green	88.9	4.4	69.9	71.6	-32.1	-31.0	1.1	-2.9
A1	orange	84.6	10.8	61.3	63.4	35.7	33.8	54.9	44.6
B2	purplish blue	96.7	3.1	38.0	40.4	8.1	6.6	-45.4	-44.1
C2	moderate red	80.3	10.5	46.8	48.6	47.3	48.7	15.8	5.6
D2	purple	89.3	4.2	28.4	30.3	22.6	24.3	-20.8	-24.2
E2	yellow green	91.2	6.7	71.5	73.9	-24.7	-25.8	60.3	54.2
F2	orange yellow	86.7	10.1	70.9	73.3	18.9	16.0	67.3	57.9
A3	blue	97.6	2.5	24.7	26.5	13.3	11.7	-49.6	-48.9
B3	green	91.5	4.9	54.1	55.7	-37.0	-37.2	31.3	26.7
C3	red	94.2	3.9	36.5	37.2	51.0	52.9	25.2	21.9
D3	yellow	96.5	4.2	80.1	82.1	6.3	3.6	91.2	93.6
E3	magenta	89.7	6.1	50.5	52.5	49.0	49.8	-13.0	-18.7
F3	cyan	99.7	2.0	49.5	51.4	-29.9	-29.4	-30.1	-30.4
A4	white	98.7	0.8	94.3	94.8	0.5	0.1	1.8	1.3
B4	neutral 8	87.2	2.1	79.9	81.2	-0.2	-1.0	0.6	-0.9
C4	neutral 6.5	84.6	3.5	66.0	68.9	0.4	0.6	-0.6	-2.6
D4	neutral 5	50.5	5.8	50.8	53.3	0.1	0.6	2.0	-3.1
E4	neutral 3.5	67.7	4.2	36.4	38.6	0.0	0.6	0.1	-3.4
F4	black	89.4	2.2	21.8	23.4	-0.1	0.6	-0.6	-1.9
A5	paper white	100.0	0.5	97.5	97.8	0.5	0.3	1.4	1.0
B5	Skin highlight L*=88	77.8	4.9	86.8	87.8	13.1	12.5	14.1	9.4
C5	Skin highlight L*=75	57.9	12.9	73.7	76.8	20.0	18.9	20.4	7.9
D5	Skin shadow L*=28	96.0	1.9	27.2	28.2	18.7	19.9	17.1	18.1
E5	Skin shadow L*=13	76.3	4.5	20.7	20.6	13.7	15.7	10.2	14.3
F5	Maximum Black	99.0	1.6	5.7	7.2	-0.2	-0.1	-2.1	-1.5
Summary Results		I* Color	I* tone	ΔE	140 Megalux hours				
Average Score for all patches		86.0	92.3	4.9					
Worst 10% (3 lowest scoring patches)		52.6	86.8	12.4					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

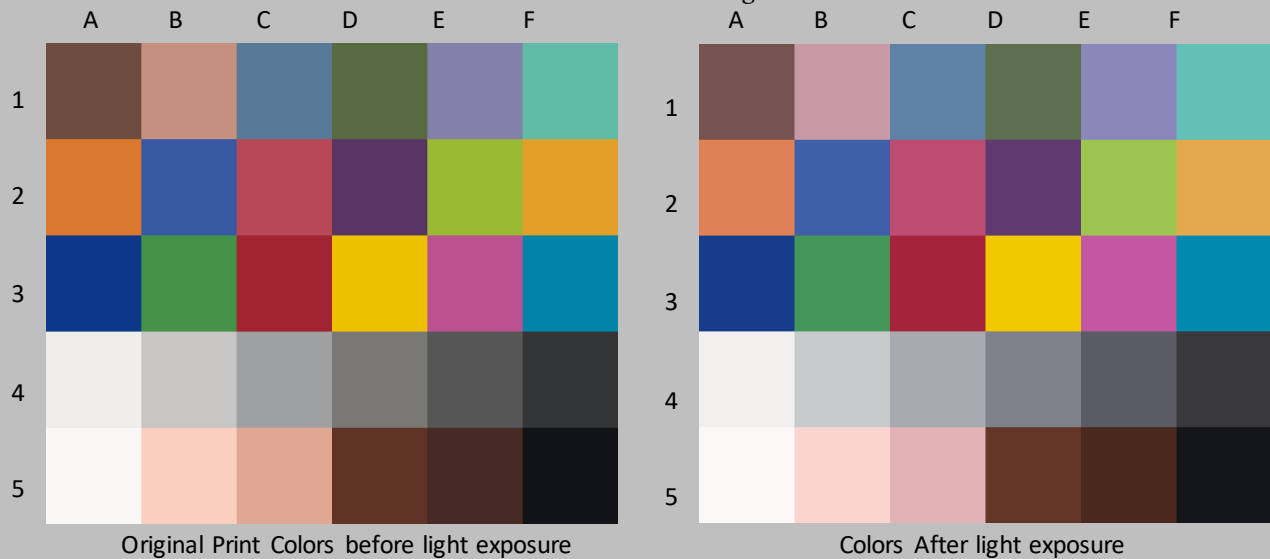


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	66.7	7.3	36.3	38.7	13.5	14.5	13.5	6.7
B1	Light Skin	33.9	17.6	64.6	68.4	17.6	18.9	18.1	1.0
C1	Blue sky	94.2	3.3	49.6	52.4	-6.3	-5.9	-21.2	-22.9
D1	Foliage	82.2	5.3	42.5	44.7	-11.7	-11.8	21.1	16.3
E1	blue flower	90.9	4.3	55.1	58.4	8.6	9.3	-22.9	-25.5
F1	bluish green	84.8	5.7	69.9	71.9	-32.1	-30.6	1.1	-4.1
A1	orange	77.7	15.3	61.3	63.8	35.7	33.8	54.9	40.0
B2	purplish blue	97.0	3.2	38.0	40.6	8.1	6.6	-45.4	-44.2
C2	moderate red	73.8	13.7	46.8	48.9	47.3	49.3	15.8	2.4
D2	purple	85.0	5.6	28.4	30.7	22.6	24.8	-20.8	-25.4
E2	yellow green	87.2	9.3	71.5	74.5	-24.7	-26.0	60.3	51.6
F2	orange yellow	81.2	14.0	70.9	73.9	18.9	15.9	67.3	53.9
A3	blue	97.7	2.6	24.7	26.8	13.3	11.8	-49.6	-48.9
B3	green	88.4	6.4	54.1	56.0	-37.0	-37.1	31.3	25.2
C3	red	91.8	5.3	36.5	37.5	51.0	53.3	25.2	20.6
D3	yellow	96.3	4.6	80.1	82.5	6.3	3.1	91.2	93.4
E3	magenta	86.5	7.7	50.5	52.8	49.0	50.3	-13.0	-20.2
F3	cyan	98.6	2.4	49.5	51.7	-29.9	-29.2	-30.1	-30.9
A4	white	96.7	1.0	94.3	95.0	0.5	0.1	1.8	1.1
B4	neutral 8	83.0	2.6	79.9	81.4	-0.2	-1.0	0.6	-1.4
C4	neutral 6.5	72.8	4.5	66.0	69.2	0.4	0.8	-0.6	-3.7
D4	neutral 5	30.6	7.7	50.8	53.6	0.1	1.0	2.0	-5.0
E4	neutral 3.5	54.2	5.5	36.4	39.0	0.0	0.8	0.1	-4.7
F4	black	83.6	2.7	21.8	23.6	-0.1	0.7	-0.6	-2.5
A5	paper white	100.0	0.6	97.5	98.0	0.5	0.3	1.4	1.0
B5	Skin highlight L*=88	71.0	6.2	86.8	88.1	13.1	12.5	14.1	8.1
C5	Skin highlight L*=75	46.5	16.1	73.7	77.2	20.0	19.3	20.4	4.6
D5	Skin shadow L*=28	96.2	1.9	27.2	28.4	18.7	20.1	17.1	17.6
E5	Skin shadow L*=13	74.3	4.9	20.7	20.6	13.7	15.9	10.2	14.5
F5	Maximum Black	99.9	1.8	5.7	7.4	-0.2	-0.1	-2.1	-1.6
Summary Results		I* Color	I* tone	ΔE	160 Megalux hours				
Average Score for all patches		80.8	91.6	6.3					
Worst 10% (3 lowest scoring patches)		37.0	85.5	16.3					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

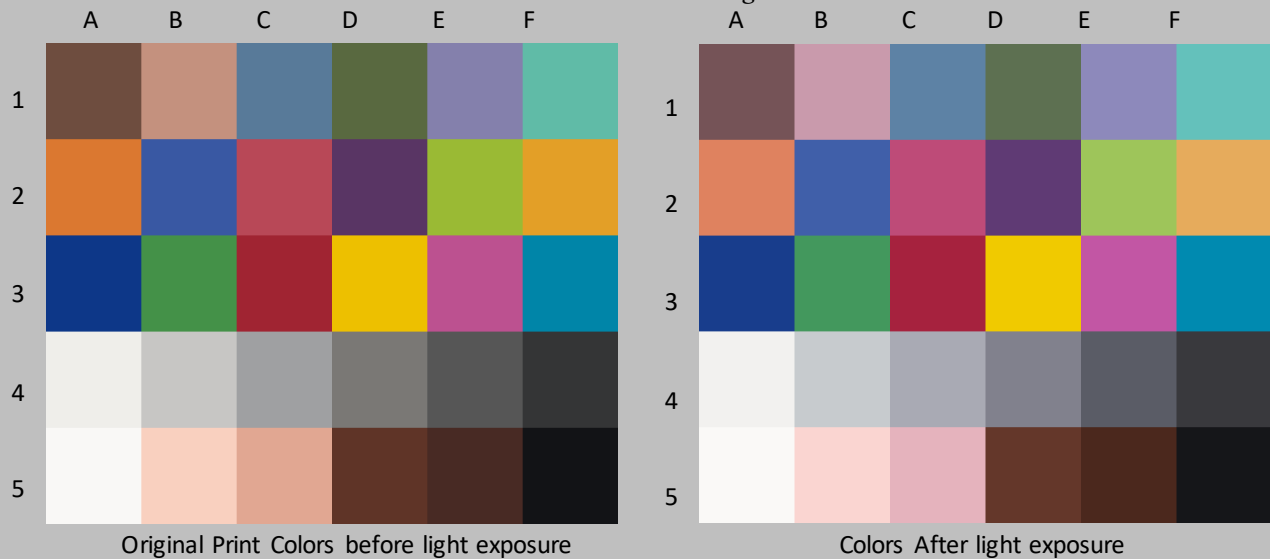

Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	54.2	9.6	36.3	39.0	13.5	14.8	13.5	4.4
B1	Light Skin	20.2	21.1	64.6	68.8	17.6	19.5	18.1	-2.4
C1	Blue sky	91.8	3.8	49.6	52.6	-6.3	-5.6	-21.2	-23.4
D1	Foliage	74.9	7.0	42.5	45.1	-11.7	-11.7	21.1	14.6
E1	blue flower	88.9	4.9	55.1	58.8	8.6	9.6	-22.9	-25.9
F1	bluish green	80.1	7.2	69.9	72.1	-32.1	-30.3	1.1	-5.6
A1	orange	69.5	20.7	61.3	64.2	35.7	34.0	54.9	34.5
B2	purplish blue	97.1	3.4	38.0	40.8	8.1	6.6	-45.4	-44.3
C2	moderate red	67.0	17.1	46.8	49.2	47.3	50.0	15.8	-0.9
D2	purple	81.0	6.8	28.4	31.0	22.6	25.3	-20.8	-26.5
E2	yellow green	81.2	13.2	71.5	75.0	-24.7	-26.2	60.3	47.6
F2	orange yellow	73.6	19.3	70.9	74.4	18.9	15.7	67.3	48.6
A3	blue	98.1	2.7	24.7	27.0	13.3	11.9	-49.6	-49.1
B3	green	84.3	8.4	54.1	56.4	-37.0	-37.1	31.3	23.2
C3	red	89.2	6.7	36.5	37.7	51.0	53.6	25.2	19.1
D3	yellow	96.0	5.0	80.1	82.9	6.3	2.5	91.2	92.7
E3	magenta	84.4	8.8	50.5	53.1	49.0	50.6	-13.0	-21.3
F3	cyan	97.3	2.9	49.5	51.9	-29.9	-29.0	-30.1	-31.4
A4	white	93.6	1.4	94.3	95.2	0.5	0.0	1.8	0.8
B4	neutral 8	78.4	3.0	79.9	81.5	-0.2	-1.0	0.6	-1.8
C4	neutral 6.5	61.5	5.6	66.0	69.7	0.4	0.9	-0.6	-4.8
D4	neutral 5	10.7	9.6	50.8	54.0	0.1	1.5	2.0	-6.8
E4	neutral 3.5	39.7	6.8	36.4	39.2	0.0	1.2	0.1	-6.0
F4	black	76.7	3.4	21.8	23.8	-0.1	0.9	-0.6	-3.1
A5	paper white	99.9	0.8	97.5	98.2	0.5	0.1	1.4	1.0
B5	Skin highlight L*=88	64.4	7.5	86.8	88.4	13.1	12.6	14.1	6.8
C5	Skin highlight L* =75	37.9	18.6	73.7	77.5	20.0	19.6	20.4	2.2
D5	Skin shadow L*=28	95.2	2.2	27.2	28.5	18.7	20.4	17.1	16.8
E5	Skin shadow L*=13	73.8	5.0	20.7	21.0	13.7	16.0	10.2	14.6
F5	Maximum Black	99.2	1.9	5.7	7.6	-0.2	0.1	-2.1	-1.6
Summary Results		I* Color	I* tone	ΔE	180 Megalux hours				
Average Score for all patches		75.3	91.0	7.8					
Worst 10% (3 lowest scoring patches)		22.9	84.2	20.3					

Epson SureColor P600, Epson OEM Ultrachrome HD, Hahnemuhle Photo Rag Pearl 320gsm, no additional coating

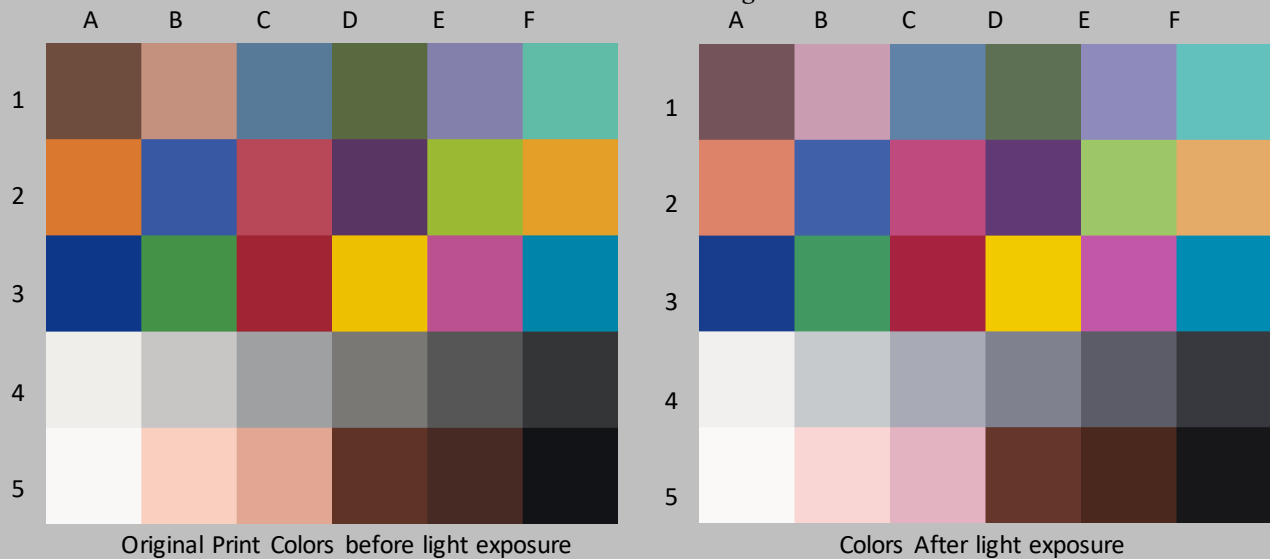


Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin	42.7	11.8	36.3	39.2	13.5	15.2	13.5	2.2
B1	Light Skin	9.9	23.7	64.6	69.1	17.6	20.2	18.1	-5.0
C1	Blue sky	90.4	4.2	49.6	52.9	-6.3	-5.4	-21.2	-23.6
D1	Foliage	67.1	8.9	42.5	45.2	-11.7	-11.4	21.1	12.7
E1	blue flower	88.2	5.2	55.1	59.1	8.6	9.7	-22.9	-26.1
F1	bluish green	74.8	8.9	69.9	72.3	-32.1	-29.6	1.1	-7.2
A1	orange	60.9	26.3	61.3	64.3	35.7	34.3	54.9	28.8
B2	purplish blue	96.9	3.6	38.0	41.0	8.1	6.7	-45.4	-44.0
C2	moderate red	61.4	19.9	46.8	49.3	47.3	50.5	15.8	-3.7
D2	purple	78.0	7.8	28.4	31.2	22.6	25.8	-20.8	-27.4
E2	yellow green	74.6	17.4	71.5	75.3	-24.7	-25.9	60.3	43.4
F2	orange yellow	66.1	24.5	70.9	74.7	18.9	15.9	67.3	43.3
A3	blue	98.2	2.8	24.7	27.1	13.3	12.0	-49.6	-49.1
B3	green	79.2	10.8	54.1	56.5	-37.0	-36.8	31.3	20.7
C3	red	86.6	8.2	36.5	37.8	51.0	53.9	25.2	17.6
D3	yellow	96.0	5.2	80.1	83.2	6.3	2.2	91.2	91.5
E3	magenta	83.6	9.3	50.5	53.3	49.0	50.8	-13.0	-21.7
F3	cyan	96.6	3.2	49.5	52.0	-29.9	-28.6	-30.1	-31.6
A4	white	91.8	1.5	94.3	95.1	0.5	0.1	1.8	0.6
B4	neutral 8	75.4	3.2	79.9	81.4	-0.2	-0.9	0.6	-2.2
C4	neutral 6.5	53.0	6.3	66.0	69.8	0.4	1.1	-0.6	-5.6
D4	neutral 5	(6.0)	11.1	50.8	54.2	0.1	2.1	2.0	-8.3
E4	neutral 3.5	25.7	8.1	36.4	39.3	0.0	1.6	0.1	-7.3
F4	black	69.6	4.0	21.8	23.9	-0.1	1.2	-0.6	-3.7
A5	paper white	100.0	0.6	97.5	98.0	0.5	0.2	1.4	1.1
B5	Skin highlight L*=88	57.2	8.9	86.8	88.4	13.1	12.7	14.1	5.4
C5	Skin highlight L*=75	31.1	20.5	73.7	77.5	20.0	19.8	20.4	0.2
D5	Skin shadow L*=28	93.0	2.6	27.2	28.5	18.7	20.6	17.1	15.9
E5	Skin shadow L*=13	72.6	5.2	20.7	20.9	13.7	16.3	10.2	14.7
F5	Maximum Black	97.0	2.2	5.7	7.8	-0.2	0.1	-2.1	-1.4
Summary Results		I* Color	I* tone	200 Megalux hours					
Average Score for all patches		70.4	90.2						
Worst 10% (3 lowest scoring patches)		9.8	83.0						

This test had been completed - no more updates



Original Print Colors before light exposure

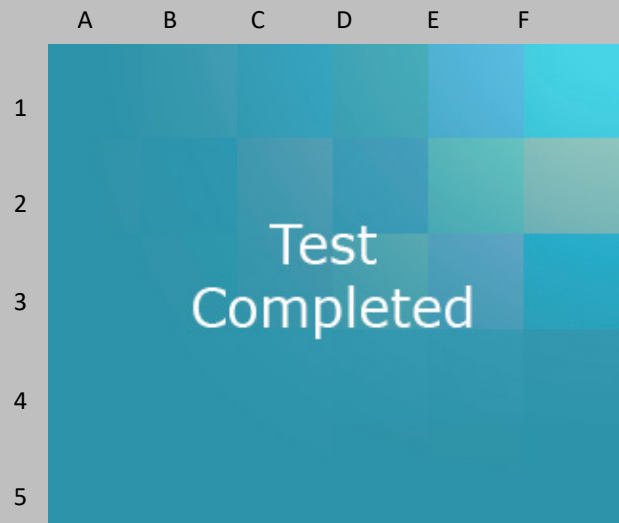

Colors After light exposure

Patch #	Description	I* Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	Dark Skin			36.3		13.5		13.5	
B1	Light Skin			64.6		17.6		18.1	
C1	Blue sky			49.6		-6.3		-21.2	
D1	Foliage			42.5		-11.7		21.1	
E1	blue flower			55.1		8.6		-22.9	
F1	bluish green			69.9		-32.1		1.1	
A1	orange			61.3		35.7		54.9	
B2	purplish blue			38.0		8.1		-45.4	
C2	moderate red			46.8		47.3		15.8	
D2	purple			28.4		22.6		-20.8	
E2	yellow green			71.5		-24.7		60.3	
F2	orange yellow			70.9		18.9		67.3	
A3	blue			24.7		13.3		-49.6	
B3	green			54.1		-37.0		31.3	
C3	red			36.5		51.0		25.2	
D3	yellow			80.1		6.3		91.2	
E3	magenta			50.5		49.0		-13.0	
F3	cyan			49.5		-29.9		-30.1	
A4	white			94.3		0.5		1.8	
B4	neutral 8			79.9		-0.2		0.6	
C4	neutral 6.5			66.0		0.4		-0.6	
D4	neutral 5			50.8		0.1		2.0	
E4	neutral 3.5			36.4		0.0		0.1	
F4	black			21.8		-0.1		-0.6	
A5	paper white			97.5		0.5		1.4	
B5	Skin highlight L*=88			86.8		13.1		14.1	
C5	Skin highlight L* =75			73.7		20.0		20.4	
D5	Skin shadow L*=28			27.2		18.7		17.1	
E5	Skin shadow L*=13			20.7		13.7		10.2	
F5	Maximum Black			5.7		-0.2		-2.1	
Summary Results		I* Color	I* tone	ΔE	> 200 Mlux hours				
Average Score for all patches									
Worst 10% (3 lowest scoring patches)									