


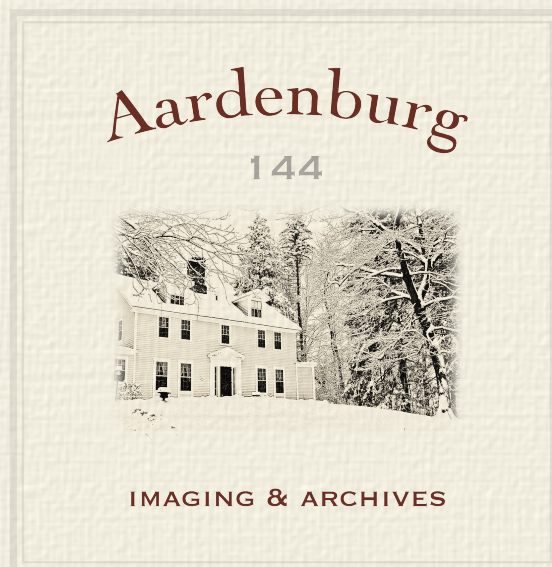

Accelerated Light Fading Test Results

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

Sample # AaI_20071218_SN005

260 Megalux-hours completed

Conservation Display Rating *	
Lower Exposure Limit (Megalux hours)	Upper Exposure limit (Megalux hours)
76	114


* Please read document **AaI_2009_0118_TA-01.pdf**, "An Overview of the AaI&A Conservation Display Ratings", located on the Documents page of the AaI&A website for an explanation of the conservation display ratings.

Document #: AaI_20071218_SN005Lf.pdf Rev: October 3, 2012

Test Print Prepared by: AaI&A Member, category: Professional

Copyright 2012. This report has been prepared for the exclusive use of members of Aardenburg Imaging & Archives. Members may share this information with other members, friends, colleagues, and individual clients. It may also be distributed to groups for educational purposes (classes, lectures, educational seminars. etc). However, all contents including but not limited to Conservation Display Ratings may not be posted to web sites and may not be reproduced or distributed for corporate research, marketing, or other promotional purposes without written permission from Aardenburg Imaging & Archives.

For more information please contact: info@aardenburg-imaging.com



About this Report

This report contains light fastness information about a single test print produced by a specific digital printing system. “System” refers to all hardware, software, and materials used to make the finished print. The hardware, software, material components, and printmaker’s skills contribute to the final image quality and image permanence. The tested sample is made with current or recently discontinued stocks of commercially available products unless otherwise stated. Each sample has been prepared by Aardenburg Imaging & Archives or one of its members in accordance with customary print making practices unless otherwise noted. The sample may also contain additional finishing materials such as overcoats and laminates which are also noted when used. Finally, the sample has been tested under standardized conditions that are defined on the Sample Description page (see page 2). AaI&A makes every effort to ensure but cannot guarantee that the samples are properly identified and documented and that test results are accurate. For this reason, AaI&A also strives to test independently produced sample replicates in order to increase sampling confidence and to provide information on process variability. Please compare the results in this report to replicate test samples when the data become available.

Understanding the Test Results



AaI_StandardColorSet(v2)forSRGB.tif


The magnitude and visual appearance of fading depends not only on the chosen printing system but the chosen image as well. In other words, different images are comprised of different colors, and the fading relationships between those colors dictate how the image will look as it fades. The sample print in this test report was made by reproducing the digital image shown on the left. It contains 30 standard colors. 24 of the colors are colorimetrically matched to the Macbeth ColorChecker™ chart viewed under D50 illumination. The remaining six colors supplement the ColorChecker™ array with four additional skin tone colors, one patch for paper white, and another for maximum black. The additional colors also round out the distribution of L* lightness values in the test target.

Information about the fading characteristics of the product is provided in three ways:

1) ***You can visually assess the fading.*** The target images reproduced in this report are digitally reconstructed from the spectrally measured color data rather than scanning or otherwise reproducing the physical print by conventional techniques. This method ensures a colorimetrically accurate representation of the print appearance as the print fades. A calibrated monitor is recommended to experience the best possible reproduction of the test sample appearance. The side-by-side presentation of the target images simulates looking at the light-exposed print along side a perfect duplicate of the unexposed original print. The “Before/After” Layer mode takes advantage of Adobe Reader Layer technology. Toggle the “Before/After” layer on and off using the layers feature of Adobe Reader to directly switch between the light exposed print colors and the initial print colors for the image located on the right side of each page. Also, use Adobe Reader’s full screen mode to cycle through the pages and “animate” the fading.

2) ***I* Color and tonal accuracy scores are reported.*** This report includes I* metric scores that compare the color and tonal relationships of the light exposed samples to the color and tonal relationships existing in the original print prior to light exposure. Perfect I* scores of 100% can be approached when no significant fading occurs. Average scores above 90% generally indicate excellent retention of original quality, 80% good, 70% fair, etc., but your conclusions may vary depending on your image quality requirements. ***I* color*** rates the retained color accuracy (hue and chroma) while ***I* tone*** rates the retained tonal accuracy (lightness and contrast). The score is on a percentile scale where 100% is a perfect match between the comparison image (e.g., “after” light exposure) and the reference image (e.g., “before” any light exposure). 0% ***I* color*** means no color accuracy is left. 0% ***I* tone*** means essentially no tonality remains and all image information content is lost. Negative I* values have significance as well and contribute to the average I* score when they occur. Negative I* color values mean false color has occurred, for example, when a skin tone turns green or a neutral gray becomes distinctly colorful. Negative I* tone scores mean visual contrast between colors has become inverted (i.e., like the tonal relationships in a photographic film negative). Serious image quality problems must arise before false colors and/or tones appear. For more information on the I* metric, please refer to the AaI&A web site.


3) ***Color changes are also reported using the classic color difference model, ΔE .*** Note that ΔE values lose perceptual scaling significance when they become large (e.g., > 15). Also, the ΔE equation does not unambiguously measure changes in image contrast. This limitation is generally not a problem for paints and textiles, but can be a serious oversight when evaluating photographic images. It was a major reason behind the development of the I* metric.



Sample Description

Printer: Epson 4800
Ink: Epson OEM (Ultrachrome K3)
Paper: Crane Museo Silver Rag 300gsm

Sample #: AaI_20071218_SN005
Test Print Submission Category: Professional

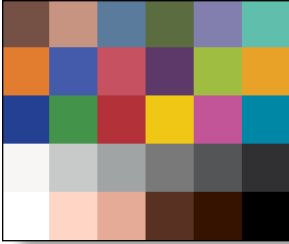

AaI_StandardColorSet(v2)forSRGB.tif

Test Image: AaI_StandardColorSet(v2)forSRGB.tif
RIP/Driver settings: 1440 dpi, high speed off, finest details 'ON', No color adjustment (NCA)
Media Setting: "Premium Luster Photo"
Printed: December 18, 2007
Original print colors measured on: January 08, 2008
Test started on: January 10, 2008

Profile: MUSEO_SILVERRAG_EP4800.icc
Profile type: generic
Profile Creation Software: n.a.

Rendering Intent: Perceptual with BPC

Paper White Color (UV–included versus UV–excluded) and Maximum Printed Black						
Optical Brighteners present? no	L*		a*		b*	
	UV inc	UV exc	UV inc	UV exc	UV inc	UV exc
Maximum Paper White (no colorants printed)	97.2	97.3	−0.2	−0.2	1.8	2.0
(1) ΔL*, Δa*, Δb* respectively	0.1		0.0		0.2	
(1) Calculated differences, especially for Δb*, indicate the role and magnitude of fluorescence on original paper color						
Maximum Printed black (UV included)	L* = 10.3		a* = 1.4		b* = −0.2	

Light Source: Phillips Colortone F40T12/C50
Filter/Glazing: Sample framed under Glass*
Light Exposure Cycle: 8 hours on, 4 hours off, twice per 24 hours
Average Illuminance during "on" cycle: 11,725 Lux
Average Temperature: 23.2°C over full test duration, 24.6°C during light exposure
Average Relative humidity: 58.5% RH full test period, 59.1% RH during light exposure
CIELAB measurements: D50 2° observer, Xrite Gretag/Macbeth Spectrolino/Spectroscan

Replicates/Compare to:

No Replicates are available at this time.

Notes/Comments:

* The Phillips Colortone F40T12/C50 fluorescent light source and ordinary glass picture frame glazing yields UVA content and overall spectral power similar to natural 5000°K daylight entering a window and then striking a print that has been framed by **standard acrylic glazing** rather than ordinary glass. Other light sources and/or different glazing options may yield greater or lesser fade rates (generally, a 2-5x increase in fade rate for direct sunlight compared to UV-excluded sources at the same Lux level). The spectral quality of the light can also affect individual colors differently.

Table to Convert Megalux-hours of Light Exposure to estimated “Years on Display”												
Indoor Light Levels for Print Display		Multiply Mlux-hrs by	Megalux-hours in test									
Light Exposure	Description		10	20	30	40	50	60	70	80	90	100
≤ 10 Lux 24 hours per day	Interior rooms, storage areas, or hallways without windows, illuminated sparingly by artificial lighting	11.42	114	228	342	457	571	685	799	913	1027	1142
50 Lux 12 hours per day	“Museum Standard” display condition	4.57	46	91	137	183	228	274	325	365	411	457
120 Lux 12 hours per day “Kodak Display Years” (1)	Average home illumination level for photos is ~ 60 lux. 90% of all displayed photos do not exceed 120 lux (1).	1.90	19	38	57	76	95	114	133	152	171	190
228 Lux 12 hours per day	Relatively bright home or office. Note the simple 1:1 relationship between “years on display” and Mlux-hr values at this condition.	1.00	10	20	30	40	50	60	70	80	90	100
450 Lux 12 hours per day “WIR Display Years” (2) Also equals 500 lux for 11.8 hours per day	A bright home or commercial office building illumination level is 200-500 lux. Also, good illumination for color critical viewing and color matching tasks begins at about 500 lux.	0.51	5	10	15	20	25	30	35	41	46	51
2000 Lux 12 hours per day	Commercial Gallery. Also, critical color evaluation standards call for 2000 lux and a D50 illumination source.	0.114	1.1	2.3	3.4	4.6	5.7	6.8	8.0	9.1	10.3	11.4
5000 Lux 12 hours per day	E.g., Sunlight through a window striking print at an angle.	0.046	0.5	0.9	1.4	1.8	2.3	2.7	3.2	3.7	4.1	4.6
10,000 Lux 12 hours per day	South-facing window in U.S.A. , e.g., storefront display with photos directly facing window.	0.023	0.2	0.5	0.7	0.9	1.1	1.4	1.6	1.8	2.1	2.3
Light levels commonly encountered in the real world fluctuate widely throughout indoor print display environments and produce large variations in how long it takes for artwork to acquire light-induced damage. Use this table as a guide to estimate how many “years on display” (denoted in red text) it takes to accumulate the light exposure test dosage. Review the test results to decide which Megalux-hour dose has caused fading to your level of concern (e.g., just noticeable, easily noticeable, objectionable, etc.). Then choose the print display description that best represents how your print is likely to be displayed. You may want to obtain a lux meter and make some measurements in your own display environment! Note that as the years of display time increase, light-induced fading can be eclipsed by other serious aging mechanisms such as fading and/or staining caused by heat, humidity, and air pollutants. Mould damage can also occur at high humidity. Even when colorants remain water fast, direct contact with liquids may result in physical deformation and staining of the substrate. Also, temperature and especially humidity cycling can cause physical cracks and/or flaking, etc. Handling damage such as scratching, abrasion, tears and creases, and catastrophic damage by smoke, fire, flood, etc., also degrade print quality over time. Thus, as illumination levels are reduced other forms of degradation take on greater proportion of risk and may appear in shorter time intervals. (1) Eastman Kodak has cited this exposure condition and 90% confidence limit as a rationale for estimating print fading times of traditional color photo materials in typical home display environments. For recent light fading claims regarding its line of pigment-based inkjet printers, Kodak has adopted the higher level of 450lux/12 hours per day which is also used by Wilhelm Imaging Research, Inc. (See below). (2) Wilhelm Imaging Research (WIR) has standardized its light fastness ratings on 450 lux for 12 hours per day in order to estimate the years on display necessary to reach “noticeable” fading. This average light exposure condition, an assumed 75°F/60%RH temperature and humidity level, and WIR’s visually weighted densitometric endpoint criteria set V3.0 has become a de facto industry standard for most predictive light fading estimates in the absence of a published International Standards Organization (ISO) test standard.												

100_{color}/100_{tone}



Original Print Colors
(measured before light exposure)



Colors at Zero Megalux-hours of Light Exposure
(same as original print colors)

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

Original Print Colors as Measured and at Start of Test

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	100	0.0	36.0		16.3		11.4	
B1	light Skin	100	0.0	63.6		21.3		15.9	
C1	blue sky	100	0.0	47.2		-4.0		-23.9	
D1	foliage	100	0.0	42.7		-13.0		20.6	
E1	blue flower	100	0.0	51.2		12.6		-26.6	
F1	bluish green	100	0.0	66.3		-38.9		-1.4	
A2	orange	100	0.0	60.7		40.4		57.1	
B2	purplish blue	100	0.0	36.1		13.1		-49.7	
C2	moderate red	100	0.0	51.2		48.8		20.7	
D2	purple	100	0.0	29.8		24.7		-20.8	
E2	yellow green	100	0.0	72.7		-23.7		57.0	
F2	orange yellow	100	0.0	69.3		19.6		71.9	
A3	blue	100	0.0	26.6		15.1		-54.7	
B3	green	100	0.0	54.7		-39.9		33.6	
C3	red	100	0.0	42.8		52.3		29.7	
D3	yellow	100	0.0	78.7		1.5		86.8	
E3	magenta	100	0.0	49.6		52.8		-1.4	
F3	cyan	100	0.0	48.1		-28.0		-32.0	
A4	white	100	0.0	94.9		0.4		2.4	
B4	neutral 8	100	0.0	79.1		0.1		0.0	
C4	neutral 6.5	100	0.0	64.9		-0.8		-0.6	
D4	neutral 5	100	0.0	48.7		1.2		-0.6	
E4	neutral 3.5	100	0.0	34.0		0.5		-1.8	
F4	black	100	0.0	20.5		1.3		-2.1	
A5	paper white	100	0.0	97.2		0.1		1.8	
B5	skin highlight L*=89	100	0.0	86.1		14.2		13.0	
C5	skin highlight L*=75	100	0.0	73.1		23.4		18.4	
D5	skin shadow L*=25	100	0.0	26.6		17.0		13.8	
E5	skin shadow L*=11	100	0.0	17.1		11.5		9.8	
F5	Max Black	100	0.0	10.3		1.4		-0.2	
Summary Results		I*Color	I*tone	ΔE	 AARDENBURG IMAGING & ARCHIVES				
Average Score for all patches		100	100	0.0					
Average Score for the Worst 10% (3 lowest scoring patches)		100	100	0.0					

99.4_{color} / 98.2_{tone}



Original Print Colors
(measured before light exposure)




Colors after 10 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

10 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	100.0	1.0	36.0	36.9	16.3	16.2	11.4	11.1
B1	light Skin	99.1	0.9	63.6	64.1	21.3	20.9	15.9	15.3
C1	blue sky	100.0	0.7	47.2	47.9	-4.0	-4.1	-23.9	-23.8
D1	foliage	100.0	0.8	42.7	43.5	-13.0	-13.3	20.6	20.3
E1	blue flower	100.0	0.8	51.2	51.9	12.6	12.4	-26.6	-26.6
F1	bluish green	98.8	1.2	66.3	67.0	-38.9	-38.6	-1.4	-2.3
A2	orange	99.0	1.3	60.7	61.3	40.4	39.7	57.1	56.1
B2	purplish blue	99.8	1.0	36.1	36.9	13.1	12.6	-49.7	-49.3
C2	moderate red	99.2	1.1	51.2	51.8	48.8	48.6	20.7	19.8
D2	purple	100.0	0.7	29.8	30.6	24.7	24.7	-20.8	-21.0
E2	yellow green	98.9	1.3	72.7	73.3	-23.7	-23.9	57.0	55.8
F2	orange yellow	99.4	1.1	69.3	69.8	19.6	18.8	71.9	71.3
A3	blue	99.6	1.0	26.6	27.3	15.1	14.5	-54.7	-54.5
B3	green	99.8	0.9	54.7	55.3	-39.9	-40.1	33.6	33.0
C3	red	99.9	0.6	42.8	43.1	52.3	52.4	29.7	29.1
D3	yellow	99.8	0.8	78.7	79.1	1.5	0.9	86.8	86.4
E3	magenta	100.0	0.6	49.6	50.1	52.8	52.7	-1.4	-1.7
F3	cyan	100.0	0.7	48.1	48.8	-28.0	-28.1	-32.0	-32.2
A4	white	97.9	0.7	94.9	95.2	0.4	0.3	2.4	1.7
B4	neutral 8	100.0	0.6	79.1	79.6	0.1	-0.1	0.0	-0.3
C4	neutral 6.5	100.0	0.6	64.9	65.5	-0.8	-1.0	-0.6	-0.8
D4	neutral 5	100.0	0.8	48.7	49.4	1.2	1.0	-0.6	-0.9
E4	neutral 3.5	100.0	0.9	34.0	34.9	0.5	0.3	-1.8	-2.1
F4	black	100.0	0.8	20.5	21.3	1.3	1.1	-2.1	-2.2
A5	paper white	96.4	0.9	97.2	97.4	0.1	0.2	1.8	1.0
B5	skin highlight L*=89	97.3	1.1	86.1	86.4	14.2	13.8	13.0	12.0
C5	skin highlight L*=75	98.3	1.2	73.1	73.7	23.4	22.9	18.4	17.5
D5	skin shadow L*=25	100.0	0.6	26.6	27.0	17.0	17.3	13.8	13.9
E5	skin shadow L*=11	100.0	0.6	17.1	17.7	11.5	11.6	9.8	10.0
F5	Max Black	100.0	0.4	10.3	10.7	1.4	1.4	-0.2	-0.2
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		99.4	98.2						
Average Score for the Worst 10% (3 lowest scoring patches)		97.2	97.1						

99.0_{color} / 97.6_{tone}

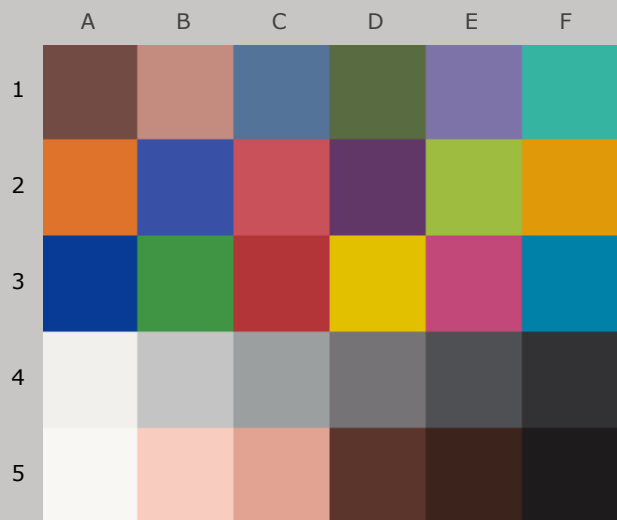

Original Print Colors
(measured before light exposure)



Colors after 20 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

20 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	100.0	1.3	36.0	37.2	16.3	16.3	11.4	10.9
B1	light Skin	98.0	1.3	63.6	64.4	21.3	20.9	15.9	15.0
C1	blue sky	100.0	1.0	47.2	48.2	-4.0	-4.1	-23.9	-23.8
D1	foliage	99.1	1.3	42.7	43.8	-13.0	-13.3	20.6	20.0
E1	blue flower	100.0	1.1	51.2	52.2	12.6	12.4	-26.6	-26.3
F1	bluish green	97.3	1.8	66.3	67.2	-38.9	-38.4	-1.4	-2.8
A2	orange	97.9	2.2	60.7	61.5	40.4	39.5	57.1	55.3
B2	purplish blue	98.7	1.6	36.1	37.2	13.1	12.3	-49.7	-48.8
C2	moderate red	98.7	1.4	51.2	51.9	48.8	48.7	20.7	19.6
D2	purple	100.0	1.0	29.8	30.9	24.7	24.6	-20.8	-20.8
E2	yellow green	97.6	2.1	72.7	73.5	-23.7	-23.9	57.0	55.0
F2	orange yellow	98.6	1.8	69.3	70.1	19.6	18.5	71.9	70.7
A3	blue	98.6	1.5	26.6	27.5	15.1	14.1	-54.7	-54.0
B3	green	98.5	1.5	54.7	55.6	-39.9	-40.0	33.6	32.4
C3	red	99.4	1.0	42.8	43.2	52.3	52.4	29.7	28.8
D3	yellow	99.3	1.3	78.7	79.3	1.5	0.6	86.8	86.0
E3	magenta	100.0	0.7	49.6	50.3	52.8	52.8	-1.4	-1.5
F3	cyan	100.0	0.9	48.1	49.0	-28.0	-28.2	-32.0	-32.1
A4	white	99.5	0.6	94.9	95.2	0.4	0.2	2.4	1.9
B4	neutral 8	100.0	0.7	79.1	79.8	0.1	-0.1	0.0	-0.2
C4	neutral 6.5	100.0	0.8	64.9	65.6	-0.8	-1.0	-0.6	-0.8
D4	neutral 5	100.0	1.0	48.7	49.7	1.2	1.1	-0.6	-1.0
E4	neutral 3.5	100.0	1.2	34.0	35.2	0.5	0.4	-1.8	-2.1
F4	black	100.0	1.0	20.5	21.4	1.3	1.2	-2.1	-2.3
A5	paper white	98.2	0.7	97.2	97.5	0.1	0.2	1.8	1.1
B5	skin highlight L*=89	94.8	1.6	86.1	86.5	14.2	13.7	13.0	11.5
C5	skin highlight L*=75	96.7	1.7	73.1	73.9	23.4	22.7	18.4	17.1
D5	skin shadow L*=25	100.0	0.8	26.6	27.2	17.0	17.3	13.8	13.8
E5	skin shadow L*=11	100.0	0.9	17.1	17.9	11.5	11.7	9.8	10.1
F5	Max Black	100.0	0.7	10.3	11.0	1.4	1.4	-0.2	-0.2
Summary Results		I*Color	I*tone	ΔE	 AARDENBURG IMAGING & ARCHIVES				
Average Score for all patches		99.0	97.6	1.2					
Average Score for the Worst 10% (3 lowest scoring patches)		96.3	96.1	2.0					

Page 7

98.4_{color} / 97.2_{tone}




Original Print Colors
(measured before light exposure)




Colors after 30 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

30 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	98.7	1.6	36.0	37.4	16.3	16.3	11.4	10.7
B1	light Skin	96.7	1.6	63.6	64.4	21.3	20.9	15.9	14.6
C1	blue sky	100.0	1.1	47.2	48.2	-4.0	-4.1	-23.9	-23.7
D1	foliage	97.6	1.6	42.7	43.9	-13.0	-13.3	20.6	19.6
E1	blue flower	99.6	1.3	51.2	52.3	12.6	12.6	-26.6	-26.0
F1	bluish green	95.8	2.3	66.3	67.2	-38.9	-38.2	-1.4	-3.4
A2	orange	97.0	2.7	60.7	61.5	40.4	39.3	57.1	54.7
B2	purplish blue	98.0	1.9	36.1	37.2	13.1	12.2	-49.7	-48.4
C2	moderate red	98.0	1.7	51.2	51.9	48.8	48.6	20.7	19.2
D2	purple	100.0	1.1	29.8	30.9	24.7	24.6	-20.8	-20.6
E2	yellow green	96.2	2.9	72.7	73.5	-23.7	-24.0	57.0	54.2
F2	orange yellow	97.7	2.4	69.3	70.1	19.6	18.3	71.9	70.1
A3	blue	97.9	1.9	26.6	27.5	15.1	13.8	-54.7	-53.7
B3	green	97.6	2.0	54.7	55.6	-39.9	-40.1	33.6	31.9
C3	red	98.8	1.3	42.8	43.2	52.3	52.4	29.7	28.4
D3	yellow	98.7	1.8	78.7	79.3	1.5	0.4	86.8	85.6
E3	magenta	100.0	0.8	49.6	50.3	52.8	52.6	-1.4	-1.5
F3	cyan	100.0	0.9	48.1	49.0	-28.0	-28.1	-32.0	-32.0
A4	white	99.1	0.6	94.9	95.0	0.4	0.2	2.4	1.9
B4	neutral 8	100.0	0.7	79.1	79.8	0.1	-0.2	0.0	-0.1
C4	neutral 6.5	100.0	0.8	64.9	65.7	-0.8	-0.9	-0.6	-0.8
D4	neutral 5	100.0	1.1	48.7	49.8	1.2	1.2	-0.6	-1.0
E4	neutral 3.5	100.0	1.3	34.0	35.3	0.5	0.5	-1.8	-2.2
F4	black	100.0	1.2	20.5	21.7	1.3	1.2	-2.1	-2.3
A5	paper white	98.8	0.6	97.2	97.3	0.1	0.2	1.8	1.2
B5	skin highlight L*=89	91.8	2.1	86.1	86.5	14.2	13.6	13.0	11.0
C5	skin highlight L*=75	94.5	2.3	73.1	74.0	23.4	22.5	18.4	16.4
D5	skin shadow L*=25	100.0	0.9	26.6	27.3	17.0	17.4	13.8	13.7
E5	skin shadow L*=11	100.0	1.1	17.1	18.1	11.5	11.7	9.8	10.1
F5	Max Black	100.0	1.0	10.3	11.3	1.4	1.4	-0.2	-0.2
Summary Results		I*Color	I*tone	ΔE	 AARDENBURG IMAGING & ARCHIVES				
Average Score for all patches		98.4	97.2	1.5					
Average Score for the Worst 10% (3 lowest scoring patches)		94.1	95.9	2.7					

97.9_{color} / 97.0_{tone}

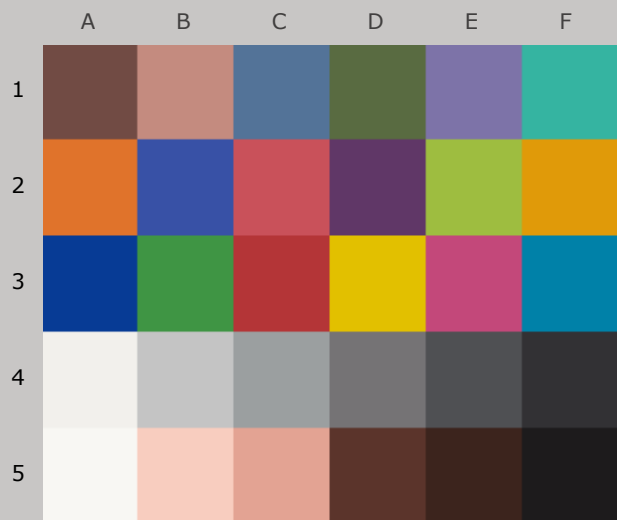

Original Print Colors
(measured before light exposure)




Colors after 40 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

40 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	97.7	1.7	36.0	37.4	16.3	16.3	11.4	10.5
B1	light Skin	96.0	1.8	63.6	64.4	21.3	21.0	15.9	14.4
C1	blue sky	100.0	1.1	47.2	48.3	-4.0	-4.1	-23.9	-23.6
D1	foliage	96.2	1.8	42.7	43.8	-13.0	-13.3	20.6	19.2
E1	blue flower	98.8	1.4	51.2	52.3	12.6	12.6	-26.6	-25.8
F1	bluish green	94.6	2.8	66.3	67.2	-38.9	-38.1	-1.4	-3.8
A2	orange	96.1	3.3	60.7	61.5	40.4	39.2	57.1	54.0
B2	purplish blue	97.0	2.4	36.1	37.3	13.1	11.9	-49.7	-48.0
C2	moderate red	97.3	2.1	51.2	51.9	48.8	48.5	20.7	18.8
D2	purple	100.0	1.2	29.8	31.0	24.7	24.5	-20.8	-20.5
E2	yellow green	95.2	3.5	72.7	73.6	-23.7	-24.0	57.0	53.6
F2	orange yellow	97.0	2.9	69.3	70.2	19.6	18.1	71.9	69.6
A3	blue	97.7	2.0	26.6	27.3	15.1	13.7	-54.7	-53.6
B3	green	96.8	2.3	54.7	55.6	-39.9	-40.1	33.6	31.5
C3	red	98.1	1.7	42.8	43.3	52.3	52.2	29.7	28.0
D3	yellow	98.2	2.2	78.7	79.3	1.5	0.3	86.8	85.1
E3	magenta	100.0	0.6	49.6	50.2	52.8	52.7	-1.4	-1.4
F3	cyan	100.0	0.9	48.1	49.0	-28.0	-28.0	-32.0	-31.7
A4	white	99.3	0.6	94.9	94.9	0.4	0.2	2.4	1.9
B4	neutral 8	100.0	0.7	79.1	79.7	0.1	-0.3	0.0	-0.2
C4	neutral 6.5	100.0	0.7	64.9	65.6	-0.8	-0.8	-0.6	-0.8
D4	neutral 5	100.0	1.3	48.7	49.9	1.2	1.2	-0.6	-1.0
E4	neutral 3.5	100.0	1.4	34.0	35.3	0.5	0.5	-1.8	-2.3
F4	black	100.0	1.2	20.5	21.7	1.3	1.2	-2.1	-2.4
A5	paper white	100.0	0.5	97.2	97.2	0.1	0.1	1.8	1.4
B5	skin highlight L*=89	88.2	2.8	86.1	86.4	14.2	13.6	13.0	10.3
C5	skin highlight L*=75	91.8	3.1	73.1	74.0	23.4	22.4	18.4	15.6
D5	skin shadow L*=25	100.0	1.0	26.6	27.4	17.0	17.3	13.8	13.4
E5	skin shadow L*=11	100.0	1.0	17.1	18.1	11.5	11.7	9.8	10.0
F5	Max Black	100.0	0.9	10.3	11.2	1.4	1.5	-0.2	-0.2
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		97.9	97.0						
Average Score for the Worst 10% (3 lowest scoring patches)		91.5	95.2						
ΔE				Page 9					

97.2_{color} / 96.2_{tone}

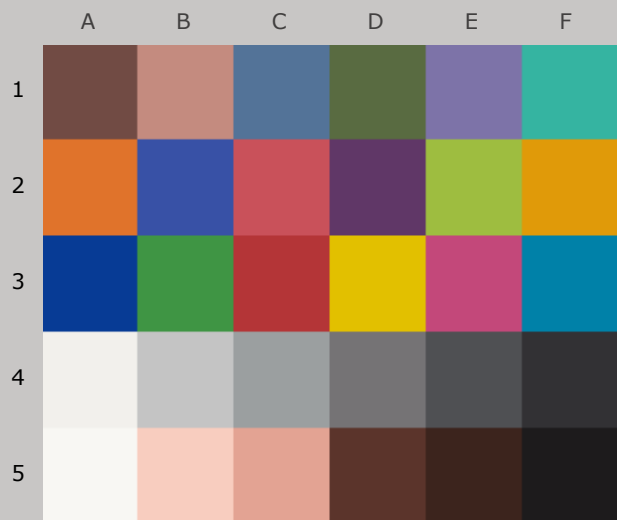

Original Print Colors
(measured before light exposure)



Colors after 50 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

50 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	96.6	2.0	36.0	37.6	16.3	16.4	11.4	10.2
B1	light Skin	94.2	2.3	63.6	64.6	21.3	20.9	15.9	13.9
C1	blue sky	100.0	1.4	47.2	48.5	-4.0	-4.0	-23.9	-23.5
D1	foliage	95.2	2.1	42.7	44.0	-13.0	-13.3	20.6	19.0
E1	blue flower	98.1	1.8	51.2	52.6	12.6	12.5	-26.6	-25.6
F1	bluish green	93.1	3.4	66.3	67.5	-38.9	-37.8	-1.4	-4.4
A2	orange	95.6	3.7	60.7	61.5	40.4	39.3	57.1	53.6
B2	purplish blue	97.1	2.3	36.1	37.2	13.1	11.9	-49.7	-48.1
C2	moderate red	96.5	2.5	51.2	52.0	48.8	48.7	20.7	18.4
D2	purple	99.9	1.6	29.8	31.3	24.7	24.5	-20.8	-20.3
E2	yellow green	94.2	4.2	72.7	73.8	-23.7	-24.0	57.0	52.9
F2	orange yellow	96.3	3.5	69.3	70.4	19.6	18.0	71.9	69.1
A3	blue	96.5	2.8	26.6	27.8	15.1	13.3	-54.7	-53.0
B3	green	95.7	3.0	54.7	55.9	-39.9	-39.9	33.6	30.9
C3	red	97.8	1.9	42.8	43.4	52.3	52.4	29.7	27.8
D3	yellow	98.0	2.4	78.7	79.5	1.5	0.0	86.8	85.1
E3	magenta	100.0	0.8	49.6	50.4	52.8	52.8	-1.4	-1.5
F3	cyan	100.0	1.2	48.1	49.3	-28.0	-28.0	-32.0	-31.7
A4	white	98.8	0.6	94.9	95.0	0.4	0.2	2.4	1.8
B4	neutral 8	100.0	0.8	79.1	79.9	0.1	-0.2	0.0	-0.1
C4	neutral 6.5	100.0	1.0	64.9	65.9	-0.8	-0.8	-0.6	-0.9
D4	neutral 5	99.5	1.4	48.7	50.0	1.2	1.3	-0.6	-1.1
E4	neutral 3.5	99.4	1.6	34.0	35.5	0.5	0.5	-1.8	-2.3
F4	black	100.0	1.3	20.5	21.7	1.3	1.1	-2.1	-2.4
A5	paper white	100.0	0.4	97.2	97.1	0.1	0.1	1.8	1.4
B5	skin highlight L*=89	83.6	3.7	86.1	86.6	14.2	13.6	13.0	9.4
C5	skin highlight L*=75	89.5	3.8	73.1	74.3	23.4	22.5	18.4	14.9
D5	skin shadow L*=25	99.7	1.0	26.6	27.4	17.0	17.5	13.8	13.6
E5	skin shadow L*=11	100.0	1.3	17.1	18.4	11.5	11.8	9.8	10.0
F5	Max Black	100.0	0.9	10.3	11.2	1.4	1.6	-0.2	-0.3
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		97.2	96.2						
Average Score for the Worst 10% (3 lowest scoring patches)		88.7	94.6						

96.6_{color} / 95.9_{tone}




Original Print Colors
(measured before light exposure)



Colors after 60 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

60 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	95.6	2.3	36.0	37.9	16.3	16.3	11.4	10.0
B1	light Skin	93.5	2.6	63.6	64.9	21.3	21.0	15.9	13.7
C1	blue sky	100.0	1.6	47.2	48.7	-4.0	-3.9	-23.9	-23.4
D1	foliage	93.4	2.6	42.7	44.3	-13.0	-13.1	20.6	18.5
E1	blue flower	97.4	2.1	51.2	52.8	12.6	12.6	-26.6	-25.3
F1	bluish green	91.4	4.1	66.3	67.8	-38.9	-37.5	-1.4	-4.9
A2	orange	94.3	4.6	60.7	61.8	40.4	39.1	57.1	52.8
B2	purplish blue	96.3	2.8	36.1	37.6	13.1	11.8	-49.7	-47.6
C2	moderate red	96.4	2.7	51.2	52.3	48.8	48.7	20.7	18.3
D2	purple	99.6	1.7	29.8	31.4	24.7	24.5	-20.8	-20.2
E2	yellow green	92.6	5.3	72.7	74.1	-23.7	-24.1	57.0	51.9
F2	orange yellow	95.6	4.0	69.3	70.5	19.6	17.8	71.9	68.5
A3	blue	96.0	3.0	26.6	27.9	15.1	13.2	-54.7	-52.8
B3	green	95.0	3.4	54.7	56.1	-39.9	-40.0	33.6	30.5
C3	red	97.5	2.1	42.8	43.4	52.3	52.4	29.7	27.6
D3	yellow	97.3	3.1	78.7	79.8	1.5	-0.2	86.8	84.4
E3	magenta	100.0	1.1	49.6	50.6	52.8	52.7	-1.4	-1.4
F3	cyan	100.0	1.4	48.1	49.5	-28.0	-27.9	-32.0	-31.7
A4	white	99.4	0.6	94.9	95.1	0.4	0.2	2.4	1.9
B4	neutral 8	100.0	1.1	79.1	80.1	0.1	-0.3	0.0	-0.2
C4	neutral 6.5	100.0	1.1	64.9	66.0	-0.8	-0.8	-0.6	-0.8
D4	neutral 5	100.0	1.7	48.7	50.3	1.2	1.4	-0.6	-1.0
E4	neutral 3.5	100.0	2.0	34.0	36.0	0.5	0.6	-1.8	-2.2
F4	black	100.0	1.9	20.5	22.4	1.3	1.3	-2.1	-2.3
A5	paper white	100.0	0.3	97.2	97.4	0.1	0.1	1.8	1.6
B5	skin highlight L*=89	80.3	4.4	86.1	86.9	14.2	13.6	13.0	8.7
C5	skin highlight L*=75	87.6	4.4	73.1	74.5	23.4	22.4	18.4	14.3
D5	skin shadow L*=25	98.7	1.6	26.6	27.9	17.0	17.3	13.8	13.1
E5	skin shadow L*=11	100.0	1.4	17.1	18.5	11.5	11.8	9.8	10.0
F5	Max Black	100.0	1.7	10.3	12.0	1.4	1.6	-0.2	-0.2
Summary Results		I*Color	I*tone	ΔE	AARDENBURG IMAGING & ARCHIVES				
Average Score for all patches		96.6	95.9	2.4					
Average Score for the Worst 10% (3 lowest scoring patches)		86.5	93.9	4.8					

Page 11

95.8_{color} / 95.8_{tone}




Original Print Colors
(measured before light exposure)



Colors after 70 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

70 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	94.4	2.5	36.0	37.9	16.3	16.3	11.4	9.8
B1	light Skin	92.3	2.9	63.6	64.9	21.3	21.0	15.9	13.4
C1	blue sky	99.7	1.6	47.2	48.7	-4.0	-3.9	-23.9	-23.3
D1	foliage	91.6	3.0	42.7	44.4	-13.0	-13.1	20.6	18.1
E1	blue flower	96.7	2.2	51.2	52.8	12.6	12.6	-26.6	-25.1
F1	bluish green	89.3	4.9	66.3	67.8	-38.9	-37.2	-1.4	-5.7
A2	orange	93.3	5.3	60.7	61.9	40.4	39.0	57.1	52.1
B2	purplish blue	95.7	3.1	36.1	37.6	13.1	11.7	-49.7	-47.3
C2	moderate red	95.7	3.0	51.2	52.3	48.8	48.7	20.7	18.0
D2	purple	99.2	1.7	29.8	31.4	24.7	24.5	-20.8	-20.1
E2	yellow green	90.8	6.4	72.7	74.2	-23.7	-24.1	57.0	50.8
F2	orange yellow	94.6	4.7	69.3	70.6	19.6	17.6	71.9	67.8
A3	blue	95.6	3.2	26.6	27.9	15.1	13.1	-54.7	-52.6
B3	green	93.9	4.0	54.7	56.1	-39.9	-39.9	33.6	29.9
C3	red	97.1	2.3	42.8	43.4	52.3	52.5	29.7	27.4
D3	yellow	96.6	3.6	78.7	79.9	1.5	-0.4	86.8	83.9
E3	magenta	100.0	1.1	49.6	50.7	52.8	52.7	-1.4	-1.3
F3	cyan	100.0	1.5	48.1	49.5	-28.0	-27.8	-32.0	-31.5
A4	white	99.5	0.6	94.9	95.1	0.4	0.2	2.4	1.9
B4	neutral 8	100.0	1.1	79.1	80.1	0.1	-0.3	0.0	-0.2
C4	neutral 6.5	100.0	1.2	64.9	66.1	-0.8	-0.7	-0.6	-0.8
D4	neutral 5	99.7	1.7	48.7	50.3	1.2	1.4	-0.6	-1.0
E4	neutral 3.5	99.4	2.1	34.0	36.0	0.5	0.7	-1.8	-2.3
F4	black	100.0	2.0	20.5	22.4	1.3	1.3	-2.1	-2.3
A5	paper white	100.0	0.2	97.2	97.4	0.1	0.1	1.8	1.8
B5	skin highlight L*=89	74.8	5.4	86.1	86.9	14.2	13.8	13.0	7.6
C5	skin highlight L*=75	84.7	5.3	73.1	74.7	23.4	22.5	18.4	13.4
D5	skin shadow L*=25	98.3	1.5	26.6	27.8	17.0	17.5	13.8	13.1
E5	skin shadow L*=11	100.0	1.4	17.1	18.5	11.5	11.9	9.8	10.0
F5	Max Black	100.0	1.5	10.3	11.7	1.4	1.6	-0.2	-0.3
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		95.8	95.8						
Average Score for the Worst 10% (3 lowest scoring patches)		82.9	93.7						

94.5_{color} / 95.4_{tone}



Original Print Colors
(measured before light exposure)



Colors after 80 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

80 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	92.6	2.9	36.0	38.1	16.3	16.4	11.4	9.5
B1	light Skin	90.3	3.4	63.6	65.0	21.3	21.1	15.9	12.8
C1	blue sky	100.0	1.7	47.2	48.8	-4.0	-3.9	-23.9	-23.5
D1	foliage	89.5	3.5	42.7	44.5	-13.0	-13.0	20.6	17.6
E1	blue flower	96.8	2.3	51.2	53.0	12.6	12.6	-26.6	-25.2
F1	bluish green	86.5	6.0	66.3	68.0	-38.9	-36.9	-1.4	-6.8
A2	orange	92.1	6.2	60.7	61.9	40.4	39.0	57.1	51.2
B2	purplish blue	95.7	3.1	36.1	37.6	13.1	11.7	-49.7	-47.4
C2	moderate red	94.8	3.5	51.2	52.3	48.8	48.7	20.7	17.5
D2	purple	99.2	1.9	29.8	31.5	24.7	24.6	-20.8	-20.1
E2	yellow green	88.8	7.6	72.7	74.4	-23.7	-24.1	57.0	49.6
F2	orange yellow	93.5	5.5	69.3	70.7	19.6	17.4	71.9	67.0
A3	blue	95.4	3.4	26.6	28.0	15.1	13.0	-54.7	-52.4
B3	green	92.9	4.5	54.7	56.2	-39.9	-40.0	33.6	29.4
C3	red	96.6	2.6	42.8	43.4	52.3	52.5	29.7	27.1
D3	yellow	95.7	4.4	78.7	80.1	1.5	-0.7	86.8	83.2
E3	magenta	100.0	1.1	49.6	50.7	52.8	52.7	-1.4	-1.5
F3	cyan	100.0	1.5	48.1	49.6	-28.0	-27.7	-32.0	-31.7
A4	white	95.5	1.0	94.9	95.2	0.4	0.3	2.4	1.5
B4	neutral 8	98.0	1.3	79.1	80.2	0.1	-0.3	0.0	-0.6
C4	neutral 6.5	100.0	1.4	64.9	66.2	-0.8	-0.7	-0.6	-1.0
D4	neutral 5	98.0	1.9	48.7	50.4	1.2	1.5	-0.6	-1.2
E4	neutral 3.5	98.1	2.2	34.0	36.1	0.5	0.7	-1.8	-2.4
F4	black	100.0	2.0	20.5	22.5	1.3	1.3	-2.1	-2.4
A5	paper white	100.0	0.3	97.2	97.4	0.1	0.1	1.8	1.6
B5	skin highlight L*=89	67.9	6.7	86.1	87.0	14.2	14.0	13.0	6.3
C5	skin highlight L*=75	80.5	6.5	73.1	74.8	23.4	22.6	18.4	12.1
D5	skin shadow L*=25	97.3	1.9	26.6	28.1	17.0	17.4	13.8	12.8
E5	skin shadow L*=11	100.0	1.7	17.1	18.7	11.5	11.9	9.8	10.0
F5	Max Black	100.0	1.9	10.3	12.2	1.4	1.7	-0.2	-0.3
Summary Results		I*Color	I*tone	ΔE	AARDENBURG IMAGING & ARCHIVES				
Average Score for all patches		94.5	95.4	3.1					
Average Score for the Worst 10% (3 lowest scoring patches)		78.3	93.2	6.9					

Page 13

93.4_{color} / 95.1_{tone}



Original Print Colors
(measured before light exposure)




Colors after 90 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

90 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	91.3	3.2	36.0	38.2	16.3	16.4	11.4	9.2
B1	light Skin	88.3	4.0	63.6	65.2	21.3	21.1	15.9	12.3
C1	blue sky	99.7	1.8	47.2	48.9	-4.0	-3.7	-23.9	-23.4
D1	foliage	87.5	4.0	42.7	44.6	-13.0	-13.0	20.6	17.1
E1	blue flower	96.4	2.5	51.2	53.2	12.6	12.7	-26.6	-25.1
F1	bluish green	83.9	7.0	66.3	68.2	-38.9	-36.6	-1.4	-7.7
A2	orange	90.8	7.1	60.7	62.1	40.4	38.9	57.1	50.3
B2	purplish blue	95.4	3.3	36.1	37.8	13.1	11.7	-49.7	-47.1
C2	moderate red	94.1	3.9	51.2	52.5	48.8	48.7	20.7	17.1
D2	purple	99.2	2.0	29.8	31.6	24.7	24.6	-20.8	-20.1
E2	yellow green	86.7	8.9	72.7	74.6	-23.7	-24.2	57.0	48.3
F2	orange yellow	92.2	6.5	69.3	70.9	19.6	17.3	71.9	66.0
A3	blue	95.1	3.6	26.6	28.1	15.1	13.0	-54.7	-52.3
B3	green	91.7	5.1	54.7	56.4	-39.9	-40.0	33.6	28.8
C3	red	96.1	2.9	42.8	43.5	52.3	52.5	29.7	26.8
D3	yellow	94.7	5.3	78.7	80.3	1.5	-0.9	86.8	82.3
E3	magenta	100.0	1.2	49.6	50.8	52.8	52.8	-1.4	-1.5
F3	cyan	100.0	1.6	48.1	49.7	-28.0	-27.7	-32.0	-31.7
A4	white	93.4	1.2	94.9	95.2	0.4	0.3	2.4	1.3
B4	neutral 8	96.1	1.5	79.1	80.4	0.1	-0.2	0.0	-0.8
C4	neutral 6.5	100.0	1.5	64.9	66.4	-0.8	-0.6	-0.6	-1.0
D4	neutral 5	97.2	2.0	48.7	50.6	1.2	1.6	-0.6	-1.2
E4	neutral 3.5	96.9	2.4	34.0	36.3	0.5	0.8	-1.8	-2.5
F4	black	100.0	2.1	20.5	22.6	1.3	1.4	-2.1	-2.5
A5	paper white	100.0	0.3	97.2	97.4	0.1	0.1	1.8	1.6
B5	skin highlight L*=89	62.6	7.7	86.1	87.1	14.2	14.2	13.0	5.3
C5	skin highlight L*=75	76.6	7.7	73.1	75.0	23.4	22.6	18.4	10.9
D5	skin shadow L*=25	96.3	2.1	26.6	28.2	17.0	17.5	13.8	12.6
E5	skin shadow L*=11	100.0	1.8	17.1	18.8	11.5	11.9	9.8	10.0
F5	Max Black	100.0	2.1	10.3	12.4	1.4	1.7	-0.2	-0.2
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		93.4	95.1						
Average Score for the Worst 10% (3 lowest scoring patches)		74.4	92.6						

92.1_{color} / 94.8_{tone}

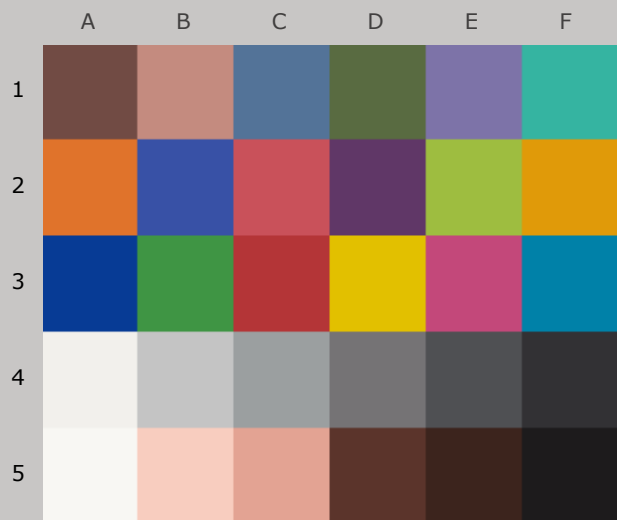

Original Print Colors
(measured before light exposure)




Colors after 100 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

100 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	89.6	3.3	36.0	38.1	16.3	16.5	11.4	8.9
B1	light Skin	86.2	4.5	63.6	65.2	21.3	21.2	15.9	11.8
C1	blue sky	99.9	1.8	47.2	48.9	-4.0	-3.8	-23.9	-23.4
D1	foliage	85.6	4.4	42.7	44.6	-13.0	-13.1	20.6	16.6
E1	blue flower	96.1	2.6	51.2	53.2	12.6	12.7	-26.6	-25.0
F1	bluish green	81.0	8.1	66.3	68.2	-38.9	-36.2	-1.4	-8.8
A2	orange	89.5	7.9	60.7	62.0	40.4	38.9	57.1	49.4
B2	purplish blue	95.2	3.3	36.1	37.7	13.1	11.6	-49.7	-47.1
C2	moderate red	93.3	4.2	51.2	52.4	48.8	48.9	20.7	16.7
D2	purple	99.5	1.8	29.8	31.5	24.7	24.8	-20.8	-20.2
E2	yellow green	84.3	10.4	72.7	74.7	-23.7	-24.2	57.0	46.8
F2	orange yellow	91.0	7.4	69.3	71.0	19.6	17.1	71.9	65.1
A3	blue	95.3	3.4	26.6	27.8	15.1	12.9	-54.7	-52.5
B3	green	90.6	5.6	54.7	56.4	-39.9	-40.1	33.6	28.3
C3	red	95.9	3.0	42.8	43.4	52.3	52.7	29.7	26.7
D3	yellow	94.0	6.0	78.7	80.4	1.5	-1.1	86.8	81.6
E3	magenta	100.0	1.2	49.6	50.8	52.8	52.9	-1.4	-1.5
F3	cyan	100.0	1.5	48.1	49.6	-28.0	-27.9	-32.0	-31.8
A4	white	91.4	1.3	94.9	95.1	0.4	0.4	2.4	1.1
B4	neutral 8	93.7	1.6	79.1	80.3	0.1	-0.2	0.0	-1.1
C4	neutral 6.5	99.4	1.6	64.9	66.4	-0.8	-0.6	-0.6	-1.1
D4	neutral 5	96.1	2.1	48.7	50.6	1.2	1.7	-0.6	-1.3
E4	neutral 3.5	95.7	2.4	34.0	36.3	0.5	0.8	-1.8	-2.6
F4	black	99.1	2.0	20.5	22.4	1.3	1.3	-2.1	-2.6
A5	paper white	100.0	0.2	97.2	97.3	0.1	0.1	1.8	1.7
B5	skin highlight L*=89	57.1	8.8	86.1	87.0	14.2	14.4	13.0	4.2
C5	skin highlight L*=75	72.0	9.0	73.1	75.0	23.4	22.8	18.4	9.6
D5	skin shadow L*=25	95.7	1.9	26.6	27.9	17.0	17.8	13.8	12.6
E5	skin shadow L*=11	97.2	1.5	17.1	18.4	11.5	12.3	9.8	10.3
F5	Max Black	100.0	1.1	10.3	11.4	1.4	1.7	-0.2	-0.3
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		92.1	94.8						
Average Score for the Worst 10% (3 lowest scoring patches)		70.0	92.1						

90.7_{color} / 94.4_{tone}

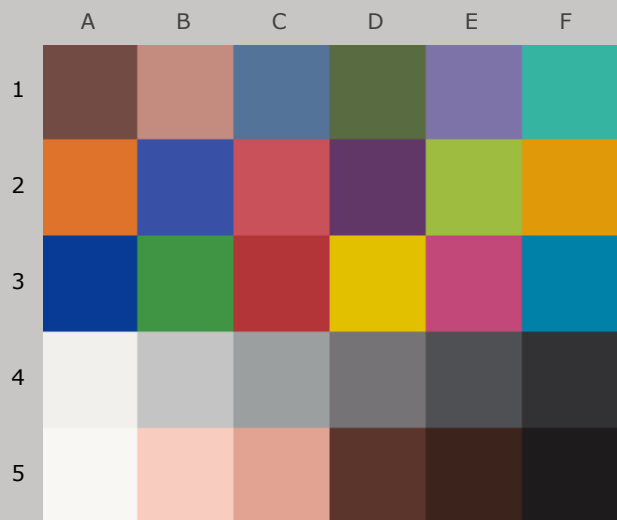

Original Print Colors
(measured before light exposure)



Colors after 110 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

110 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	87.9	3.7	36.0	38.2	16.3	16.6	11.4	8.5
B1	light Skin	83.4	5.2	63.6	65.3	21.3	21.4	15.9	11.0
C1	blue sky	100.0	1.8	47.2	48.9	-4.0	-3.8	-23.9	-23.5
D1	foliage	82.8	5.1	42.7	44.6	-13.0	-13.0	20.6	15.9
E1	blue flower	95.9	2.6	51.2	53.2	12.6	12.7	-26.6	-24.9
F1	bluish green	77.8	9.4	66.3	68.3	-38.9	-35.9	-1.4	-10.0
A2	orange	87.8	9.1	60.7	62.0	40.4	38.9	57.1	48.2
B2	purplish blue	94.8	3.5	36.1	37.6	13.1	11.5	-49.7	-46.9
C2	moderate red	92.4	4.7	51.2	52.3	48.8	48.9	20.7	16.2
D2	purple	99.7	1.7	29.8	31.4	24.7	24.8	-20.8	-20.2
E2	yellow green	81.6	12.0	72.7	74.8	-23.7	-24.2	57.0	45.2
F2	orange yellow	89.2	8.7	69.3	71.0	19.6	17.1	71.9	63.7
A3	blue	95.1	3.5	26.6	27.7	15.1	12.8	-54.7	-52.4
B3	green	89.4	6.3	54.7	56.4	-39.9	-40.2	33.6	27.6
C3	red	95.4	3.3	42.8	43.2	52.3	52.8	29.7	26.4
D3	yellow	92.7	7.0	78.7	80.4	1.5	-1.3	86.8	80.6
E3	magenta	100.0	1.1	49.6	50.7	52.8	52.9	-1.4	-1.6
F3	cyan	100.0	1.4	48.1	49.5	-28.0	-27.8	-32.0	-31.8
A4	white	89.0	1.5	94.9	94.9	0.4	0.5	2.4	0.9
B4	neutral 8	90.2	1.8	79.1	80.2	0.1	-0.2	0.0	-1.4
C4	neutral 6.5	97.3	1.5	64.9	66.3	-0.8	-0.5	-0.6	-1.3
D4	neutral 5	95.0	2.2	48.7	50.7	1.2	1.7	-0.6	-1.4
E4	neutral 3.5	94.3	2.4	34.0	36.2	0.5	0.9	-1.8	-2.8
F4	black	98.4	1.9	20.5	22.3	1.3	1.3	-2.1	-2.7
A5	paper white	100.0	0.2	97.2	97.1	0.1	0.1	1.8	1.7
B5	skin highlight L*=89	51.8	9.8	86.1	86.9	14.2	14.6	13.0	3.2
C5	skin highlight L*=75	66.9	10.5	73.1	74.9	23.4	22.9	18.4	8.0
D5	skin shadow L*=25	94.8	2.0	26.6	27.8	17.0	17.8	13.8	12.4
E5	skin shadow L*=11	96.4	1.3	17.1	18.0	11.5	12.3	9.8	10.4
F5	Max Black	100.0	0.9	10.3	11.2	1.4	1.7	-0.2	-0.3
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		90.7	94.4						
Average Score for the Worst 10% (3 lowest scoring patches)		65.5	91.7						
				Page 16					

89.0_{color} / 93.9_{tone}



Original Print Colors
(measured before light exposure)



Colors after 120 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

120 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	85.8	4.1	36.0	38.3	16.3	16.6	11.4	8.1
B1	light Skin	80.1	6.1	63.6	65.4	21.3	21.6	15.9	10.1
C1	blue sky	100.0	1.8	47.2	49.0	-4.0	-3.6	-23.9	-23.6
D1	foliage	79.9	5.8	42.7	44.8	-13.0	-12.9	20.6	15.2
E1	blue flower	96.0	2.8	51.2	53.4	12.6	12.7	-26.6	-24.9
F1	bluish green	74.2	10.8	66.3	68.5	-38.9	-35.3	-1.4	-11.3
A2	orange	86.0	10.4	60.7	62.2	40.4	38.8	57.1	46.9
B2	purplish blue	94.5	3.7	36.1	37.8	13.1	11.5	-49.7	-46.8
C2	moderate red	91.3	5.3	51.2	52.4	48.8	49.1	20.7	15.6
D2	purple	99.7	1.8	29.8	31.6	24.7	24.8	-20.8	-20.2
E2	yellow green	78.7	13.9	72.7	75.0	-23.7	-24.1	57.0	43.3
F2	orange yellow	87.5	10.0	69.3	71.2	19.6	16.9	71.9	62.4
A3	blue	94.6	3.8	26.6	27.9	15.1	12.6	-54.7	-52.2
B3	green	88.0	7.0	54.7	56.6	-39.9	-40.1	33.6	26.9
C3	red	94.8	3.7	42.8	43.3	52.3	52.9	29.7	26.0
D3	yellow	91.4	8.2	78.7	80.6	1.5	-1.6	86.8	79.4
E3	magenta	100.0	1.2	49.6	50.8	52.8	52.9	-1.4	-1.8
F3	cyan	100.0	1.6	48.1	49.7	-28.0	-27.7	-32.0	-31.9
A4	white	86.9	1.7	94.9	95.0	0.4	0.5	2.4	0.7
B4	neutral 8	86.3	2.2	79.1	80.4	0.1	-0.1	0.0	-1.8
C4	neutral 6.5	95.4	1.8	64.9	66.5	-0.8	-0.5	-0.6	-1.4
D4	neutral 5	93.1	2.4	48.7	50.8	1.2	1.7	-0.6	-1.6
E4	neutral 3.5	92.2	2.6	34.0	36.4	0.5	0.9	-1.8	-2.9
F4	black	96.9	2.2	20.5	22.6	1.3	1.4	-2.1	-2.9
A5	paper white	100.0	0.2	97.2	97.2	0.1	0.1	1.8	1.7
B5	skin highlight L*=89	46.7	10.8	86.1	87.0	14.2	14.8	13.0	2.2
C5	skin highlight L*=75	61.8	12.0	73.1	75.1	23.4	23.1	18.4	6.5
D5	skin shadow L*=25	93.3	2.4	26.6	27.9	17.0	17.8	13.8	12.0
E5	skin shadow L*=11	96.6	1.4	17.1	18.1	11.5	12.4	9.8	10.2
F5	Max Black	100.0	1.2	10.3	11.4	1.4	1.7	-0.2	-0.3
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		89.0	93.9						
Average Score for the Worst 10% (3 lowest scoring patches)		60.9	91.1						

87.7^{color} / 93.7^{tone}



Original Print Colors
(measured before light exposure)



Colors after 130 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

130 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	83.6	4.5	36.0	38.4	16.3	16.7	11.4	7.7
B1	light Skin	77.1	6.9	63.6	65.6	21.3	21.6	15.9	9.3
C1	blue sky	99.9	2.0	47.2	49.1	-4.0	-3.6	-23.9	-23.5
D1	foliage	76.9	6.5	42.7	44.9	-13.0	-12.8	20.6	14.5
E1	blue flower	95.6	2.9	51.2	53.5	12.6	12.7	-26.6	-24.8
F1	bluish green	70.6	12.2	66.3	68.6	-38.9	-34.8	-1.4	-12.6
A2	orange	84.0	11.8	60.7	62.3	40.4	38.8	57.1	45.5
B2	purplish blue	94.3	3.8	36.1	37.8	13.1	11.4	-49.7	-46.7
C2	moderate red	90.3	5.8	51.2	52.6	48.8	49.0	20.7	15.1
D2	purple	99.2	2.0	29.8	31.7	24.7	24.8	-20.8	-20.1
E2	yellow green	75.1	16.0	72.7	75.2	-23.7	-23.9	57.0	41.2
F2	orange yellow	85.4	11.5	69.3	71.3	19.6	16.8	71.9	60.9
A3	blue	94.2	4.0	26.6	28.0	15.1	12.5	-54.7	-52.0
B3	green	86.0	8.1	54.7	56.7	-39.9	-40.0	33.6	25.8
C3	red	94.1	4.1	42.8	43.5	52.3	52.8	29.7	25.6
D3	yellow	89.7	9.7	78.7	80.9	1.5	-1.7	86.8	77.9
E3	magenta	100.0	1.4	49.6	50.9	52.8	52.8	-1.4	-1.7
F3	cyan	100.0	1.7	48.1	49.8	-28.0	-27.6	-32.0	-31.8
A4	white	87.5	1.7	94.9	95.1	0.4	0.5	2.4	0.7
B4	neutral 8	84.2	2.4	79.1	80.4	0.1	0.0	0.0	-2.0
C4	neutral 6.5	94.2	2.0	64.9	66.7	-0.8	-0.4	-0.6	-1.5
D4	neutral 5	91.7	2.6	48.7	51.0	1.2	1.8	-0.6	-1.7
E4	neutral 3.5	90.5	2.8	34.0	36.5	0.5	1.0	-1.8	-3.1
F4	black	96.4	2.3	20.5	22.6	1.3	1.5	-2.1	-2.9
A5	paper white	100.0	0.1	97.2	97.2	0.1	0.1	1.8	1.9
B5	skin highlight L*=89	42.4	11.6	86.1	87.1	14.2	15.1	13.0	1.4
C5	skin highlight L*=75	56.7	13.6	73.1	75.3	23.4	23.3	18.4	5.0
D5	skin shadow L*=25	92.4	2.7	26.6	28.1	17.0	17.8	13.8	11.8
E5	skin shadow L*=11	97.4	1.5	17.1	18.3	11.5	12.3	9.8	10.1
F5	Max Black	100.0	1.4	10.3	11.7	1.4	1.7	-0.2	-0.5

Summary Results

I*Color

I*tone

ΔE

Average Score for all patches

87.7

93.7


5.3

Average Score for the Worst 10%
(3 lowest scoring patches)

56.6


90.8

13.9



AARDENBURG IMAGING
& ARCHIVES

86.0_{color} / 93.4_{tone}

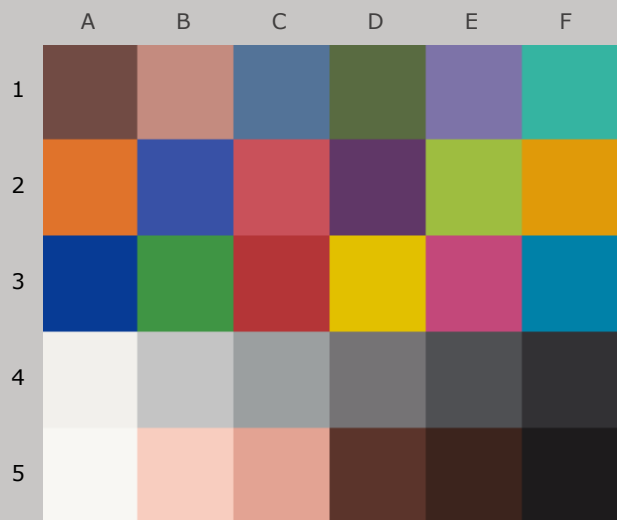

Original Print Colors
(measured before light exposure)



Colors after 140 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

140 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	81.4	4.9	36.0	38.5	16.3	16.7	11.4	7.2
B1	light Skin	73.5	7.8	63.6	65.7	21.3	21.8	15.9	8.4
C1	blue sky	100.0	2.0	47.2	49.2	-4.0	-3.6	-23.9	-23.6
D1	foliage	73.4	7.3	42.7	45.0	-13.0	-12.7	20.6	13.7
E1	blue flower	95.4	3.0	51.2	53.6	12.6	12.7	-26.6	-24.8
F1	bluish green	66.8	13.7	66.3	68.8	-38.9	-34.1	-1.4	-13.9
A2	orange	81.7	13.4	60.7	62.4	40.4	38.8	57.1	43.8
B2	purplish blue	94.1	3.9	36.1	37.8	13.1	11.4	-49.7	-46.6
C2	moderate red	89.1	6.4	51.2	52.6	48.8	49.1	20.7	14.5
D2	purple	99.1	2.0	29.8	31.7	24.7	24.9	-20.8	-20.1
E2	yellow green	71.4	18.4	72.7	75.5	-23.7	-23.7	57.0	38.8
F2	orange yellow	83.0	13.4	69.3	71.5	19.6	16.7	71.9	59.0
A3	blue	94.2	4.0	26.6	28.0	15.1	12.5	-54.7	-51.9
B3	green	83.9	9.1	54.7	56.8	-39.9	-40.0	33.6	24.8
C3	red	93.5	4.5	42.8	43.6	52.3	52.9	29.7	25.3
D3	yellow	87.8	11.3	78.7	81.1	1.5	-1.9	86.8	76.3
E3	magenta	100.0	1.4	49.6	51.0	52.8	52.9	-1.4	-1.8
F3	cyan	100.0	1.8	48.1	49.9	-28.0	-27.6	-32.0	-31.8
A4	white	87.3	1.7	94.9	95.1	0.4	0.5	2.4	0.7
B4	neutral 8	80.7	2.7	79.1	80.5	0.1	0.0	0.0	-2.3
C4	neutral 6.5	91.6	2.3	64.9	66.8	-0.8	-0.3	-0.6	-1.7
D4	neutral 5	89.7	2.8	48.7	51.1	1.2	1.9	-0.6	-1.9
E4	neutral 3.5	88.5	3.1	34.0	36.6	0.5	1.0	-1.8	-3.3
F4	black	95.2	2.4	20.5	22.7	1.3	1.5	-2.1	-3.0
A5	paper white	100.0	0.1	97.2	97.2	0.1	0.1	1.8	1.9
B5	skin highlight L*=89	38.6	12.4	86.1	87.2	14.2	15.2	13.0	0.7
C5	skin highlight L*=75	52.1	14.9	73.1	75.4	23.4	23.5	18.4	3.6
D5	skin shadow L*=25	90.9	3.0	26.6	28.2	17.0	17.9	13.8	11.5
E5	skin shadow L*=11	96.9	1.6	17.1	18.4	11.5	12.4	9.8	10.0
F5	Max Black	100.0	1.3	10.3	11.6	1.4	1.8	-0.2	-0.4
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		86.0	93.4	5.9					
Average Score for the Worst 10% (3 lowest scoring patches)		52.5	90.5	15.7					

84.3_{color} / 93.0_{tone}



Original Print Colors
(measured before light exposure)




Colors after 150 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

150 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	78.9	5.4	36.0	38.6	16.3	16.8	11.4	6.8
B1	light Skin	69.6	8.9	63.6	65.8	21.3	22.0	15.9	7.4
C1	blue sky	100.0	2.1	47.2	49.3	-4.0	-3.6	-23.9	-23.7
D1	foliage	70.0	8.2	42.7	45.1	-13.0	-12.5	20.6	12.8
E1	blue flower	95.6	3.1	51.2	53.7	12.6	12.8	-26.6	-24.8
F1	bluish green	63.2	15.1	66.3	68.9	-38.9	-33.6	-1.4	-15.2
A2	orange	79.2	15.2	60.7	62.4	40.4	38.9	57.1	42.1
B2	purplish blue	93.8	4.1	36.1	37.9	13.1	11.3	-49.7	-46.4
C2	moderate red	87.8	7.1	51.2	52.7	48.8	49.2	20.7	13.8
D2	purple	99.2	2.1	29.8	31.8	24.7	24.8	-20.8	-20.1
E2	yellow green	67.1	21.0	72.7	75.7	-23.7	-23.5	57.0	36.2
F2	orange yellow	80.1	15.5	69.3	71.6	19.6	16.7	71.9	56.9
A3	blue	93.8	4.3	26.6	28.0	15.1	12.4	-54.7	-51.8
B3	green	81.8	10.2	54.7	56.9	-39.9	-39.9	33.6	23.7
C3	red	92.6	5.0	42.8	43.6	52.3	52.9	29.7	24.8
D3	yellow	85.7	13.1	78.7	81.3	1.5	-2.1	86.8	74.4
E3	magenta	99.9	1.6	49.6	51.1	52.8	52.9	-1.4	-2.0
F3	cyan	100.0	1.9	48.1	50.0	-28.0	-27.5	-32.0	-31.9
A4	white	87.2	1.7	94.9	95.1	0.4	0.6	2.4	0.7
B4	neutral 8	77.7	3.0	79.1	80.5	0.1	0.1	0.0	-2.6
C4	neutral 6.5	89.0	2.5	64.9	66.9	-0.8	-0.2	-0.6	-2.0
D4	neutral 5	87.4	3.0	48.7	51.2	1.2	2.0	-0.6	-2.1
E4	neutral 3.5	86.4	3.3	34.0	36.8	0.5	1.1	-1.8	-3.5
F4	black	94.3	2.6	20.5	22.8	1.3	1.5	-2.1	-3.1
A5	paper white	100.0	0.2	97.2	97.2	0.1	0.0	1.8	1.9
B5	skin highlight L*=89	35.7	12.9	86.1	87.3	14.2	15.3	13.0	0.2
C5	skin highlight L*=75	48.1	16.1	73.1	75.5	23.4	23.7	18.4	2.4
D5	skin shadow L*=25	89.5	3.3	26.6	28.3	17.0	17.9	13.8	11.2
E5	skin shadow L*=11	96.7	1.7	17.1	18.5	11.5	12.4	9.8	10.1
F5	Max Black	99.9	1.4	10.3	11.6	1.4	1.8	-0.2	-0.5
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		84.3	93.0						
Average Score for the Worst 10% (3 lowest scoring patches)		49.0	90.1						

82.9_{color} / 92.8_{tone}

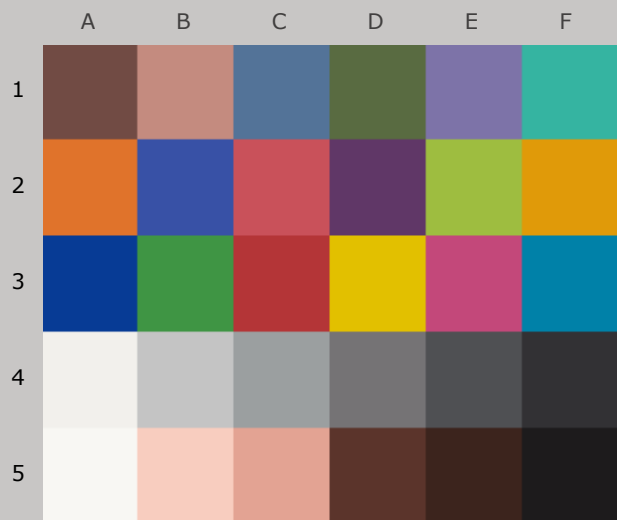

Original Print Colors
(measured before light exposure)



Colors after 160 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

160 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	76.5	5.8	36.0	38.6	16.3	16.9	11.4	6.3
B1	light Skin	66.1	9.8	63.6	65.8	21.3	22.2	15.9	6.4
C1	blue sky	99.4	2.3	47.2	49.4	-4.0	-3.5	-23.9	-23.4
D1	foliage	66.4	9.0	42.7	45.2	-13.0	-12.3	20.6	12.0
E1	blue flower	94.4	3.4	51.2	53.8	12.6	12.6	-26.6	-24.5
F1	bluish green	60.1	16.2	66.3	68.9	-38.9	-32.9	-1.4	-16.2
A2	orange	76.3	17.1	60.7	62.3	40.4	39.0	57.1	40.1
B2	purplish blue	92.6	4.6	36.1	37.9	13.1	11.0	-49.7	-45.9
C2	moderate red	86.4	7.8	51.2	52.6	48.8	49.0	20.7	13.1
D2	purple	98.7	2.2	29.8	31.9	24.7	24.8	-20.8	-19.9
E2	yellow green	63.4	23.3	72.7	75.8	-23.7	-23.1	57.0	33.9
F2	orange yellow	77.3	17.5	69.3	71.7	19.6	16.8	71.9	54.7
A3	blue	92.7	4.9	26.6	28.2	15.1	12.1	-54.7	-51.2
B3	green	79.3	11.5	54.7	57.0	-39.9	-39.5	33.6	22.3
C3	red	91.8	5.5	42.8	43.7	52.3	52.7	29.7	24.3
D3	yellow	83.4	15.1	78.7	81.3	1.5	-2.1	86.8	72.3
E3	magenta	100.0	1.5	49.6	51.0	52.8	52.7	-1.4	-1.9
F3	cyan	99.3	2.0	48.1	50.0	-28.0	-27.3	-32.0	-31.6
A4	white	90.7	1.4	94.9	94.9	0.4	0.6	2.4	1.0
B4	neutral 8	78.2	2.9	79.1	80.4	0.1	0.2	0.0	-2.6
C4	neutral 6.5	88.1	2.6	64.9	66.9	-0.8	-0.1	-0.6	-2.1
D4	neutral 5	86.0	3.1	48.7	51.3	1.2	2.1	-0.6	-2.2
E4	neutral 3.5	84.8	3.3	34.0	36.7	0.5	1.1	-1.8	-3.6
F4	black	92.7	2.4	20.5	22.6	1.3	1.5	-2.1	-3.2
A5	paper white	100.0	0.5	97.2	97.0	0.1	0.0	1.8	2.2
B5	skin highlight L*=89	33.7	13.3	86.1	87.1	14.2	15.5	13.0	-0.2
C5	skin highlight L*=75	44.0	17.3	73.1	75.6	23.4	23.9	18.4	1.2
D5	skin shadow L*=25	88.4	3.5	26.6	28.3	17.0	17.9	13.8	10.9
E5	skin shadow L*=11	97.4	1.8	17.1	18.7	11.5	12.4	9.8	9.9
F5	Max Black	99.4	1.3	10.3	11.5	1.4	1.8	-0.2	-0.5
Summary Results		I*Color	I*tone	ΔE	AARDENBURG IMAGING & ARCHIVES				
Average Score for all patches		82.9	92.8	7.1					
Average Score for the Worst 10% (3 lowest scoring patches)		45.9	89.5	19.4					

Page 21

79.8_{color} / 91.9_{tone}



Original Print Colors
(measured before light exposure)



Colors after 180 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

180 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

				L*		a*		b*	
Column/row	Color Patch	I*Color	ΔE	Before	After	Before	After	Before	After
A1	dark Skin	71.2	6.9	36.0	38.9	16.3	17.1	11.4	5.2
B1	light Skin	58.1	11.9	63.6	66.2	21.3	22.7	15.9	4.4
C1	blue sky	99.3	2.4	47.2	49.5	-4.0	-3.4	-23.9	-23.7
D1	foliage	59.0	10.8	42.7	45.4	-13.0	-12.0	20.6	10.2
E1	blue flower	94.4	3.6	51.2	54.1	12.6	12.8	-26.6	-24.5
F1	bluish green	54.3	18.5	66.3	69.2	-38.9	-32.1	-1.4	-18.3
A2	orange	70.8	21.0	60.7	62.7	40.4	39.1	57.1	36.2
B2	purplish blue	92.3	4.9	36.1	38.1	13.1	11.0	-49.7	-45.7
C2	moderate red	83.8	9.2	51.2	52.9	48.8	49.5	20.7	11.7
D2	purple	98.8	2.3	29.8	32.0	24.7	24.9	-20.8	-20.0
E2	yellow green	54.3	28.9	72.7	76.3	-23.7	-22.4	57.0	28.3
F2	orange yellow	71.4	22.0	69.3	72.1	19.6	16.8	71.9	50.3
A3	blue	92.3	5.2	26.6	28.3	15.1	11.9	-54.7	-51.1
B3	green	74.5	14.1	54.7	57.3	-39.9	-39.4	33.6	19.8
C3	red	90.4	6.3	42.8	43.6	52.3	53.2	29.7	23.5
D3	yellow	78.8	19.2	78.7	81.8	1.5	-2.3	86.8	68.2
E3	magenta	99.4	1.7	49.6	51.1	52.8	53.0	-1.4	-2.2
F3	cyan	99.6	2.2	48.1	50.2	-28.0	-27.3	-32.0	-31.9
A4	white	91.1	1.4	94.9	95.1	0.4	0.6	2.4	1.1
B4	neutral 8	73.8	3.3	79.1	80.6	0.1	0.3	0.0	-3.0
C4	neutral 6.5	82.4	3.1	64.9	67.2	-0.8	0.1	-0.6	-2.6
D4	neutral 5	81.6	3.7	48.7	51.6	1.2	2.2	-0.6	-2.6
E4	neutral 3.5	81.1	3.8	34.0	37.1	0.5	1.3	-1.8	-3.9
F4	black	90.6	3.0	20.5	23.2	1.3	1.6	-2.1	-3.4
A5	paper white	100.0	0.5	97.2	97.2	0.1	0.0	1.8	2.3
B5	skin highlight L*=89	31.5	13.7	86.1	87.4	14.2	15.4	13.0	-0.7
C5	skin highlight L*=75	39.3	18.7	73.1	75.6	23.4	24.2	18.4	-0.2
D5	skin shadow L*=25	85.1	4.3	26.6	28.6	17.0	18.1	13.8	10.2
E5	skin shadow L*=11	95.7	1.8	17.1	18.5	11.5	12.6	9.8	9.9
F5	Max Black	98.3	1.7	10.3	11.9	1.4	1.9	-0.2	-0.5
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		79.8	91.9						
Average Score for the Worst 10% (3 lowest scoring patches)		41.7	88.6						
ΔE				Page 22					

76.8_{color} / 91.3_{tone}



Original Print Colors
(measured before light exposure)



Colors after 200 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

200 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	67.0	7.7	36.0	39.1	16.3	17.2	11.4	4.4
B1	light Skin	51.4	13.7	63.6	66.5	21.3	23.1	15.9	2.6
C1	blue sky	98.6	2.6	47.2	49.7	-4.0	-3.2	-23.9	-23.8
D1	foliage	52.5	12.4	42.7	45.7	-13.0	-11.6	20.6	8.6
E1	blue flower	93.9	3.9	51.2	54.3	12.6	12.8	-26.6	-24.3
F1	bluish green	49.8	20.3	66.3	69.3	-38.9	-31.3	-1.4	-19.9
A2	orange	65.1	25.0	60.7	62.9	40.4	39.5	57.1	32.2
B2	purplish blue	91.8	5.1	36.1	38.2	13.1	11.0	-49.7	-45.5
C2	moderate red	81.1	10.6	51.2	53.0	48.8	49.7	20.7	10.3
D2	purple	98.7	2.5	29.8	32.1	24.7	24.9	-20.8	-20.0
E2	yellow green	46.2	33.9	72.7	76.7	-23.7	-21.6	57.0	23.4
F2	orange yellow	65.2	26.6	69.3	72.4	19.6	17.1	71.9	45.6
A3	blue	92.0	5.3	26.6	28.3	15.1	11.9	-54.7	-50.9
B3	green	69.0	16.9	54.7	57.5	-39.9	-39.0	33.6	17.0
C3	red	88.8	7.3	42.8	43.8	52.3	53.2	29.7	22.5
D3	yellow	73.4	23.8	78.7	82.1	1.5	-2.4	86.8	63.5
E3	magenta	99.1	2.0	49.6	51.3	52.8	52.9	-1.4	-2.4
F3	cyan	99.1	2.3	48.1	50.3	-28.0	-27.1	-32.0	-32.0
A4	white	91.7	1.3	94.9	95.2	0.4	0.5	2.4	1.1
B4	neutral 8	71.4	3.6	79.1	80.6	0.1	0.5	0.0	-3.2
C4	neutral 6.5	76.9	3.6	64.9	67.3	-0.8	0.3	-0.6	-3.0
D4	neutral 5	76.8	4.1	48.7	51.8	1.2	2.4	-0.6	-3.0
E4	neutral 3.5	77.3	4.2	34.0	37.3	0.5	1.4	-1.8	-4.3
F4	black	88.1	3.2	20.5	23.3	1.3	1.8	-2.1	-3.6
A5	paper white	99.6	0.5	97.2	97.2	0.1	0.0	1.8	2.3
B5	skin highlight L*=89	30.0	14.0	86.1	87.5	14.2	15.5	13.0	-0.9
C5	skin highlight L*=75	34.9	20.0	73.1	75.8	23.4	24.4	18.4	-1.5
D5	skin shadow L*=25	82.1	4.9	26.6	28.7	17.0	18.1	13.8	9.5
E5	skin shadow L*=11	95.5	1.9	17.1	18.6	11.5	12.6	9.8	9.5
F5	Max Black	96.9	1.9	10.3	12.1	1.4	2.0	-0.2	-0.7
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		76.8	91.3						
Average Score for the Worst 10% (3 lowest scoring patches)		37.0	88.1						

73.6_{color} / 90.6_{tone}



Original Print Colors
(measured before light exposure)



Colors after 220 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

220 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	62.3	8.7	36.0	39.3	16.3	17.4	11.4	3.5
B1	light Skin	44.7	15.5	63.6	66.7	21.3	23.6	15.9	0.9
C1	blue sky	97.9	2.8	47.2	49.8	-4.0	-3.0	-23.9	-24.1
D1	foliage	45.4	14.2	42.7	45.9	-13.0	-11.2	20.6	6.9
E1	blue flower	94.0	4.0	51.2	54.5	12.6	13.0	-26.6	-24.4
F1	bluish green	46.2	21.7	66.3	69.4	-38.9	-30.6	-1.4	-21.1
A2	orange	58.5	29.6	60.7	63.0	40.4	39.9	57.1	27.5
B2	purplish blue	91.6	5.3	36.1	38.3	13.1	11.0	-49.7	-45.3
C2	moderate red	78.0	12.3	51.2	53.0	48.8	50.1	20.7	8.6
D2	purple	98.9	2.5	29.8	32.2	24.7	25.0	-20.8	-20.1
E2	yellow green	37.9	39.1	72.7	76.9	-23.7	-20.7	57.0	18.3
F2	orange yellow	58.4	31.7	69.3	72.7	19.6	17.5	71.9	40.4
A3	blue	91.7	5.5	26.6	28.3	15.1	11.7	-54.7	-50.8
B3	green	62.5	20.3	54.7	57.8	-39.9	-38.4	33.6	13.6
C3	red	86.7	8.5	42.8	43.7	52.3	53.4	29.7	21.2
D3	yellow	68.0	28.5	78.7	82.4	1.5	-2.3	86.8	58.7
E3	magenta	98.3	2.2	49.6	51.3	52.8	53.1	-1.4	-2.8
F3	cyan	98.6	2.5	48.1	50.4	-28.0	-26.9	-32.0	-32.2
A4	white	90.8	1.4	94.9	95.1	0.4	0.6	2.4	1.0
B4	neutral 8	69.3	3.8	79.1	80.7	0.1	0.6	0.0	-3.4
C4	neutral 6.5	70.9	4.1	64.9	67.5	-0.8	0.4	-0.6	-3.6
D4	neutral 5	71.9	4.6	48.7	52.0	1.2	2.5	-0.6	-3.4
E4	neutral 3.5	72.9	4.6	34.0	37.4	0.5	1.7	-1.8	-4.6
F4	black	84.0	3.5	20.5	23.3	1.3	1.8	-2.1	-4.0
A5	paper white	100.0	0.4	97.2	97.1	0.1	0.1	1.8	2.2
B5	skin highlight L*=89	29.0	14.2	86.1	87.5	14.2	15.5	13.0	-1.1
C5	skin highlight L*=75	32.2	20.8	73.1	75.7	23.4	24.5	18.4	-2.3
D5	skin shadow L*=25	78.4	5.7	26.6	28.7	17.0	18.2	13.8	8.7
E5	skin shadow L*=11	93.9	2.0	17.1	18.5	11.5	12.8	9.8	9.3
F5	Max Black	95.8	2.0	10.3	12.1	1.4	2.0	-0.2	-0.8
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		73.6	90.6						
Average Score for the Worst 10% (3 lowest scoring patches)		33.0	86.8						

70.9_{color} / 90.0_{tone}



Original Print Colors
(measured before light exposure)



Colors after 240 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

240 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	57.5	9.6	36.0	39.6	16.3	17.7	11.4	2.6
B1	light Skin	40.0	16.8	63.6	67.1	21.3	23.8	15.9	-0.3
C1	blue sky	97.2	3.2	47.2	50.2	-4.0	-2.9	-23.9	-24.3
D1	foliage	39.7	15.6	42.7	46.2	-13.0	-10.9	20.6	5.6
E1	blue flower	93.9	4.3	51.2	54.9	12.6	13.1	-26.6	-24.4
F1	bluish green	43.4	22.8	66.3	69.6	-38.9	-30.0	-1.4	-22.1
A2	orange	52.9	33.5	60.7	63.2	40.4	40.4	57.1	23.6
B2	purplish blue	91.1	5.7	36.1	38.6	13.1	11.0	-49.7	-45.1
C2	moderate red	74.7	14.0	51.2	53.3	48.8	50.2	20.7	6.9
D2	purple	99.1	2.7	29.8	32.4	24.7	25.1	-20.8	-20.2
E2	yellow green	30.8	43.5	72.7	77.3	-23.7	-19.7	57.0	14.0
F2	orange yellow	51.9	36.5	69.3	73.1	19.6	17.8	71.9	35.6
A3	blue	92.2	5.2	26.6	28.4	15.1	11.9	-54.7	-51.0
B3	green	55.9	23.7	54.7	58.1	-39.9	-37.6	33.6	10.3
C3	red	84.4	10.0	42.8	44.1	52.3	53.4	29.7	19.8
D3	yellow	62.6	33.2	78.7	82.8	1.5	-2.2	86.8	54.0
E3	magenta	97.5	2.7	49.6	51.6	52.8	53.2	-1.4	-3.2
F3	cyan	98.0	2.8	48.1	50.6	-28.0	-26.7	-32.0	-32.5
A4	white	90.4	1.5	94.9	95.3	0.4	0.5	2.4	1.0
B4	neutral 8	68.5	3.9	79.1	80.9	0.1	0.6	0.0	-3.4
C4	neutral 6.5	67.2	4.6	64.9	67.8	-0.8	0.5	-0.6	-3.9
D4	neutral 5	66.9	5.2	48.7	52.4	1.2	2.6	-0.6	-3.9
E4	neutral 3.5	68.2	5.1	34.0	37.7	0.5	1.7	-1.8	-5.1
F4	black	81.9	3.9	20.5	23.7	1.3	1.9	-2.1	-4.2
A5	paper white	100.0	0.4	97.2	97.3	0.1	0.0	1.8	2.2
B5	skin highlight L*=89	29.0	14.2	86.1	87.8	14.2	15.4	13.0	-1.1
C5	skin highlight L*=75	29.8	21.6	73.1	76.0	23.4	24.6	18.4	-3.0
D5	skin shadow L*=25	75.0	6.5	26.6	29.0	17.0	18.3	13.8	8.0
E5	skin shadow L*=11	92.4	2.4	17.1	18.8	11.5	12.8	9.8	8.9
F5	Max Black	94.4	2.3	10.3	12.4	1.4	2.1	-0.2	-1.0
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		70.9	90.0						
Average Score for the Worst 10% (3 lowest scoring patches)		29.9	86.1						

68.9_{color} / 89.7_{tone}



Original Print Colors
(measured before light exposure)




Colors after 260 Megalux-hours
light exposure

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*

260 Mlux-hrs Light Exposure (i.e., after) Compared to Original Print Colors (i.e., before)

Column/row	Color Patch	I*Color	ΔE	L*		a*		b*	
				Before	After	Before	After	Before	After
A1	dark Skin	54.7	10.3	36.0	39.8	16.3	17.9	11.4	2.0
B1	light Skin	38.1	17.3	63.6	67.1	21.3	24.1	15.9	-0.8
C1	blue sky	95.8	3.4	47.2	50.2	-4.0	-2.5	-23.9	-24.2
D1	foliage	33.8	17.0	42.7	46.3	-13.0	-10.4	20.6	4.2
E1	blue flower	92.0	4.8	51.2	55.0	12.6	13.2	-26.6	-23.8
F1	bluish green	41.2	23.6	66.3	69.4	-38.9	-29.3	-1.4	-22.7
A2	orange	47.7	37.2	60.7	63.4	40.4	41.1	57.1	20.0
B2	purplish blue	90.5	5.9	36.1	38.6	13.1	11.1	-49.7	-44.7
C2	moderate red	73.1	14.9	51.2	53.5	48.8	50.5	20.7	6.1
D2	purple	98.3	3.0	29.8	32.6	24.7	25.2	-20.8	-19.9
E2	yellow green	24.2	47.5	72.7	77.5	-23.7	-18.7	57.0	10.0
F2	orange yellow	46.1	40.9	69.3	73.3	19.6	18.5	71.9	31.2
A3	blue	91.3	5.8	26.6	28.5	15.1	11.9	-54.7	-50.4
B3	green	48.6	27.6	54.7	58.2	-39.9	-36.4	33.6	6.5
C3	red	83.3	10.6	42.8	44.2	52.3	53.6	29.7	19.2
D3	yellow	56.6	38.4	78.7	83.0	1.5	-1.8	86.8	48.8
E3	magenta	98.2	2.6	49.6	51.7	52.8	53.2	-1.4	-2.8
F3	cyan	96.7	3.2	48.1	50.7	-28.0	-26.1	-32.0	-32.5
A4	white	95.0	1.0	94.9	95.2	0.4	0.5	2.4	1.4
B4	neutral 8	72.6	3.6	79.1	80.9	0.1	0.7	0.0	-3.0
C4	neutral 6.5	66.3	4.8	64.9	67.9	-0.8	0.7	-0.6	-3.9
D4	neutral 5	63.8	5.5	48.7	52.5	1.2	2.9	-0.6	-4.1
E4	neutral 3.5	66.0	5.5	34.0	38.1	0.5	2.0	-1.8	-5.2
F4	black	78.4	4.2	20.5	23.8	1.3	2.0	-2.1	-4.5
A5	paper white	96.8	0.8	97.2	97.1	0.1	0.0	1.8	2.6
B5	skin highlight L*=89	32.5	13.6	86.1	87.9	14.2	15.2	13.0	-0.5
C5	skin highlight L*=75	30.3	21.4	73.1	76.1	23.4	24.7	18.4	-2.8
D5	skin shadow L*=25	72.3	7.1	26.6	29.2	17.0	18.4	13.8	7.4
E5	skin shadow L*=11	91.1	2.9	17.1	19.4	11.5	12.6	9.8	8.4
F5	Max Black	92.0	2.4	10.3	12.4	1.4	2.2	-0.2	-1.2
Summary Results		I*Color	I*tone	 AARDENBURG IMAGING & ARCHIVES					
Average Score for all patches		68.9	89.7						
Average Score for the Worst 10% (3 lowest scoring patches)		29.0	85.1						

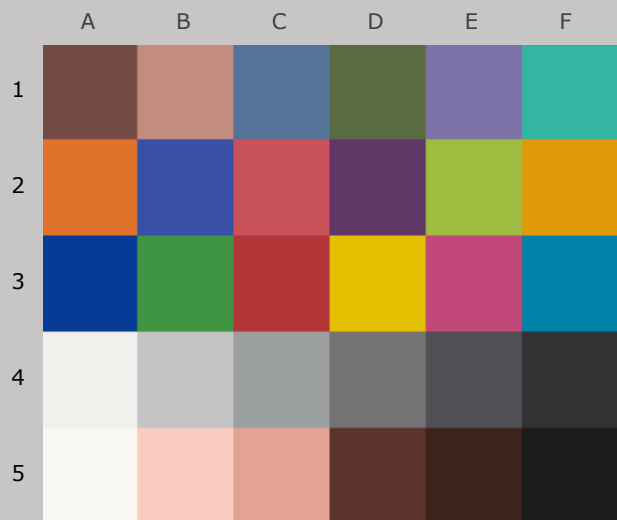

Original Print Colors
(measured before light exposure)



Test Complete

No further updates

*Epson 4800 Printer, Epson OEM ink (Ultrachrome K3),
Crane Museo Silver Rag 300gsm Paper*



AARDENBURG IMAGING
& ARCHIVES